

**AASHTO's
National Transportation
Product Evaluation
Program**

Report NTPEP 8001.42

**LABORATORY RESULTS OF EVALUATIONS ON
GEOTEXTILES & GEOSYNTHETICS
(JULY 2008 TO DECEMBER 2010 CYCLE 4)**

AASHTO
THE VOICE OF TRANSPORTATION

April 2011

American Association of State Highway and Transportation Officials (AASHTO)

444 North Capitol Street, NW, Suite 249 - Washington, DC - 20001 - (t) 202.624.5800 - (f) 202.624.5469 - www.NTPEP.ORG

PROLOGUE

General Facts about NTPEP Reports,

- ❖ NTPEP Reports contain data collected according to laboratory testing and field evaluation protocols developed through consensus-based decision by the AASHTO's NTPEP Committee. These test and evaluation protocols are described in the *Project Work Plan* found in the Appendix of this Report.
- ❖ Products are voluntarily submitted by manufacturers for testing by NTPEP. Testing fees are assessed from manufacturers to reimburse AASHTO member departments for conducting testing and to report results. AASHTO member departments provide a voluntary yearly contribution to support the administrative functions of NTPEP.
- ❖ AASHTO/NTPEP does not endorse any manufacturer's product over another. Use of certain proprietary products as "test control specimens" does not constitute endorsement of those products.
- ❖ AASHTO/NTPEP does not issue product approval or disapproval; rather, test data is furnished for the User to make judgment for product prequalification or approval for their transportation agency.

Guidelines for Proper Use of NTPEP Results,

- ❖ The User is urged to carefully read any introductory notes at the beginning of this Report. Also, to consider any special clauses, footnotes or conditions which may apply to any test reported herein. Any of these notes may be relevant to the proper use of NTPEP test data.
- ❖ The User of this Report must be sufficiently familiar with the product performance requirements and/or (standard) specification of their agency in order to determine which test data is relevant to meeting those qualifying factors.
- ❖ NTPEP test data is intended to be predictive of actual product performance. Where a transportation agency has successful historical experience with a given product it is suggested to factor that precedence in granting or withholding product approval or prequalification.

NTPEP Report Special Advisory for Geotextiles (GTX),

- ❖ Products included in this edition of **NTPEP Report 8001** are required to resubmit to NTPEP every three (3) years for qualification. Hence, all products included in this Report supercede previous Editions of **NTPEP Report 8001**.
- ❖ The User is guided to read the Minimum Average Roll Values (MARV) Advisory provided in the introductory text of this Report.
- ❖ For specific questions regarding this NTPEP Report or for advice on how to implement NTPEP data furnished in this Report the User is encouraged to contact the NTPEP Manager at (202) 624-7830 for a listing of NTPEP Lead States.

Tony Allen (Washington State DOT)
Chairman, Geotextiles Technical Committee

Jim Curtis (New York State DOT)
Vice Chairman, Geotextiles Technical Committee

2011 NTPEP Report Series



Laboratory Evaluation by:

New York State DOT and TRI

Report Review by:

New York State Department of Transportation

© Copyright 2011, by the American Association of State Highway and Transportation Officials (AASHTO). *All Rights Reserved.* Printed in the United States of America. This book or parts thereof, may not be reproduced without express written permission of the publisher. The report does not constitute an endorsement by AASHTO of the products contained herein. This report provides an original source of technical information to facilitate development of acceptability standards and is primarily intended for use by state and local transportation agencies.

American Association of State Highway and Transportation Officials (AASHTO)

Executive Office: 444 North Capitol Street, NW, Suite 249 • Washington, DC • 20001
(t) 202.624.5800 • (f) 202.624.5469 • www.NTPEP.ORG

Table of Contents

Title	Page
Introduction	1-3
Micrographs on Fabric Structure.....	4
Test Results by Manufacturer	Page
Assurance Corporation.....	5
BBA FiberWeb.....	6
Belton Industries.....	7
Carthage Mills, Inc.	8-10
Contech Construction Products, Inc.....	11
Crown Resources (formerly TNS Advanced Technologies)	12
DALCO Nonwovens	13
DDD Erosion Control, Inc.	14-15
DGI Industries, Inc.	16
Don & Low, LTD.....	17
Edge Tech, LLC	18
GEO Fabrics, LLC	19
GSE Lining Technologies	20
Hanes GEO (formerly Webtec and Ikex).....	21-23
Indian Valley Industries, Inc.	24
Kintex	25
Mattex.....	26
Performance Fabrics and Fibers LLC	27
Poly Industrial Products, Inc.	28
Propex Inc. (formerly MIRAFI Construction Products).....	29-31
Silt Saver, Inc.	32
Skaps Industries.....	33-34
Spilo PTY, LTD.	35
SRW Products	36
TenCate Geosynthetics (formerly MIRAFI Construction Products).....	37-40
Thrace-LINQ, Inc.	41-44
US Fabrics	45-46
Vantage Partners, LLC.....	47
Western Excelsior.....	48-49
Willacoochee Industrial Fabrics.....	50-52
Appendix A- NTPEP Committee Roster	53-57

INTRODUCTION

The purpose of the American Association of State Highway and Transportation Officials (AASHTO) National Transportation Product Evaluation Program (NTPEP) is to provide an efficient, cost effective way of evaluating products that are used by member transportation departments in the construction of transportation facilities.

Manufacturers/suppliers wishing to have their products considered for use on transportation projects submit their materials to a lead State agency, which coordinates a testing program by one or more testing facilities. A report is generated showing the results of the testing, and is distributed to member departments for their use in determining the applicability of the products for use in their State.

GEOTEXTILE PROGRAM

For the geotextile program, New York State Department of Transportation acts as the lead State. After conducting a national survey, the AASHTO/NTPEP Geotextile Panel selected the following tests for inclusion in the program:

Test	ASTM Designation
Permittivity	D4491
Apparent Opening Size	D4751
Grab Strength/Elongation	D4632
Mass/Unit Area	D5261
Puncture Resistance	D4833 ¹
Static Puncture – 50mm Probe	D6241 ²
Trapezoid Tear Strength	D4833
UV Stability	D4355 ³

¹ Test Cycle 05-09 and all preceding cycles.

² Test Cycle 06-01 and all subsequent cycles.

³ Test Cycle 09-01 and all subsequent cycles.

Once an application for testing has been received and approved by the NTPEP Manager, each material is assigned an NTPEP GTX number. The lead State makes arrangements to have the material sampled, the material is sent to the lead State for preparation and distribution to the other test centers (when applicable), the testing is completed, the results are summarized by the lead State and forwarded to the NTPEP Manager.

Sampling is monitored by a DoT representative from the State where the manufacturer/supplier is located, or by an NTPEP-approved independent monitor if the manufacturer/supplier is located outside of the U.S. Sampling consists of obtaining five samples, each three feet long by roll width, taken from a single representative roll of each style designation to be tested. The lead State agency laboratory prepares one set of specimens for each test, from three of the five samples. The number of specimens is based on the requirements of the individual test procedure. The remaining two samples are stored for use in the event a manufacturer appeals the initial test results.

Each manufacturer/supplier receives a Draft Final Report for review. If a manufacturer/supplier appeals the results, the original testing laboratory will be provided another set of specimens, from the fourth sample, on which to perform a second round of testing. If the test results from the second round are questioned, one of the other test centers (if applicable) will be asked to perform tests on specimens from the fifth sample.

The lead State keeps on file the results of the testing for the individual specimens. The Report contains the average of these results.

When a firm sells their products under a private label agreement with another manufacturer, the private label firm submits an application to NTPEP identifying the original product designation, their designation and a letter of certification from the primary manufacturer verifying the information. A Report is issued under the private label firm's name and material designations. The results that are reported are those which were obtained on the materials as submitted by the primary manufacturer.

NTPEP GTX code explanation for products tested prior to 2010, the GTX code is as follows: The NTPEP Manager assigns sample numbers (GTX YY-MM-xx) to products as applications are approved for a testing cycle. The explanation of numbering is as follows: "GTX" refers to the geotextile products evaluation program; "YY" refers to the last two digits of the calendar year (eg YY = 08, 09, 10, etc); "MM" refers to the submission month of the program ("01" = January, "04" = April, etc.); "xx" represents sequential sample numbers which are assigned to samples listed on the application. In the tables, missing sequential numbers may indicate the testing of a particular material is incomplete, or the manufacturer withdrew the material from the program prior to testing. The results for the incomplete testing will be included in the report edition following completion of the testing. Starting in 2010, the GTX code is the following (Year(YYYY)-Testing Cycle (XX)-Sample Number(XXX)). For example, 2010-02-023 represents a product that was twenty-third product tested in the second cycle of 2010.

Each Final Report issued for a testing cycle will include all results from previous submissions so that all the information obtained during the three year test cycle will be in one report, and easily accessible. Also contained in the report will be the product Drop Date (month and year). This month and year indicates when the product data will no longer be reported in NTPEP reports

NOTE: 36th Edition is the first Edition to include the Drop Date. All future additions will include current products as per the publish date and the three year cycle.

ADVISORIES

Since a private label company must identify their geotextile supplier in the AASHTO/NTPEP submission process, this source must not change throughout the three-year reporting period without written notification to AASHTO, thirty days prior to delivery of geotextiles from the new supplier. If written notification is not provided, the State should notify AASHTO and the product will be removed from the report immediately.

The data shown in this report are averages of test results of specimens taken from laboratory samples of each product designation submitted. These results should not be considered minimum, minimum average roll values (MARV), or typical values, nor should they be used as the sole criterion for material acceptance. It is strongly suggested that a project quality assurance program be established by agencies using the product information in this report.

MARV values found in the report are as provided by the manufacturer in their submission. The product NTPEP test results summarized in the table (mean, COV) only represent the sample tested and do not represent the property statistics for the product in general. The test results summarized in the table only demonstrate whether or not the properties of the sample tested meet or exceed the MARV's provided by the manufacturer as representative of their product. Therefore, the NTPEP test results and associated statistics summarized in the table should not be used to estimate a MARV for the product or be considered characteristic of the product properties.


MISCELLANEOUS INFORMATION - The following pictures are of various manufactured structures of geotextiles.



Micrograph of a Needle-Punched Non-Woven Geotextile



Micrograph of a Slit-film Woven Geotextile

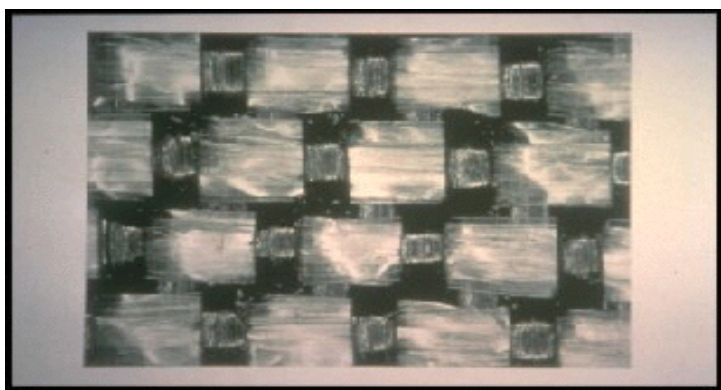

Micrograph of a Monofilament Woven Geotextile w/ Fibrillated Yarn

Manufacturer: Assurene Corporation

Contact Info: Larry Hale

269 Angela Drive SE

Smyrna, GA 30082

Phone:(770) 335-4127

Fax:

Email: larryh@aassurene.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jan-13	ASR-8100	Cir-W	09-04-07	Mean	124	24	146	22	71	64	423	0.22	0.33	3.0	94	90
				COV (%)	10.7%	NA	6.9%	NA	19.9%	7.8%	4.1%	18.4%	12.2%	2.0%		
				MARV	124	NA	124	NA	65	65	NA	0.05	0.60	NA	80%	80%
Jan-13	ASR-8200	SF-W	09-04-08	Mean	244	24	196	18	101	88	764	0.16	0.29	4.3	Not Tested	Not Tested
				COV (%)	3.8%	NA	4.2%	NA	14.6%	5.3%	5.3%	23.8%	20.6%	1.6%		
				MARV	200	NA	200	NA	75	75	725	0.1	0.425	NA	80%	80%
Jan-13	ASR-8300	SF-W	09-04-09	Mean	376	28	370	22	167	126	1329	0.13	0.33	7.2	Not Tested	Not Tested
				COV (%)	7.8%	NA	4.3%	NA	5.4%	7.2%	3.1%	10.0%	9.1%	1.1%		
				MARV	315	NA	315	NA	120	120	1100	0.05	0.425	NA	80%	80%
Jan-13	ASR-8080	Cir-W	09-10-01	Mean	124	38	140	35	45	48	263	0.10	0.32	2.1	57	75
				COV (%)	5.2%	NA	2.2%	NA	10.1%	9.0%	4.9%	26.1%	9.4%	2.3%	NA	NA
				MARV	100	NA	100	NA	50	50	350	0.10	0.85	2.2	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **BBA Fiberweb**

Contact Info: Mr. Robert Whitlock
 70 Old Hickory Blvd.
 Old Hickory, TN 37138
 Phone:(615) 847-7000

Fax: (615) 847-7068

Email: rwhitlock@fiberweb.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	TYPAR 3341G	HB-NW	07-09-01	Mean	130	88	141	78	48	59	249	1.6	0.28	3.5		
				COV (%)	11.5%		7.8%		14.6%	25.4%	8.0%	8.8%	0.0%	4.6%		
				MARV												
Jul-11	TYPAR 3401G	HB-NW	07-09-02	Mean	153	101	169	92	79	76	262	1.42	0.21	3.9		
				COV (%)	11.1%		6.5%		20.3%	15.8%	10.7%	3.5%	0.0%	3.6%		
				MARV												
Jul-11	TYPAR 3501G	HB-NW	07-09-03	Mean	179	101	229	76	103	118	351	0.71	0.15	4.8		
				COV (%)	14.5%		5.2%		9.7%	12.7%	10.5%	15.5%	6.7%	6.0%		
				MARV												
Jul-11	TYPAR 3601G	HB-NW	07-09-04	Mean	292	90	252	81	124	127	437	0.25	0.08	6		
				COV (%)	11.3%		12.3%		7.3%	13.4%	8.9%	20.0%	12.5%	4.7%		
				MARV												
Jul-11	TYPAR 3631G	HB-NW	07-09-05	Mean	307	86	285	78	109	137	517	0.23	0.07	6		
				COV (%)	7.8%		16.1%		17.4%	14.6%	7.0%	8.7%	0.0%	3.7%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Belton Industries

Contact Info: Mr. Bob Moran

P.O. Box 127

Belton, SC 29627

Phone:(770) 587-0257

Fax: (770) 992-6361

Email: Bmoran@beltonindustries.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	BELTECH 2x2	SF-W	07-06-08	Mean	381	33	318	20	179	137	1205	0.46	0.42	7.3		
				COV (%)	3.9%		2.5%		5.6%	5.1%	4.8%	15.2%	1.0%	0.7%		
				MARV												
Sep-11	BELTECH 4x4	SF-W	08-01-34	Mean	715	32	581	21	331	258	1690	0.39	0.39	12.9		
				COV (%)	3.8%		4.3%		13.9%	8.9%	7.2%	7.7%	2.6%	0.2%		
				MARV												
Jun-12	1980	SF-W	09-04-03	Mean	235	28	200	17	108	102	892	0.35	0.41	4.7	Not Tested	Not Tested
				COV (%)	3.4%		4.0%		3.7%	10.8%	2.9%	8.6%	4.9%	4.9%		
				MARV									4	70	70	
Jun-12	1475	SF-W	09-04-04	Mean	268	28	274	22	113	115	1073	0.35	0.52	5.5	Not Tested	Not Tested
				COV (%)	4.9%		7.3%		8.0%	3.5%	3.0%	5.7%	9.6%	0.5%		
				MARV	250		250		90	90		0.05	0.6	4.9	70	70
Jun-12	977	SF-W	09-04-05	Mean	335	29	326	22	153	123	1318	0.15	0.33	6.5	Not Tested	Not Tested
				COV (%)	4.5%		4.6%		6.5%	5.7%		13.3%	12.1%	0.8%		
				MARV	315		315		120	115		0.05	0.5	6	70	70
Jun-12	940	SF-W	09-04-06	Mean	146	33	107	20	78	60	474	0.19	0.4	2.9	85	98
				COV (%)	3.4%		6.5%		14.1%	13.3%	5.3%	10.5%	2.5%	0.7%		
				MARV	125		101		55	55		0.05	0.6	2.75	70	70
Jan-13	BELTECH 1935	SF-W	09-10-02	Mean	139	24	118	16	77	64	545	0.48	0.42	3.5	85	89
				COV (%)	10.3%	NA	14.7%	NA	11.3%	7.5%	6.0%	25.2%	24.0%	1.7%	NA	NA
				MARV	125	NA	115	NA	70 (ave)	70 (ave)	NA	NA	0.6	NA	70	70
Apr-13	BELTECH 884	SF-W	2010-01-005	Mean	558	38	597	32	219	228	1920	0.21	0.41	8.9	Not Tested	Not Tested
				COV (%)	3.5%	NA	3.5%	NA	5.4%	6.0%	2.5%	8.9%	2.5%	0.4%	NA	NA
				MARV	490	NA	530	NA	170	200	NA	0.05	0.5	9.0	70	70
Apr-11	1853 4x6	SF-W	2010-04-015	Mean	768	36	846	22	366	491	2967	0.54	0.40	16.8	Not Tested	Not Tested
				COV (%)	3.5%	NA	2.6%	NA	6.4%	22.5%	6.1%	12.2%	2.5%	0.2%	NA	NA
				MARV	650	NA	710	NA	270	300	280	0.30	0.43	16.0	NA	NA
Apr-11	Beltech 2x2	SF-W	2010-04-017	Mean	386	35	298	22	167	122	1421	0.41	0.41	7.2	Not Tested	Not Tested
				COV (%)	6.0%	NA	5.4%	NA	6.0%	4.2%	3.0%	12.4%	6.8%	1.0%	NA	NA
				MARV	370	NA	300	NA	150	130	200	0.35	0.60	7.3	NA	NA

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Carthage Mills, Inc**

Contact Info: Toni Haines
 4243 Hunt Rd.
 Cincinnati, OH 45242
 Phone:(513) 794-1600

Fax: Email: thaines@carthagemills.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355			
					MD		XD		Strength (lbs)		MD	XD	Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD								
Sep-11	FX-40HS-C	NP-NW	07-09-42	Mean	139	76	134	74	53	71	323	2.61	0.19	4.4				
				COV (%)	11.5%		9.7%		17.0%	8.5%	15.5%	18.4%	5.3%	2.3%				
				MARV														
Sep-11	FX-38A/O	NP-NW	07-09-43	Mean	126	67	154	67	50	82	347	2.23	0.2	4.9				
				COV (%)	7.9%		10.4%		10.0%	4.9%	5.8%	5.8%	5.0%	2.0%				
				MARV														
Sep-11	FX-11	SF-W	07-09-44	Mean	134	18	108	24	83	70	363	0.16	0.27	2.8				
				COV (%)	7.5%		15.7%		14.5%	7.1%	3.9%	31.3%	11.1%	0.7%				
				MARV														
Sep-11	FX-370TF	SF-W	07-09-45	Mean	475	24	428	16	216	155	1556	0.23	0.3	9.7				
				COV (%)	4.4%		4.9%		8.3%	7.1%	10.1%	34.8%	6.7%	1.0%				
				MARV														
Sep-11	FX-400TF	SF-W	07-09-46	Mean	719	29	691	21	321	222	2200	0.19	0.17	12.7				
				COV (%)	3.5%		3.0%		6.5%	2.3%	10.6%	21.1%	5.9%	0.8%				
				MARV														
Mar-12	FX-50HS	NP-NW	09-01-26	Mean	167	59	156	73	71	83	498	2.2	0.16	5.9	Not Tested	Not Tested		
				COV (%)	10.2%		14.7%		8.5%	14.5%	9.4%	18.2%	6.3%	3.4%				
				MARV														
Mar-12	FX-80HS	NP-NW	09-01-27	Mean	263	64	258	76	119	143	634	1.2	0.14	6.8	Not Tested	Not Tested		
				COV (%)	9.1%		9.3%		12.6%	11.2%	5.4%	8.3%	7.1%	5.9%				
				MARV														
Mar-12	FX-100HS	NP-NW	09-01-28	Mean	305	89	467	70	150	245	1063	1.3	0.14	11.9	Not Tested	Not Tested		
				COV (%)	15.1%		13.7%		12.0%	13.5%	14.8%	15.4%	7.1%	10.9%				
				MARV														
Mar-12	FX-120HS	NP-NW	09-01-29	Mean	326	86	571	64	163	281	1296	1.1	0.16	13.4	Not Tested	Not Tested		
				COV (%)	8.0%		4.2%		25.8%	13.2%	8.3%	9.1%	6.3%	6.0%				
				MARV														
Jun-12	FX-42A/O	NP-NW	09-01-30	Mean	118	74	140	78	50	60	330	2.30	0.15	4.9	Not Tested	Not Tested		
				COV (%)	10.2%		5.7%		12.0%	11.7%	8.5%	6.5%	6.8%	2.7%				
				MARV	105	NA	105	NA	45	45	NA	NA	NA	4.1	70	70		

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Carthage Mills, Inc**

Contact Info: Toni Haines
4243 Hunt Rd.
Cincinnati, OH 45242
Phone:(513) 794-1600

Fax: Email: thaines@carthagemills.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jun-12	Carthage 4%-HD	MF-W	09-01-31	Mean	444	22	358	21	275	298	1361	1.10	0.42	8.8	Not Tested	Not Tested
				COV (%)	7.2%		5.9%		4.7%	12.8%	11.4%	6.4%	0.2%	0.6%		
				MARV	400	NA	315	NA	150	165	1150	0.90	0.43	8.0	90	90
Jun-12	Carthage 6%	MF-W	09-01-32	Mean	496	36	278	31	192	77	1064	0.76	0.21	6.3	Not Tested	Not Tested
				COV (%)	3.6%		4.3%		6.8%	10.4%	3.5%	5.3%	0.0%	0.3%		
				MARV	370	NA	250	NA	100	60	950	0.28	0.21	5.6	90	90
Jun-12	Carthage 15%	MF-W	09-01-33	Mean	430	35	234	16	191	106	737	2.70	0.44	6.0	94	96
				COV (%)	3.7%		3.4%		11.0%	5.7%	16.4%	7.8%	18.2%	0.7%		
				MARV	365	NA	200	NA	115	75	675	2.10	0.43	5.6	90	90
Mar-12	FX-200MF	C-W	09-01-34	Mean	399	24	335	17	147	111	1315	0.6	0.41	7.4	Not Tested	Not Tested
				COV (%)	3.8%		3.6%		9.5%	8.1%	9.5%	6.7%	2.4%	1.4%		
				MARV												
Jun-12	FX-370MF	MF-W	09-01-35	Mean	503	34	301	22	273	150	1565	0.53	0.36	9.8	Not Tested	Not Tested
				COV (%)	3.4%		5.0%		7.0%	7.3%	19.0%	13.2%	8.3%	0.7%		
				MARV	400	NA	250	NA	180	110	NA	0.52	0.60	8.5	70	70
Jun-12	FX-400MF	MF-W	09-01-36	Mean	521	23	484	23	253	343	1389	0.68	0.59	13.9	Not Tested	Not Tested
				COV (%)	6.0%		11.8%		9.5%	16.6%	11.3%	13.2%	0.3%	0.6%		
				MARV	475	NA	440	NA	180	180	NA	0.40	0.60	14.5	70	70
Jun-12	FX-465MF	MF-W	09-01-37	Mean	504	24	384	25	196	224	1450	0.63	0.40	8.6	Not Tested	Not Tested
				COV (%)	5.0%		12.5%		7.1%	10.3%	9.0%	14.3%	2.5%	1.4%		
				MARV	450	NA	350	NA	140	175	NA	0.26	0.43	10.1	70	70
Jun-12	FX-270TF	SF-W	09-01-38	Mean	360	27	338	24	149	155	1278	0.31	0.28	6.7	Not Tested	Not Tested
				COV (%)	2.8%		5.9%		4.7%	7.1%	5.1%	12.9%	3.6%	1.2%		
				MARV	350	NA	350	NA	120	120	1000	0.27	0.50	6.9	80	80
Jun-12	FX-46A/O	NP-NW	09-04-16	Mean	125	76	152	77	55	77	414	1.98	0.15	4.9	Not Tested	Not Tested
				COV (%)	9.8%	NA	9.5%	NA	14.7%	12.4%	6.4%	20.4%	1.4%	4.1%		
				MARV	120	NA	120	NA	50	50	NA	NA	NA	4.6	70	70
Sep-12	FX-30HS	NP-NW	09-07-35	Mean	98	63	96	99	53	60	268	2.38	0.24	3.6	94	86
				COV (%)	14.1%	NA	16.1%	NA	12.5%	17.2%	14.9%	26.4%	15.0%	10.5%		
				MARV	80	NA	80	NA	30	30	210	2.00	0.30	2.5	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Carthage Mills, Inc**

Contact Info: Toni Haines
 4243 Hunt Rd.
 Cincinnati, OH 45242
 Phone:(513) 794-1600

Fax: Email: thaines@carthagemills.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-12	FX-40HS	NP-NW	09-07-36	Mean	116	62	150	80	59	80	392	2.41	0.21	4.4	Not Tested	Not Tested
				COV (%)	8.6%	NA	14.4%	NA	13.6%	20.0%	6.9%	17.3%	0.7%	2.5%		
				MARV	115	NA	115	NA	50	50	310	2.00	0.212	3.5	70	70
Sep-12	FX-45HS	NP-NW	09-07-37	Mean	126	64	126	105	65	83	360	2.49	0.24	4.2	Not Tested	Not Tested
				COV (%)	10.7%	NA	13.6%	NA	13.4%	15.0%	16.0%	16.7%	8.1%	5.7%		
				MARV	120	NA	120	NA	50	50	335	1.50	0.212	4.0	70	70
Sep-12	FX-60HS	NP-NW	09-07-38	Mean	216	82	171	93	116	131	455	1.50	0.16	5.6	Not Tested	Not Tested
				COV (%)	8.3%	NA	22.5%	NA	17.1%	15.0%	10.2%	12.0%	9.5%	7.2%		
				MARV	160	NA	160	NA	60	60	410	1.50	0.212	5.0	70	70
Sep-12	FX-70HS	NP-NW	09-07-39	Mean	216	80	210	84	117	136	564	1.18	0.15	6.6	Not Tested	Not Tested
				COV (%)	9.3%	NA	13.4%	NA	9.2%	17.4%	8.1%	8.3%	3.8%	7.6%		
				MARV	180	NA	180	NA	75	75	460	1.50	0.212	5.9	70	70
Sep-12	FX-80HS(E)	NP-NW	09-07-40	Mean	250	77	345	80	137	205	865	1.66	0.17	9.3	Not Tested	Not Tested
				COV (%)	16.0%	NA	28.1%	NA	15.2%	13.3%	14.8%	5.6%	8.2%	6.6%		
				MARV	220	NA	220	NA	95	95	575	1.50	0.18	8.0	70	70
Sep-12	FX-55	SF-W	09-07-41	Mean	233	26	208	16	100	83	813	0.25	0.42	4.1	86	88
				COV (%)	3.9%	NA	4.9%	NA	4.3%	5.7%	5.0%	37.6%	17.2%	0.9%		
				MARV	200	NA	200	NA	75	75	700	0.05	0.425	4.0	70	70
Sep-12	FX-66	SF-W	09-07-42	Mean	326	27	336	15	128	122	1304	0.27	0.47	6.5	Not Tested	Not Tested
				COV (%)	4.2%	NA	2.1%	NA	5.8%	7.2%	7.6%	21.9%	6.3%	0.5%		
				MARV	315	NA	315	NA	113	113	900	0.05	0.425	4.2	70	70

Manufacturer: **Contech Construction Products**

Contact Info: Randy Ramsey

9025 Centre Pointe Dr. Suite 400

West Chester, OH 45069

Phone:(513) 645-7545

Fax:

Email: ramseyr@contech-cpi.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear		50 mm Puncture		Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241		ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)		
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD	
Jun-12	C80NW	NP-NW	09-01-25	Mean	263	64	258	76	119	143	634	1.2	0.14	6.8	Not Tested	Not Tested	
				COV (%)	9.1%		9.3%		12.6%	11.2%	5.4%	8.3%	7.1%	5.9%			
				MARV													

Manufacturer: Crown Resources

Contact Info: Mr. Marshall Gaddy
 2694 Hayes Wilbank Road
 Toccoa, CA 30577
 Phone:(864) 968-0592

Fax: (864) 848-2623

Email: mgaddy@crowresources.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jan-13	R035	NP-NW	09-10-03	Mean	102	110	127	133	50	70	298	2.32	0.20	4.8	101	101
				COV (%)	10.0%	NA	13.6%	NA	23.8%	16.4%	16.1%	7.7%	5.1%	2.5%	NA	NA
				MARV	90	NA	90	NA	40	40	NA	2.20	0.30	NA	70	70
Jan-13	R060	NP-NW	09-10-04	Mean	169	108	194	109	89	132	450	1.83	0.15	6.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	13.0%	NA	15.6%	22.6%	14.5%	8.4%	0.7%	2.5%	NA	NA
				MARV	160	NA	160	NA	65	65	NA	1.60	0.212	NA	70	70
Jan-13	R070	NP-NW	09-10-05	Mean	194	103	221	118	101	152	529	1.56	0.15	8.0	Not Tested	Not Tested
				COV (%)	13.2%	NA	11.4%	NA	10.8%	22.8%	10.8%	7.1%	0.7%	5.8%	NA	NA
				MARV	180	NA	180	NA	75	75	NA	1.50	0.212	NA	70	70
Jan-13	R080	NP-NW	09-10-06	Mean	212	100	265	110	99	169	597	1.55	0.14	7.6	Not Tested	Not Tested
				COV (%)	8.7%	NA	12.2%	NA	19.3%	14.7%	8.4%	13.6%	6.9%	5.5%	NA	NA
				MARV	205	NA	205	NA	85	85	NA	1.40	0.18	NA	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: DALCO Nonwovens

Contact Info: Mr. John Shave

P.O. Box 1479, Evergreen Drive

Conover, NC 28613

Phone:(828) 459-2577

Fax:

Email: johnshave@dalcononwovens.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)		
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD	
Apr-13	DalTex 1031	NP-NW	09-10-28	Mean	87	60	128	62	42	69	305	3.18	0.23	3.5	98	94	
				COV (%)	11.3%	NA	13.9%	NA	9.2%	15.6%	9.3%	5.4%	8.6%	5.6%	NA	NA	
				MARV	80	NA	80	NA	25	25	210	2.20	0.30	3.1 ave	70	70	
Apr-13	DalTex 1035	NP-NW	09-10-29	Mean	134	86	176	80	67	93	335	2.29	0.16	4.1	Not Tested	Not Tested	
				COV (%)	10.2%	NA	11.1%	NA	21.5%	11.8%	11.7%	20.2%	6.1%	7.3%	NA	NA	
				MARV	90	NA	90	NA	40	40	260	2.20	0.30	3.5 ave	70	70	
Apr-13	DalTex 1040	NP-NW	09-10-30	Mean	116	66	127	84	60	80	330	2.04	0.15	4.0	Not Tested	Not Tested	
				COV (%)	12.2%	NA	13.6%	NA	9.7%	18.1%	4.2%	11.5%	0.7%	4.5%	NA	NA	
				MARV	100	NA	100	NA	45	45	310	2.00	0.21	4.0 ave	70	70	
Apr-13	DalTex 1045	NP-NW	09-10-31	Mean	128	82	147	89	70	86	361	2.66	0.21	4.4	Not Tested	Not Tested	
				COV (%)	10.3%	NA	9.8%	NA	15.7%	14.0%	12.0%	9.4%	4.7%	5.2%	NA	NA	
				MARV	120	NA	120	NA	50	50	335	1.80	0.21	4.5 ave	70	70	
Apr-13	DalTex 1060	NP-NW	09-10-32	Mean	192	87	232	84	112	146	531	1.56	0.15	6.2	Not Tested	Not Tested	
				COV (%)	13.5%	NA	8.6%	NA	9.9%	12.4%	9.9%	32.1%	2.0%	5.5%	NA	NA	
				MARV	160	NA	160	NA	60	60	410	1.60	0.21	6.0 ave	70	70	
Apr-13	DalTex 1070	NP-NW	09-10-33	Mean	189	72	228	75	95	129	554	1.95	0.14	6.0	Not Tested	Not Tested	
				COV (%)	10.2%	NA	7.7%	NA	10.6%	12.5%	5.7%	15.2%	0.7%	2.3%	NA	NA	
				MARV	180	NA	180	NA	75	75	460	1.50	0.21	7.0 ave	70	70	
Apr-13	DalTex 1080	NP-NW	09-10-34	Mean	231	78	261	78	130	143	664	1.38	0.13	7.6	Not Tested	Not Tested	
				COV (%)	7.3%	NA	8.3%	NA	14.3%	9.2%	9.1%	8.0%	3.8%	4.1%	NA	NA	
				MARV	205	NA	205	NA	80	80	525	1.40	0.18	8.0	70	70	
	DalTex 1100 Withdrawn	NP-NW	09-10-35	Mean													
				COV (%)													
				MARV													
Apr-13	DalTex 1101	NP-NW	09-10-36	Mean	322	82	358	77	153	201	864	1.41	0.14	10.1	Not Tested	Not Tested	
				COV (%)	8.2%	NA	5.1%	NA	15.6%	8.8%	7.3%	5.2%	3.7%	2.5%	NA	NA	
				MARV	270	NA	270	NA	100	100	725	0.94	0.15	10.0	70	70	

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: DDD Erosion Control, Inc

Contact Info: Mr. Don Davis/ Mrs. Kelli Davis
 P.O. Box 694, 1383 Industrial Dr.
 Ashburn, GA 31714
 Phone:(229) 567-0751

Fax:

Email: ddderosion@windstream.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear		50 mm Puncture		Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Mar-12	1211 SF 3.2	SF-W	09-01-10	Mean	135	25	120	35	71	72	477	0.15	0.221	2.9	Not Tested	Not Tested
				COV (%)	10.4%		5.8%		5.6%	8.3%	5.0%	13.3%	9.0%	1.0%		
				MARV	143	NA	231	NA	55	88	75	0.165	0.326	2.9		
Jun-12	DDDSF 1211A	SF-W	09-04-01	Mean	115	35	131	42	48	56	291	0.17	0.27	2.1	Not Tested	Not Tested
				COV (%)	6.1%		4.6%		6.3%	8.9%	8.2%	17.6%	18.5%	1.4%		
				MARV	140	NA	153	NA	54	60	NA	0.09	0.36	2.1	>90	>90
Sep-12	3D3.1NW	NP-NW	2010-01-016	Mean	86	62	101	87	45	56	296	3.25	0.25	3.2	Pending	Pending
				COV (%)	13.0%	NA	15.1%	NA	9.8%	27.7%	12.1%	9.1%	11.8%	7.7%	NA	NA
				MARV	80	NA	80	NA	30	30	175	2.20	0.30	3.1 ave	70	70
Sep-12	3D3.5NW	NP-NW	2010-01-017	Mean	95	60	111	86	55	70	321	2.14	0.18	3.6	Not Tested	Not Tested
				COV (%)	14.7%	NA	10.8%	NA	9.6%	13.7%	14.4%	20.3%	11.6%	19.4%		
				MARV	90	NA	90	NA	40	40	300	2.2	0.30	3.5	70	70
Sep-12	3D4NW	NP-NW	2010-01-018	Mean	129	122	124	55	84	60	334	2.08	0.22	4.2	Not Tested	Not Tested
				COV (%)	15.4%	NA	13.8%	NA	16.4%	15.3%	17.7%	14.9%	13.4%	5.9%		
				MARV	100	NA	100	NA	50	50	325	2.0	0.212	4.0	70	70
Sep-12	3D4.5NW	NP-NW	2010-01-019	Mean	135	58	123	78	58	65	406	1.72	0.15	4.4	Not Tested	Not Tested
				COV (%)	9.6%	NA	7.0%	NA	25.3%	12.1%	10.6%	10.9%	1.8%	8.2%		
				MARV	120	NA	120	NA	50	50	350	1.8	0.212	4.2	70	70
Sep-12	3D6NW	NP-NW	2010-01-020	Mean	196	69	195	80	98	96	511	1.83	0.15	6.0	Not Tested	Not Tested
				COV (%)	16.0%	NA	9.6%	NA	13.3%	9.2%	6.6%	19.5%	0.3%	9.0%		
				MARV	160	NA	160	NA	65	65	450	1.6	0.212	6.0		
Sep-12	3D7NW	NP-NW	2010-01-021	Mean	224	76	232	92	121	141	638	1.31	0.13	7.3	Not Tested	Not Tested
				COV (%)	6.2%	NA	8.1%	NA	21.4%	10.6%	6.6%	4.7%	2.8%	8.7%		
				MARV	180	NA	180	NA	75	75	525	1.5	0.212	7.0	70	70
Sep-12	3D8NW	NP-NW	2010-01-022	Mean	259	76	237	89	122	146	747	1.02	0.11	7.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	7.8%	NA	7.3%	20.3%	5.2%	7.7%	8.4%	7.3%		
				MARV	205	NA	205	NA	85	85	650	1.4	0.180	8.0	70	70
Sep-11	3D10NW	NP-NW	2010-01-023	Mean	315	66	266	90	115	139	728	0.84	0.13	9.9		
				COV (%)	7.6%		8.6%		11.3%	11.5%	6.6%	16.7%	7.7%	4.8%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: DDD Erosion Control, Inc

Contact Info: Mr. Don Davis/ Mrs. Kelli Davis
 P.O. Box 694, 1383 Industrial Dr.
 Ashburn, GA 31714
 Phone:(229) 567-0751

Fax:

Email: ddderosion@windstream.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear		50 mm Puncture		Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	3D12NW	NP-NW	2010-01-024	Mean	340	73	327	92	151	134	875	1.03	0.13	11.3		
				COV (%)	9.1%		4.0%		10.6%	6.0%	4.9%	4.9%	15.4%	4.0%		
				MARV												
Sep-11	3D16NW	NP-NW	2010-01-025	Mean	547	76	546	99	216	265	1356	0.61	0.12	16.9		
				COV (%)	6.8%		11.4%		11.6%	4.9%	3.7%	13.1%	0.0%	3.9%		
				MARV												
Sep-12	3D200W	SF-W	2010-01-026	Mean	207	23	216	20	97	104	805	0.11	0.13	4.3	83	64
				COV (%)	3.4%	NA	3.9%	NA	6.1%	3.8%	4.0%	45.6%	6.4%	0.7%		
				MARV	200	NA	200	NA	75	75	450	0.05	0.3	4.0	70	70
Apr-13	3D315W	SF-W	2010-01-027	Mean	372	33	379	22	165	128	1472	0.16	0.19	6.8	Not tested	Not Tested
				COV (%)	5.1%	NA	3.5%	NA	9.3%	4.5%	1.6%	27.9%	15.5%	1.5%	NA	NA
				MARV	315	NA	315	NA	120	120	1000	0.05	0.43	6.3	70	70
Jan-13	DDDGA36-A	C-W	2010-01-028	Mean	173	19	118	20	79	72	564	1.75	0.46	3.5	Pending	Pending
				COV (%)	5.2%	NA	9.1%	NA	8.6%	6.4%	4.1%	7.4%	8.8%	0.9%	NA	NA
				MARV	150	NA	110	NA	60	60	NA	1.00	0.60	NA	80	80
Jan-13	DDDGA36-C	MF-W	2010-01-029	Mean	351	38	208	24	199	83	759	3.17	0.42	5.6	Not Tested	Not Tested
				COV (%)	5.2%	NA	4.3%	NA	9.8%	8.3%	2.6%	3.1%	0.5%	0.5%	NA	NA
				MARV	350	NA	200	NA	65	65	NA	0.50	0.43	NA	80	80
Nov-11	3D-2198	MF-W	2010-01-030	Mean	374	43	329	27	177	128	718	2.35	0.43	6.7		
				COV (%)	3.2%		5.5%		7.3%	6.3%	18.8%	2.6%	4.7%	2.1%		
				MARV												
Nov-11	3D-2199	MF-W	2010-01-031	Mean	435	42	289	24	157	83	799	1.11	0.21	6.8		
				COV (%)	7.1%		3.8%		15.3%	6.0%	4.0%	4.5%	0.0%	1.0%		
				MARV												
Jul-13	GreenSilt	Recycled Reinforced NP-NW	2010-01-032	Mean	135	39	87	60	31	28	229	2.54	0.15	3.8	Not Tested	Not Tested
				COV (%)	8.3%	NA	11.7%	NA	11.8%	16.4%	12.0%	5.5%	8.7%	3.1%	NA	NA
				MARV	95	NA	66	NA	38	18	NA	2.22	0.13	4.0	NA	NA
Apr-14	3D-SFHF	MuF-W	2010-04-016	Mean	125	30	134	27	92	94	411	0.32	0.40	2.9	Not Tested	Not Tested
				COV (%)	9.0%	NA	5.8%	NA	18.2%	5.7%	3.4%	21.3%	2.0%	1.7%	NA	NA
				MARV	124	NA	124	NA	65	65	470	0.20	0.60	3.0	NA	NA

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **DGI Industries, Inc**

Contact Info: Mr. John Demetry

P.O. Box 16522

Hookset, NH 03106

Phone:(603) 227-0495

Fax: (603) 588-8027

Email: dgi@mcttelecom.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-12	CT21303611	SF-W	2010-02-024	Mean	125	21	152	40	66	108	465	0.25	0.45	3.3	88	92
				COV (%)	3.9%	NA	5.0%	NA	5.4%	7.2%	13.9%	38.3%	8.7%	0.6%		
				MARV	124	NA	124	NA	65	65	NA	0.10	0.60	3.1	80	80
Sep-12	NY21303616X	SF-W	2010-02-025	Mean	125	21	152	40	66	108	465	0.25	0.45	3.3	88	92
				COV (%)	3.9%	NA	5.0%	NA	5.4%	7.2%	13.9%	38.3%	8.7%	0.6%		
				MARV	124	NA	124	NA	65	65	NA	0.10	0.60	3.1	80	80
Sep-12	PP213036	SF-W	2010-02-026	Mean	125	21	152	40	66	108	465	0.25	0.45	3.3	88	92
				COV (%)	3.9%	NA	5.0%	NA	5.4%	7.2%	13.9%	38.3%	8.7%	0.6%		
				MARV	124	NA	124	NA	65	65	NA	0.10	0.60	3.1	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Don & Low, LTD**

Contact Info: Mrs. Kelly Johnson

Glamis Road

Forfar, Angus DD8 1FR Scotland

Phone:01307 452200

Fax: 01307 452201

Email: kelly.filmer@donlow.co.uk

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	LOTRAK 315GT	SF-W	07-09-06	Mean	360	23	350	20	140	146	1275	0.34	0.43	6.5		
				COV (%)	4.4%		2.0%		4.3%	4.1%	5.8%	26.5%	9.3%	0.6%		
				MARV												
Jul-11	LOTRAK 300GT	SF-W	07-09-39	Mean	342	17	311	14	121	129	1165	0.24	0.32	6.5		
				COV (%)	6.7%		6.4%		5.0%	3.9%	9.0%	16.7%	9.4%	0.3%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Edge Tech, LLC

Contact Info: Mr. Stephen Stock
 7108 Crossroads Blvd Suite 307
 Brentwood TN 37027
 Phone:(615)-724-0967

Fax:

Email: stephen@edgetechproducts.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jun-12	ET340X	NP-NW	09-04-10	Mean	94	77	100	62	40	42	280	1.53	0.16	3.8	65	64
				COV (%)	22.7%		10.0%		17.4%	10.2%	6.4%	16.6%	5.4%	2.4%		
				MARV	101	60	90	60	45	39	292	1.70	0.10	4.0		
Jun-12	ET360X	NP-NW	09-04-11	Mean	163	70	192	61	53	63	460	0.78	0.09	5.9	63	58
				COV (%)	9.7%		6.6%		9.3%	10.5%	6.1%	15.2%	4.7%	1.0%		
				MARV	135	60	118	60	67	60	436	1.34	0.09	6.0		
Jun-12	ET380X	NP-NW	09-04-12	Mean	193	77	258	55	74	85	609	0.54	0.08	8.0	73	76
				COV (%)	5.0%		7.4%		12.0%	12.3%	3.6%	14.2%	3.2%	1.2%		
				MARV	191	60	168	60	90	79	607	1.00	0.07	8.3		
Jan-13	ET200GT	SF-W	09-10-10	Mean	222	24	230	20	99	99	853	0.11	0.13	4.4	Not Tested	Not Tested
				COV (%)	3.2%	NA	4.7%	NA	6.4%	6.6%	1.5%	30.4%	7.5%	0.9%	NA	NA
				MARV	215	NA	225	NA	90	110	700	0.05	0.30	4.0	70	70
Jun-12	ET300GT	SF-W	09-10-11	Mean	378	30	297	25	155	115	1152	0.23	0.14	5.9	Not Tested	Not Tested
				COV (%)	3.9%	NA	4.4%	NA	3.9%	4.5%	1.9%	12.3%	7.1%	0.5%	NA	NA
				MARV	330	NA	320	NA	135	125	1000	0.05	0.42	6.3	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **GEO Fabrics, LLC**

Contact Info: Mr. Sid Johnson

P.O. Box 46

Enigma, GA 31749

Phone:(229) 533-5785

Fax: (229) 533-6941

Email: geofabrics@alltel.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jan-14	DOT A	MuF-W	2010-03-001	Mean	163	19	102	15	72	54	506	1.54	0.56	3.1	81	100
				COV (%)	7.2%	NA	14.2%	NA	8.1%	6.4%	4.6%	9.9%	5.0%	1.0%	NA	NA
				MARV	120	NA	120	NA	NA	NA	NA	NA	NA	NA	80	80
Jan-14	402	MF-W	2010-03-002	Mean	303	36	264	23	126	97	792	2.84	0.49	5.7	85	98
				COV (%)	3.9%	NA	3.7%	NA	6.3%	6.7%	2.5%	8.3%	11.2%	0.9%	NA	NA
				MARV	260	NA	260	NA	NA	NA	NA	NA	NA	NA	70	70
Jan-14	500	SF-W	2010-03-003	Mean	234	18	222	13	83	83	852	0.21	0.26	4.6	Not Tested	Not Tested
				COV (%)	3.4%	NA	7.1%	NA	7.7%	7.7%	4.5%	17.4%	12.3%	1.1%	NA	NA
				MARV	200	NA	200	NA	NA	NA	NA	NA	NA	NA	NA	NA

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: GSE Lining Technologies

Contact Info: Mr. Adam Glassman
19103 Gundle Road
Houston, TX 77073

Phone:(281)230-8601 , (800) 435-2008

Fax: (281) 230-8650

Email: aglassman@gseworld.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	CE 3	NP-NW	07-09-07	Mean	93	80	152	77	50	85	354	3.03	0.19	4.2		
				COV (%)	10.8%		6.6%		16.0%	7.1%	7.9%	11.6%	5.3%	4.8%		
				MARV												
Jul-11	CE 4	NP-NW	07-09-08	Mean	119	86	178	71	55	106	400	2.21	0.17	4.8		
				COV (%)	9.2%		7.9%		12.7%	16.0%	5.8%	5.0%	11.8%	4.2%		
				MARV												
Jul-11	NW 10	NP-NW	07-09-11	Mean	387	73	275	80	223	140	968	1.81	0.15	10.1		
				COV (%)	6.5%		5.8%		7.2%	15.7%	6.3%	5.0%	6.7%	4.0%		
				MARV												
Nov-11	CE 6	NP-NW	08-06-01	Mean	158	66	186	63	95	144	652	1.93	0.15	6.9		
				COV (%)	4.4%		5.9%		11.6%	12.5%	11.2%	4.7%	0.0%	8.7%		
				MARV												
Nov-11	CE 8	NP-NW	08-06-02	Mean	228	63	237	71	133	179	635	1.5	0.16	7.8		
				COV (%)	7.0%		17.7%		14.3%	9.5%	10.2%	6.7%	12.5%	7.7%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Hanes Geo Components (formerly Webtec and Ikex)**

Contact Info: Mr. Keith Harris
815 Buxton St.

Winston-Salem, NC 27101

Phone:(800) 438-0027

Fax: (800) 239-4539

Email: keith.harris@hanescompanies.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Nov-11	TerraTex N10	NP-NW	08-01-36	Mean	315	66	266	90	115	139	728	0.84	0.13	9.9		
				COV (%)	7.6%		8.6%		11.3%	11.5%	6.6%	16.7%	7.7%	4.8%		
				MARV												
Nov-11	TerraTex N12	NP-NW	08-01-37	Mean	340	73	327	92	151	134	875	1.03	0.13	11.3		
				COV (%)	9.1%		4.0%		10.6%	6.0%	4.9%	4.9%	15.4%	4.0%		
				MARV												
Nov-11	TerraTex N16	NP-NW	08-01-38	Mean	547	76	546	99	216	265	1356	0.61	0.12	16.9		
				COV (%)	6.8%		11.4%		11.6%	4.9%	3.7%	13.1%	0.0%	3.9%		
				MARV												
Nov-11	TerraTex GS-250	SF-W	08-01-39	Mean	318	26	288	22	132	113	1025	0.17	0.26	5.8		
				COV (%)	2.8%		3.1%		6.8%	5.3%	4.8%	5.9%	15.4%	0.5%		
				MARV												
Nov-11	TerraTex OL	NP-NW	08-01-41	Mean	114	48	103	71	49	54	318	1.37	0.15	4		
				COV (%)	11.4%		14.6%		16.3%	11.1%	13.8%	23.4%	6.7%	4.0%		
				MARV												
Nov-11	TerraTex OLI	NP-NW	08-01-42	Mean	146	49	122	71	53	59	346	1.16	0.14	4.6		
				COV (%)	12.3%		14.8%		13.2%	10.2%	15.6%	25.9%	0.0%	3.3%		
				MARV												
Nov-11	TerraTex SC	SF-W	08-01-43	Mean	243	24	313	33	144	91	718	2.79	0.76	5.8		
				COV (%)	6.6%		5.1%		9.7%	6.6%	15.5%	6.1%	10.5%	1.4%		
				MARV												
Nov-11	TerraTex EP-11	MF-W	08-01-55	Mean	374	36	201	22	117	48	639	1.89	0.39	5.7		
				COV (%)	4.5%		5.0%		4.3%	10.4%	3.3%	3.2%	30.8%	1.2%		
				MARV												
Nov-11	TerraTex SCs	SF-W	08-01-58	Mean	243	24	313	33	144	91	718	2.79	0.76	5.8		
				COV (%)	6.6%		5.1%		9.7%	6.6%	15.5%	6.1%	10.5%	1.4%		
				MARV												
Mar-12	TerraTex SF-D	SF-W	08-04-23	Mean	140	20	108	31	75	65	359	0.24	0.4	2.5		
				COV (%)	9.3%		18.5%		5.3%	7.7%	10.9%	29.2%	50.0%	1.6%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Hanes Geo Components (formerly Webtec and Ikex)**

Contact Info: Mr. Keith Harris
815 Buxton St.

Winston-Salem, NC 27101

Phone:(800) 438-0027

Fax: (800) 239-4539

Email: keith.harris@hanescompanies.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Mar-12	TerraTex SF-90	SF-W	08-04-24	Mean	109	23	92	27	64	52	261	0.25	0.4	1.9		
				COV (%)	10.1%		11.9%		6.3%	7.7%	8.8%	40.0%	25.0%	1.6%		
				MARV												
Sep-11	TerraTex EP	MF-W	08-04-29	Mean	419	25	257	25	155	106	996	0.53	0.25	6.2		
				COV (%)	2.1%		6.6%		6.5%	7.5%	8.2%	5.7%	12.0%	0.5%		
				MARV												
Sep-12	Terra Tex HPG-16	C-W	09-04-02	Mean	394	28	314	16	174	113	1270	0.80	0.56	7.1	Not Tested	Not Tested
				COV (%)	4.0%	NA	3.7%	NA	6.7%	4.9%	2.2%	3.4%	2.5%	0.3%		
				MARV	315	15	315	15	125	125	700	0.7	0.425	NA	80	80
Sep-12	TerraTex N04	NP-NW	09-07-53	Mean	95	60	111	86	55	70	321	2.14	0.18	3.6	Not Tested	Not Tested
				COV (%)	14.7%	NA	10.8%	NA	9.6%	13.7%	14.4%	20.3%	11.6%	19.4%		
				MARV	90	NA	90	NA	40	40	300	2.2	0.30	3.5	70	70
Sep-12	TerraTex SD	NP-NW	09-07-54	Mean	129	122	124	55	84	60	334	2.08	0.22	4.2	Not Tested	Not Tested
				COV (%)	15.4%	NA	13.8%	NA	16.4%	15.3%	17.7%	14.9%	13.4%	5.9%		
				MARV	100	NA	100	NA	50	50	325	2.0	0.212	4.0	70	70
Sep-12	TerraTex N4.5	NP-NW	09-07-55	Mean	135	58	123	78	58	65	406	1.72	0.15	4.4	Not Tested	Not Tested
				COV (%)	9.6%	NA	7.0%	NA	25.3%	12.1%	10.6%	10.9%	1.8%	8.2%		
				MARV	120	NA	120	NA	50	50	350	1.8	0.212	4.2	70	70
Sep-12	TerraTex N06	NP-NW	09-07-56	Mean	196	69	195	80	98	96	511	1.83	0.15	6.0	Not Tested	Not Tested
				COV (%)	16.0%	NA	9.6%	NA	13.3%	9.2%	6.6%	19.5%	0.3%	9.0%		
				MARV	160	NA	160	NA	65	65	450	1.6	0.212	6.0		
Sep-12	TerraTex N07	NP-NW	09-07-57	Mean	224	76	232	92	121	141	638	1.31	0.13	7.3	Not Tested	Not Tested
				COV (%)	6.2%	NA	8.1%	NA	21.4%	10.6%	6.6%	4.7%	2.8%	8.7%		
				MARV	180	NA	180	NA	75	75	525	1.5	0.212	7.0	70	70
Sep-12	TerraTex N08	NP-NW	09-07-58	Mean	259	76	237	89	122	146	747	1.02	0.11	7.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	7.8%	NA	7.3%	20.3%	5.2%	7.7%	7.3%			
				MARV	205	NA	205	NA	85	85	650	1.4	0.180	8.0	70	70
Sep-12	TerraTex HPG-37	C-W	09-07-59	Mean	463	25	314	21	217	164	1457	0.61	0.38	8.5	Not Tested	Not Tested
				COV (%)	6.1%	NA	6.9%	NA	12.4%	10.8%	13.2%	11.7%	3.5%	0.9%		
				MARV	400	NA	250	NA	170	125	1300	0.52	0.60	8.8	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Hanes Geo Components (formerly Webtec and Ikex)

Contact Info: Mr. Keith Harris

815 Buxton St.

Winston-Salem, NC 27101

Phone:(800) 438-0027

Fax: (800) 239-4539

Email: keith.harris@hanescompanies.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-12	TerraTex HPG-56	C-W	09-07-60	Mean	587	24	576	21	211	398	2090	0.15	0.14	12.9	Not Tested	Not Tested
				COV (%)	5.0%	NA	11.4%	NA	6.2%	11.2%	8.5%	8.6%	24.0%	0.3%		
				MARV	550	NA	550	NA	150	200	1750	0.025	0.43	13.0	80	80
Sep-12	TerraTex HPG-57	C-W	09-07-61	Mean	487	21	503	16	226	412	2081	0.78	0.60	13.8	Not Tested	Not Tested
				COV (%)	15.2%	NA	8.0%	NA	4.0%	15.5%	7.8%	6.6%	0.5%	0.4%		
				MARV	475	NA	440	NA	180	180	2000	0.40	0.60	14	80	80
Sep-12	TerraTex GS	SF-W	09-07-62	Mean	207	23	216	20	97	104	805	0.11	0.13	4.3	83	64
				COV (%)	3.4%	NA	3.9%	NA	6.1%	3.8%	4.0%	45.6%	6.4%	0.7%		
				MARV	200	NA	200	NA	75	75	450	0.05	0.3	4.0	70	70
Apr-13	TerraTex N03	NP-NW	2010-02-001	Mean	86	62	101	87	45	56	296	3.25	0.25	3.2	Pending	Pending
				COV (%)	13.0%	NA	15.1%	NA	9.8%	27.7%	12.1%	9.1%	11.8%	7.7%	NA	NA
				MARV	80	NA	80	NA	30	30	175	2.20	0.30	3.1 ave	70	70
Apr-13	TerraTex HD	SF-W	2010-02-002	Mean	372	33	379	22	165	128	1472	0.16	0.19	6.8	Not tested	Not Tested
				COV (%)	5.1%	NA	3.5%	NA	9.3%	4.5%	1.6%	27.9%	15.5%	1.5%	NA	NA
				MARV	315	NA	315	NA	120	120	1000	0.05	0.43	6.3	70	70
Nov-11	TerraTex EP9	MF-W	2010-02-04	Mean	435	42	289	24	157	83	799	1.11	0.21	6.8		
				COV (%)	7.1%		3.8%		15.3%	6.0%	4.0%	4.5%	0.0%	1.0%		
				MARV												
Jan-13	TerraTex GASF-C	MF-W	2010-02-05	Mean	351	38	208	24	199	83	759	3.17	0.42	5.6	Not Tested	Not Tested
				COV (%)	5.2%	NA	4.3%	NA	9.8%	8.3%	2.6%	3.1%	0.5%	0.5%	NA	NA
				MARV	350	NA	200	NA	65	65	NA	0.50	0.43	NA	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Indian Valley Industries

Contact Info: Mr. Phil March

P.O. Box 810

Johnson City, NY 13790

Phone:(607)729-5111

Fax: (607)729-5158

Email: pmarch@iviindustries.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355			
					MD		XD		Strength (lbs)		MD	XD	Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD							MD	XD
Sep-11	3611 MC	SF-W	2010-03-005	Mean	134	18	108	24	83	70	363	0.16	0.27	2.8				
				COV (%)														
				MARV														
Sep-11	3617 C	SF-W	2010-03-004	Mean	134	18	108	24	83	70	363	0.16	0.27	2.8				
				COV (%)														
				MARV														
Apr-13	IVI - 66	NP-NW	2010-02-003	Mean	231	78	261	78	130	143	664	1.38	0.13	7.6	Not Tested	Not Tested		
				COV (%)	7.3%	NA	8.3%	NA	14.3%	9.2%	9.1%	8.0%	3.8%	4.1%	NA	NA		
				MARV	205	NA	205	NA	80	80	525	1.40	0.18	8.0	70	70		

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needleponched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Kintex**

Contact Info: Mr. Sean Kiniry
 102 Brownfield Dr.
 Summerville, SC 29483
 Phone:(843) 832-6860

Fax:

Email: kintex@knology.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jan-13	DuPont SF40	HB-NW	09-10-25	Mean	163	72	188	72	86	84	334	1.38	0.27	4.1	97	87
				COV (%)	8.7%	NA	10.3%	NA	12.3%	26.5%	6.8%	18.3%	11.0%	3.4%	NA	NA
				MARV	130	NA	130	NA	60	60	NA	0.80	0.21	NA	70	70
Jan-13	DuPont SF49	HB-NW	09-10-26	Mean	234	67	230	63	91	82	421	0.59	0.14	4.9	Not Tested	Not Tested
				COV (%)	9.0%	NA	12.1%	NA	15.6%	16.8%	9.4%	27.0%	6.9%	2.0%	NA	NA
				MARV	180	NA	180	NA	56	56	NA	0.30	0.15	NA	70	70
Jan-13	Dupont SF65	HB-NW	09-10-27	Mean	305	71	343	65	98	115	556	0.52	0.10	6.5	Not Tested	Not Tested
				COV (%)	10.6%	NA	10.3%	NA	18.0%	16.3%	7.7%	28.4%	3.8%	2.5%	NA	NA
				MARV	250	NA	250	NA	79	79	NA	0.1	0.09	NA	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Mattex Geotextiles**

Contact Info: Mr. Robert Rossing

PO Box 112470

Dubai, United Arab Emirates

Phone: +971 4 803 8111

Fax: +971 4 803 8222

Email: robert.r@mattex.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jun-12	Mattex 200	SF-W	09-01-23	Mean	245	23	231	18	85	130	838	0.24	0.33	4.7	102	102
				COV (%)	3.7%		9.1%		3.5%	6.2%	3.7%	12.5%	15.2%	0.4%		
				MARV	200	NA	200	NA	75	75	700	0.05	0.425	4.7	80	80
Jun-12	Mattex 315	SF-W	09-01-24	Mean	333	27	345	20	127	160	1242	0.2	0.34	6.5	Not Tested	Not Tested
				COV (%)	2.7%		3.5%		3.9%	16.9%	10.3%	15.0%	11.8%	0.3%		
				MARV	315	NA	315	NA	115	115	900	0.05	0.425	6.6	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Performance Fabrics and Fibers**

Contact Info: Mr. Peter McGill
 P.O. Box 1490
 Andrews, SC 29510
 Phone:

Fax:

Email: pcmgill@performanceff.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	NG0310	NP-NW	07-09-36	Mean	86	69	119	68	39	45	289	2.47	0.17	3.8		
				COV (%)	17.4%		10.1%		17.9%	26.7%	11.8%	5.3%	11.8%	8.4%		
				MARV												
Jul-11	NG0420	NP-NW	07-09-37	Mean	129	86	141	84	64	70	382	2.73	0.15	4.5		
				COV (%)	11.6%		14.9%		7.8%	21.4%	12.3%	23.4%	6.7%	7.1%		
				MARV												
Jul-11	NG01200	NP-NW	07-09-38	Mean	352	74	434	66	161	179	1162	1.16	0.12	12.5		
				COV (%)	14.2%		13.1%		12.4%	12.8%	11.2%	12.1%	8.3%	12.0%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needleponched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Poly Industrial Products, Inc

Contact Info: Mr. Sunil Kumar Kulshrestha
 #16/3251 Parker Hill Road
 Mississauga, ON. L5B 1V7, Canada
 Phone:(905) 270-8518

Fax: (905) 270-8859

Email: info@canpackinternational.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2				
					ASTM D4632		ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355				
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	PIP075B36	SF-W	08-01-30	Mean	78	24	76	32	57	52	253	0.07	0.23	1.9		
				COV (%)	11.5%		11.8%		15.8%	7.7%	5.5%	14.3%	17.4%	2.6%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Propex, Inc (formerly SI Geosolutions)

Contact Info: Brittany Garner

6025 Lee Highway Suite 425

Chattanooga, TN 37422

Phone :423-553-2532

Fax: (423) 899-7619

Email: brittany.garner@propexus.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Mar-12	Geotex 501	NP-NW	09-01-04	Mean	167	59	156	73	71	83	498	2.2	0.16	5.9	Not Tested	Not Tested
				COV (%)	10.2%		14.7%		8.5%	14.5%	9.4%	18.2%	6.3%	3.4%		
				MARV												
Mar-12	Geotex 1001	NP-NW	09-01-05	Mean	305	89	467	70	150	245	1063	1.3	0.14	11.9	Not Tested	Not Tested
				COV (%)	15.1%		13.7%		12.0%	13.5%	14.8%	15.4%	7.1%	10.9%		
				MARV												
Mar-12	Geotex 1201	NP-NW	09-01-06	Mean	326	86	571	64	163	281	1296	1.1	0.16	13.4	Not Tested	Not Tested
				COV (%)	8.0%		4.2%		25.8%	13.2%	8.3%	9.1%	6.3%	6.0%		
				MARV												
Mar-12	Geotex 4598	NP-NW	09-01-07	Mean	98	64	98	85	45	61	338	1.9	0.18	5.8	Not Tested	Not Tested
				COV (%)	8.2%		9.2%		22.2%	41.0%	13.3%	21.1%	11.1%	8.6%		
				MARV												
Mar-12	Geotex 2x2HF	C-W	09-01-08	Mean	399	24	335	17	147	111	1315	0.6	0.41	7.4	Not Tested	Not Tested
				COV (%)	3.8%		3.6%		9.5%	8.1%	9.5%	6.7%	2.4%	1.4%		
				MARV												
Mar-12	Geotex 801	NP-NW	09-01-09	Mean	263	64	258	76	119	143	634	1.2	0.14	6.8	Not Tested	Not Tested
				COV (%)	9.1%		9.3%		12.6%	11.2%	5.4%	8.3%	7.1%	5.9%		
				MARV												
Sep-12	Geotex 200ST	SF-W	09-07-16	Mean	233	26	208	16	100	83	813	0.25	0.42	4.1	86	88
				COV (%)	3.9%	NA	4.9%	NA	4.3%	5.7%	5.0%	37.6%	17.2%	0.9%		
				MARV	200	NA	200	NA	75	75	700	0.05	0.425	4.0	70	70
Sep-12	Geotex 311	NP-NW	09-07-18	Mean	98	63	96	99	53	60	268	2.38	0.24	3.6	94	86
				COV (%)	14.1%	NA	16.1%	NA	12.5%	17.2%	14.9%	26.4%	15.0%	10.5%		
				MARV	80	NA	80	NA	30	30	210	2.00	0.30	2.5	70	70
Sep-12	Geotex 401	NP-NW	09-07-19	Mean	116	62	150	80	59	80	392	2.41	0.21	4.4	Not Tested	Not Tested
				COV (%)	8.6%	NA	14.4%	NA	13.6%	20.0%	6.9%	17.3%	0.7%	2.5%		
				MARV	115	NA	115	NA	50	50	310	2.00	0.212	3.5	70	70
Sep-12	Geotex 2130	SF-W	09-07-20	Mean	125	21	152	40	66	108	465	0.25	0.45	3.3	88	92
				COV (%)	3.9%	NA	5.0%	NA	5.4%	7.2%	13.9%	38.3%	8.7%	0.6%		
				MARV	124	NA	124	NA	65	65	NA	0.10	0.60	3.1	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Propex, Inc (formerly SI Geosolutions)

Contact Info: Brittany Garner

6025 Lee Highway Suite 425

Chattanooga, TN 37422

Phone :423-553-2532

Fax: (423) 899-7619

Email: brittany.garner@propexus.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2				
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
	Geotex 2130D / Withdrawal	SF-W	09-07-21	Mean												
				COV (%)												
				MARV												
Sep-12	Geotex451	NP-NW	09-07-22	Mean	126	64	126	105	65	83	360	2.49	0.24	4.2	Not Tested	Not Tested
				COV (%)	10.7%	NA	13.6%	NA	13.4%	15.0%	16.0%	16.7%	8.1%	5.7%		
				MARV	120	NA	120	NA	50	50	335	1.50	0.212	4.0	70	70
Sep-12	Geotex 601	NP-NW	09-07-23	Mean	216	82	171	93	116	131	455	1.50	0.16	5.6	Not Tested	Not Tested
				COV (%)	8.3%	NA	22.5%	NA	17.1%	15.0%	10.2%	12.0%	9.5%	7.2%		
				MARV	160	NA	160	NA	60	60	410	1.50	0.212	5.0	70	70
Sep-12	Geotex 701	NP-NW	09-07-24	Mean	216	80	210	84	117	136	564	1.18	0.15	6.6	Not Tested	Not Tested
				COV (%)	9.3%	NA	13.4%	NA	9.2%	17.4%	8.1%	8.3%	3.8%	7.6%		
				MARV	180	NA	180	NA	75	75	460	1.50	0.212	5.9	70	70
Sep-12	Geotex 861	NP-NW	09-07-25	Mean	250	77	345	80	137	205	865	1.66	0.17	9.3	Not Tested	Not Tested
				COV (%)	16.0%	NA	28.1%	NA	15.2%	13.3%	14.8%	5.6%	8.2%	6.6%		
				MARV	220	NA	220	NA	95	95	575	1.50	0.18	8.0	70	70
Jul-13	Geotex 4x4HF	MF-W	2010-01-012	Mean	609	21	486	20	321	433	1652	0.86	0.59	12.4	Not tested	Not Tested
				COV (%)	3.9%	NA	15.6%	NA	11.8%	13.8%	13.0%	7.8%	0.2%	0.6%	NA	NA
				MARV	475	NA	440	NA	180	180	NA	0.40	0.60	13.8	80	80
Jul-13	Geotex 104F	MF-W	2010-01-013	Mean	412	26	262	22	142	89	1146	0.41	0.19	5.9	101.2	95.1
				COV (%)	2.9%	NA	1.7%	NA	11.1%	8.1%	1.8%	14.3%	8.3%	0.8%	NA	NA
				MARV	370	NA	250	NA	100	60	950	0.28	0.21	6	90	90
Jul-13	Geotex 1601	NP-NW	2010-01-014	Mean	459	85	636	92	242	394	1464	0.61	0.11	16.0	Not tested	Not Tested
				COV (%)	5.5%	NA	8.0%	NA	13.4%	11.8%	8.6%	10.2%	7.3%	6.4%	NA	NA
				MARV	380	NA	380	NA	150	150	1025	0.7	0.15	15	70	70
Jul-13	Petromat 4598	NP-NW	2010-01-015	Mean	130	70	167	92	62	92	389	2.70	0.23	4.8	Not tested	Not Tested
				COV (%)	8.6%	NA	13.6%	NA	18.2%	20.3%	14.7%	13.8%	9.5%	6.9%	NA	NA
				MARV	101	NA	101	NA	40	40	260	1.5	0.3	4.1	70	70
Jul-13	Geotex 315ST	SF-W	2010-02-027	Mean	365	29	366	19	165	120	1401	0.08	0.14	6.8	Not Tested	Not Tested
				COV (%)	5.1%	NA	5.7%	NA	7.0%	7.0%	1.6%	77.7%	3.5%	0.4%	NA	NA
				MARV	315	NA	315	NA	113	113	900	0.05	0.42	4.2	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Propex, Inc (formerly SI Geosolutions)**

Contact Info: Brittany Garner

6025 Lee Highway Suite 425

Chattanooga, TN 37422

Phone :423-553-2532

Fax: (423) 899-7619

Email: brittany.garner@propexus.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2				
					ASTM D4632		ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355				
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-13	Geotex 1341NH	NP-NW	2010-02-028	Mean	469	85	516	102	273	365	1258	0.88	0.12	13.9	Not Tested	Not Tested
				COV (%)	5.8%	NA	7.4%	NA	16.2%	20.4%	11.5%	7.5%	14.4%	4.7%	NA	NA
				MARV	330	NA	330	NA	125	125	925	0.80	0.15	13.3	70	70
Apr-14	Geotex 250ST	SF-W	2010-04-001	Mean	231	15	289	22	86	123	1246	0.17	0.27	6.0	Not Tested	Not Tested
				COV (%)	4.8%	NA	6.6%	NA	5.8%	7.4%	3.8%	21.5%	9.8%	1.0%	NA	NA
				MARV	250	NA	250	NA	90	90	750	0.05	0.43	5.0	NA	NA
Apr-14	Geotex 351	NP-NW	2010-04-002	Mean	90	77	131	87	44	78	245	2.28	0.20	3.6	Not Tested	Not Tested
				COV (%)	14.6%	NA	12.2%	NA	13.5%	16.3%	17.0%	20.4%	14.8%	6.4%	NA	NA
				MARV	95	NA	95	NA	40	40	260	2.00	0.30	3.0	NA	NA
Apr-14	Geotex 4599	NP-NW	2010-04-003	Mean	103	74	125	98	53	76	298	3.03	0.25	4.0	Not Tested	Not Tested
				COV (%)	9.3%	NA	12.0%	NA	18.7%	13.8%	14.6%	16.3%	11.3%	6.8%	NA	NA
				MARV	90	NA	90	NA	40	40	260	2.00	0.30	3.6	NA	NA
Apr-14	Geotex 1071	NP-NW	2010-04-004	Mean	315	81	400	78	174	207	908	1.30	0.15	11.9	Not Tested	Not Tested
				COV (%)	18.2%	NA	10.3%	NA	14.5%	15.2%	8.7%	14.2%	0.0%	7.3%	NA	NA
				MARV	270	NA	270	NA	105	105	725	1.20	0.15	10.0	NA	NA
Apr-14	Geotex 102F	MF-W	2010-04-005	Mean	475	31	414	20	284	137	1465	0.27	0.41	7.7	Not Tested	Not Tested
				COV (%)	4.3%	NA	2.3%	NA	20.6%	9.3%	2.0%	3.7%	26.8%	0.4%	NA	NA
				MARV	350	NA	250	NA	100	100	800	0.28	0.21	6.5	NA	NA

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Silt Saver, Inc**

Contact Info: Mr. Earl R. Singleton
 1094 Culpepper Drive
 Conyers, GA 30094
 Phone:(770) 388-7818

Fax: (770) 388-7640

Email: roger@siltsaver.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2				
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
	Belted Silt Retention Fence/ Withdrawn	NP-NW	08-09-01	Mean												
				COV (%)												
				MARV												

Manufacturer: Skaps Industries

Contact Info: Mr. Anurag Shah
335 Athena Drive
Athens, GA 30601
Phone:(706) 693-3440

Fax: (706) 693-3450

Email: anurag@skaps.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	W 250	SF-W	08-01-01	Mean	318	26	288	22	132	113	1025	0.17	0.26	5.8		
				COV (%)	2.8%		3.1%		6.8%	5.3%	4.8%	5.9%	15.4%	0.5%		
				MARV												
Sep-11	W 100	SF-W	08-01-02	Mean	243	24	313	33	144	91	718	2.79	0.76	5.8		
				COV (%)	6.6%		5.1%		9.7%	6.6%	15.5%	6.1%	10.5%	1.4%		
				MARV												
Sep-11	M 404	MF-W	08-01-03	Mean	374	36	201	22	117	48	639	1.89	0.39	5.7		
				COV (%)	4.5%		5.0%		4.3%	10.4%	3.3%	3.2%	30.8%	1.2%		
				MARV												
Sep-11	M 706	MF-W	08-01-04	Mean	446	27	275	26	183	100	860	0.45	0.17	6		
				COV (%)	2.7%		5.1%		5.5%	9.0%	16.9%	40.0%	11.8%	1.0%		
				MARV												
Sep-11	GC 130	NP-NW	08-01-05	Mean	114	48	103	71	49	54	318	1.37	0.15	4		
				COV (%)	11.4%		14.6%		16.3%	11.1%	13.8%	23.4%	6.7%	4.0%		
				MARV												
Sep-11	GC 140	NP-NW	08-01-06	Mean	146	49	122	71	53	59	346	1.16	0.14	4.6		
				COV (%)	12.3%		14.8%		13.2%	10.2%	15.6%	25.9%	0.0%	3.3%		
				MARV												
Sep-11	GT 110	NP-NW	08-01-07	Mean	315	66	266	90	115	139	728	0.84	0.13	9.9		
				COV (%)	7.6%		8.6%		11.3%	11.5%	6.6%	16.7%	7.7%	4.8%		
				MARV												
Sep-11	GT 112	NP-NW	08-01-08	Mean	340	73	327	92	151	134	875	1.03	0.13	11.3		
				COV (%)	9.1%		4.0%		10.6%	6.0%	4.9%	4.9%	15.4%	4.0%		
				MARV												
Sep-11	GT 116	NP-NW	08-01-09	Mean	547	76	546	99	216	265	1356	0.61	0.12	16.9		
				COV (%)	6.8%		11.4%		11.6%	4.9%	3.7%	13.1%	0.0%	3.9%		
				MARV												
Sep-12	GT 135	NP-NW	09-07-08	Mean	95	60	111	86	55	70	321	2.14	0.18	3.6	Not Tested	Not Tested
				COV (%)	14.7%	NA	10.8%	NA	9.6%	13.7%	14.4%	20.3%	11.6%	19.4%		
				MARV	90	NA	90	NA	40	40	300	2.2	0.30	3.5	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Skaps Industries

Contact Info: Mr. Anurag Shah
335 Athena Drive
Athens, GA 30601
Phone:(706) 693-3440

Fax: (706) 693-3450

Email: anurag@skaps.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2				
					ASTM D4632		ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355				
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-12	GT 140	NP-NW	09-07-09	Mean	129	122	124	55	84	60	334	2.08	0.22	4.2	Not Tested	Not Tested
				COV (%)	15.4%	NA	13.8%	NA	16.4%	15.3%	17.7%	14.9%	13.4%	5.9%		
				MARV	100	NA	100	NA	50	50	325	2.0	0.212	4.0	70	70
Sep-12	GT 142	NP-NW	09-07-10	Mean	135	58	123	78	58	65	406	1.72	0.15	4.4	Not Tested	Not Tested
				COV (%)	9.6%	NA	7.0%	NA	25.3%	12.1%	10.6%	10.9%	1.8%	8.2%		
				MARV	120	NA	120	NA	50	50	350	1.8	0.212	4.2	70	70
Sep-12	GT 160	NP-NW	09-07-11	Mean	196	69	195	80	98	96	511	1.83	0.15	6.0	Not Tested	Not Tested
				COV (%)	16.0%	NA	9.6%	NA	13.3%	9.2%	6.6%	19.5%	0.3%	9.0%		
				MARV	160	NA	160	NA	65	65	450	1.6	0.212	6.0		
Sep-12	GT 170	NP-NW	09-07-12	Mean	224	76	232	92	121	141	638	1.31	0.13	7.3	Not Tested	Not Tested
				COV (%)	6.2%	NA	8.1%	NA	21.4%	10.6%	6.6%	4.7%	2.8%	8.7%		
				MARV	180	NA	180	NA	75	75	525	1.5	0.212	7.0	70	70
Sep-12	GT 180	NP-NW	09-07-13	Mean	259	76	237	89	122	146	747	1.02	0.11	7.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	7.8%	NA	7.3%	20.3%	5.2%	7.7%	8.4%	7.3%		
				MARV	205	NA	205	NA	85	85	650	1.4	0.180	8.0	70	70
Sep-12	SW 200	SF-W	09-07-14	Mean	207	23	216	20	97	104	805	0.11	0.13	4.3	83	64
				COV (%)	3.4%	NA	3.9%	NA	6.1%	3.8%	4.0%	45.6%	6.4%	0.7%		
				MARV	200	NA	200	NA	75	75	450	0.05	0.3	4.0	70	70
Apr-13	GT 131	NP-NW	2010-01-001	Mean	86	62	101	87	45	56	296	3.25	0.25	3.2	Pending	Pending
				COV (%)	13.0%	NA	15.1%	NA	9.8%	27.7%	12.1%	9.1%	11.8%	7.7%	NA	NA
				MARV	80	NA	80	NA	30	30	175	2.20	0.30	3.1 ave	70	70
Apr-13	SW 315	SF-W	2010-01-002	Mean	372	33	379	22	165	128	1472	0.16	0.19	6.8	Not tested	Not Tested
				COV (%)	5.1%	NA	3.5%	NA	9.3%	4.5%	1.6%	27.9%	15.5%	1.5%	NA	NA
				MARV	315	NA	315	NA	120	120	1000	0.05	0.43	6.3	70	70
Jan-14	GT 175	NP-NW	2010-03-006	Mean	210	70	255	86	102	146	NA	666	1.35	0.13	7.1	Not Tested
				COV (%)	17.8%	NA	9.4%	NA	11.9%	9.6%	NA	8.4%	17.5%	6.0%	3.5%	NA
				MARV	203	NA	203	NA	80	80	NA	400	0.70	0.15	7.5	NA

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Spilo PTY, Ltd.**

Contact Info: Mr. Bernard Reed

PO Box 282, Paarl

South Africa, 7620

Phone: +27 21 862-6100

Fax: +27 21 862-9361

Email: bernardr@spilo.co.za

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab		Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2				
					ASTM D4632		ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355				
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jun-12	Spilo 200	SF-W	09-01-11	Mean	233	25	227	19	93	86	936	0.17	0.31	4.6	90	93
				COV (%)	5.2%		3.1%		8.6%	3.5%	4.5%	11.8%	16.3%	0.6%		
				MARV	200	15	200	10	75	75	NA	0.07	0.30	NA	90	90

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **SRW Products**

Contact Info: Mr. John Wold

32020 126th Street

Priceton, MN 55371

Phone:(763) 389-2722 Ext 122

Fax:

Email: johnwold@srwproducts.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	Bulldog LS3	NP-NW	07-04-19	Mean	86	69	119	68	39	45	289	2.47	0.17	3.8		
				COV (%)	17.4%		10.1%		17.9%	26.7%	11.8%	5.3%	11.8%	8.4%		
				MARV												
Jul-11	Bulldog NW4.5	NP-NW	07-04-20	Mean	129	86	141	84	64	70	382	2.73	0.15	4.5		
				COV (%)	11.6%		14.9%		7.8%	21.4%	12.3%	23.4%	6.7%	7.1%		
				MARV												
Jul-11	SRW LS3	NP-NW	07-04-21	Mean	86	69	119	68	39	45	289	2.47	0.17	3.8		
				COV (%)	17.4%		10.1%		17.9%	26.7%	11.8%	5.3%	11.8%	8.4%		
				MARV												
Jul-11	SRW NW4.5	NP-NW	07-04-22	Mean	129	86	141	84	64	70	382	2.73	0.15	4.5		
				COV (%)	11.6%		14.9%		7.8%	21.4%	12.3%	23.4%	6.7%	7.1%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **TenCate Geosynthetics (formerly MIRAFI Construction Products)**

Contact Info: Ms. Teri Krock

365 S. Holland Dr.

Pendergrass, GA 30567

Phone:(706) 693-2226

Fax: (706) 693-4400

Email: t.krock@tencate.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	MIRAFIFW-400	MF-W	07-04-07	Mean	366	26	339	25	144	148	1177	1.57	0.32	6		
				COV (%)	3.8%		5.3%		8.3%	8.1%	6.3%	20.4%	9.4%	0.5%		
				MARV												
Jul-11	MIRAFI 600X	SF-W	07-04-14	Mean	405	28	411	19	187	144	1456	0.14	0.17	7.4		
				COV (%)	4.0%		3.6%		4.8%	4.9%	3.4%	28.6%	11.8%	0.3%		
				MARV												
Jul-11	PP15	SF-W	07-04-30	Mean	405	28	411	19	187	144	1456	0.14	0.17	7.4		
				COV (%)	4.0%		3.6%		4.8%	4.9%	3.4%	28.6%	11.8%	0.3%		
				MARV												
Jul-11	PW44	MF-W	07-04-31	Mean	400	24	358	24	257	435	1114	0.98	0.42	8.3		
				COV (%)	10.3%		7.3%		8.6%	12.4%	8.3%	3.1%	0.0%	0.6%		
				MARV												
Jul-11	PP 10	SF-W	07-04-32	Mean	243	26	189	23	124	115	712	0.22	0.16	4		
				COV (%)	5.8%		12.7%		5.6%	7.0%	5.6%	13.6%	6.3%	1.8%		
				MARV												
Sep-11	FW700	MF-W	08-04-18	Mean	419	25	257	25	155	106	996	0.53	0.25	6.2		
				COV (%)	2.1%		6.6%		6.5%	7.5%	8.2%	5.7%	12.0%	0.5%		
				MARV												
Sep-11	140 NC	NP-NW	08-04-19	Mean	128	61	143	66	62	81	376	2.64	0.2	4.44		
				COV (%)	21.1%		14.7%		16.1%	16.0%	8.2%	9.8%	5.0%	6.5%		
				MARV												
Sep-11	160N	NP-NW	08-04-20	Mean	185	66	194	90	94	110	529	2.1	0.21	7.14		
				COV (%)	13.0%		6.2%		12.8%	19.1%	9.3%	10.0%	1.0%	3.4%		
				MARV												
Sep-11	180N	NP-NW	08-04-21	Mean	220	56	214	74	135	161	724	1.28	0.16	8.89		
				COV (%)	23.6%		17.3%		20.0%	23.0%	13.8%	24.2%	6.3%	2.4%		
				MARV												
Sep-11	MPV 500	HB-NW	08-04-22	Mean	108	54	104	71	52	61	326	2.36	0.21	4.66		
				COV (%)	11.1%		13.5%		17.3%	13.1%	13.5%	9.3%	9.5%	8.4%		
				MARV												

Manufacturer: **TenCate Geosynthetics (formerly MIRAFI Construction Products)**

Contact Info: Ms. Teri Krock

365 S. Holland Dr.

Pendergrass, GA 30567

Phone:(706) 693-2226

Fax: (706) 693-4400

Email: t.krock@tencate.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355			
					MD		XD		Strength (lbs)		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD	MD	XD						
Sep-11	PW70	MF-W	08-04-25	Mean	419	25	257	25	155	106	996	0.53	0.25	6.2				
				COV (%)	2.1%		6.6%		6.5%	7.5%	8.2%	5.7%	12.0%	0.5%				
				MARV														
Sep-11	TN40	NP-NW	08-04-26	Mean	128	61	143	66	62	81	376	2.64	0.2	4.44				
				COV (%)	21.1%		14.7%		16.1%	16.0%	8.2%	9.8%	5.0%	6.5%				
				MARV														
Sep-11	TN60	NP-NW	08-04-27	Mean	185	66	194	90	94	110	529	2.1	0.21	7.14				
				COV (%)	13.0%		6.2%		12.8%	19.1%	9.3%	10.0%	1.0%	3.4%				
				MARV														
Sep-11	TN80	NP-NW	08-04-28	Mean	220	56	214	74	135	161	724	1.28	0.16	8.89				
				COV (%)	23.6%		17.3%		20.0%	23.0%	13.8%	24.2%	6.3%	2.4%				
				MARV														
Sep-12	Mirafi 550X	SF-W	09-07-01	Mean	321	28	264	17	148	110	1261	0.21	0.28	6.0	Not Tested	Not Tested		
				COV (%)	2.8%	NA	5.7%	NA	6.7%	6.7%	4.3%	37.0%	3.4%	0.6%				
				MARV	250	NA	250	NA	90	90	900	0.05	0.43	5.0	70	70		
Sep-12	Mirafi 170N	NP-NW	09-07-02	Mean	195	63	188	83	128	141	632	1.21	0.15	7.0	Not Tested	Not Tested		
				COV (%)	14.3%	NA	12.8%	NA	25.1%	21.3%	12.8%	15.6%	2.3%	6.1%				
				MARV	180	NA	180	NA	75	75	450	1.2	0.15	7.4	70	70		
Sep-12	Mirafi 1100 NPA	NP-NW	09-07-03	Mean	307	66	280	112	193	236	914	0.95	0.12	11.1	Not Tested	Not Tested		
				COV (%)	13.3%	NA	16.6%	NA	14.3%	11.2%	10.3%	4.2%	3.7%	5.1%				
				MARV	270	NA	270	NA	100	100	700	0.8	0.15	10.8	70	70		
Sep-12	Mirafi HP370	C-W	09-07-04	Mean	463	25	314	21	217	164	1457	0.61	0.38	8.5	Not Tested	Not Tested		
				COV (%)	6.1%	NA	6.9%	NA	12.4%	10.8%	13.2%	11.7%	3.5%	0.9%				
				MARV	400	NA	250	NA	170	125	1300	0.52	0.60	8.8	80	80		
Sep-12	Mirafi HP565	C-W	09-07-05	Mean	587	24	576	21	211	398	2090	0.15	0.14	12.9	Not Tested	Not Tested		
				COV (%)	5.0%	NA	11.4%	NA	6.2%	11.2%	8.5%	8.6%	24.0%	0.3%				
				MARV	550	NA	550	NA	150	200	1750	0.025	0.43	13.0	80	80		
Sep-12	Mirafi HP570	C-W	09-07-06	Mean	487	21	503	16	226	412	2081	0.78	0.60	13.8	Not Tested	Not Tested		
				COV (%)	15.2%	NA	8.0%	NA	4.0%	15.5%	7.8%	6.6%	0.5%	0.4%				
				MARV	475	NA	440	NA	180	180	2000	0.40	0.60	14	80	80		

Manufacturer: **TenCate Geosynthetics (formerly MIRAFI Construction Products)**

Contact Info: Ms. Teri Krock

365 S. Holland Dr.

Pendergrass, GA 30567

Phone:(706) 693-2226

Fax: (706) 693-4400

Email: t.krock@tencate.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-12	PP35	C-W	09-07-49	Mean	463	25	314	21	217	164	1457	0.61	0.38	8.5	Not Tested	Not Tested
				COV (%)	6.1%	NA	6.9%	NA	12.4%	10.8%	13.2%	11.7%	3.5%	0.9%		
				MARV	400	NA	250	NA	170	125	1300	0.52	0.60	8.8	80	80
Sep-12	PP70	C-W	09-07-50	Mean	487	21	503	16	226	412	2081	0.78	0.60	13.8	Not Tested	Not Tested
				COV (%)	15.2%	NA	8.0%	NA	4.0%	15.5%	7.8%	6.6%	0.5%	0.4%		
				MARV	475	NA	440	NA	180	180	2000	0.40	0.60	14	80	80
Sep-12	TN70	NP-NW	09-07-51	Mean	195	63	188	83	128	141	632	1.21	0.15	7.0	Not Tested	Not Tested
				COV (%)	14.3%	NA	12.8%	NA	25.1%	21.3%	12.8%	15.6%	2.3%	6.1%		
				MARV	180	NA	180	NA	75	75	450	1.2	0.15	7.4	70	70
Sep-12	TNPA11	NP-NW	09-07-52	Mean	307	66	280	112	193	236	914	0.95	0.12	11.1	Not Tested	Not Tested
				COV (%)	13.3%	NA	16.6%	NA	14.3%	11.2%	10.3%	4.2%	3.7%	5.1%		
				MARV	270	NA	270	NA	100	100	700	0.8	0.15	10.8	70	70
Apr-13	Mirafi HP770	C-W	09-10-16	Mean	774	29	604	27	341	522	2250	0.35	0.40	16.0	Not Tested	Not Tested
				COV (%)	6.6%	NA	9.3%	NA	14.9%	21.3%	9.3%	6.1%	17.4%	0.7%	NA	NA
				MARV	550	NA	450	NA	250	300	1900	0.23	0.60	17.0 ave	80	80
Apr-13	Mirafi 500X	SF-W	09-10-19	Mean	260	29	203	21	110	92	860	0.13	0.20	4.2	80	76
				COV (%)	5.9%	NA	7.7%	NA	5.0%	8.0%	2.5%	22.4%	10.0%	1.0%	NA	NA
				MARV	200	NA	200	NA	75	75	700	0.05	0.42	4.0 ave	70	70
Apr-13	Mirafi MPV500	NP-NW	09-10-21	Mean	111	69	96	89	53	52	260	2.34	0.21	4.0	79	75
				COV (%)	4.1%	NA	18.2%	NA	17.1%	25.3%	22.0%	9.4%	9.5%	2.5%	NA	NA
				MARV	101	NA	101	NA	39	39	250	1.75	0.21	4.4 ave	70	70
Apr-13	PP10	SF-W	09-10-22	Mean	260	29	203	21	110	92	860	0.13	0.20	4.2	80	76
				COV (%)	5.9%	NA	7.7%	NA	5.0%	8.0%	2.5%	22.4%	10.0%	1.0%	NA	NA
				MARV	200	NA	200	NA	75	75	700	0.05	0.42	4.0 ave	70	70
Apr-14	Mirafi HP270	C-W	2010-04-006	Mean	320	18	254	17	133	126	1149	0.50	0.49	6.2	100	74
				COV (%)	3.5%	NA	6.6%	NA	9.6%	8.2%	7.0%	7.0%	10.1%	0.8%	NA	NA
				MARV	290	NA	255	NA	120	140	1000	0.70	0.60	5.7	80	80
Apr-14	Mirafi 140NL	NP-NW	2010-04-007	Mean	121	59	87	103	65	62	267	2.36	0.24	3.5	78	80
				COV (%)	19.7%	NA	13.6%	NA	21.0%	15.6%	12.6%	21.7%	7.0%	8.1%	NA	NA
				MARV	90	NA	90	NA	40	40	250	2.00	0.25	2.8	70	70

Manufacturer: **TenCate Geosynthetics (formerly MIRAFI Construction Products)**

Contact Info: Ms. Teri Krock

365 S. Holland Dr.

Pendergrass, GA 30567

Phone:(706) 693-2226

Fax: (706) 693-4400

Email: t.krock@tencate.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355			
					MD		XD		Strength (lbs)		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD	MD	XD						
Apr-14	Mirafi 140N	NP-NW	2010-04-008	Mean	114	61	129	83	56	84	375	1.84	0.18	4.9	Not Tested	Not Tested		
				COV (%)	16.1%	NA	10.7%	NA	11.9%	14.2%	6.9%	12.8%	13.1%	7.4%	NA	NA		
				MARV	120	NA	120	NA	50	50	300	1.70	0.21	3.0	NA	NA		
Apr-14	Mirafi FW402	MF-W	2010-04-009	Mean	449	33	212	13	231	103	817	2.06	0.36	6.1	100	100		
				COV (%)	5.0%	NA	3.3%	NA	19.3%	10.9%	12.1%	2.1%	13.3%	2.3%	NA	NA		
				MARV	365	NA	200	NA	115	75	675	2.10	0.43	5.6	90	90		
Apr-14	Mirafi FW404	MF-W	2010-04-010	Mean	406	22	386	21	201	395	1328	0.83	0.42	8.7	Not Tested	Not Tested		
				COV (%)	6.6%	NA	8.5%	NA	8.2%	10.7%	12.6%	6.6%	0.7%	0.9%	NA	NA		
				MARV	400	NA	315	NA	150	165	1150	0.90	0.43	7.8	NA	NA		
Apr-14	Mirafi MPV600	NP-NW	2010-04-012	Mean	146	65	133	81	73	89	347	1.54	0.20	4.8	Not Tested	Not Tested		
				COV (%)	9.5%	NA	10.9%	NA	10.6%	13.6%	12.5%	20.1%	5.5%	9.1%	NA	NA		
				MARV	120	NA	120	NA	45	45	320	1.50	0.21	4.6	NA	NA		
Apr-14	Mirafi S800	NP-NW	2010-04-013	Mean	274	60	246	85	160	168	768	1.46	0.16	8.2	73	73		
				COV (%)	6.6%	NA	8.4%	NA	12.5%	16.7%	7.6%	17.0%	8.1%	1.8%	NA	NA		
				MARV	230	NA	230	NA	90	90	600	1.36	0.15	8.0	80	80		
Apr-14	Mirafi S1000	NP-NW	2010-04-014	Mean	324	63	290	80	166	203	972	1.21	0.15	10.4	Not Tested	Not Tested		
				COV (%)	8.2%	NA	10.5%	NA	12.7%	16.4%	7.9%	10.4%	2.7%	7.9%	NA	NA		
				MARV	265	NA	265	NA	100	100	700	1	0.15	10.0	NA	NA		

Manufacturer: Ten Cate Geosynthetics

Contact Info:

Fax:

Email:

Notes: (1) MARV's based on submission information. (2) Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		Puncture Index	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D4833	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD						MD	XD
TWB 12/15/2010	Mirafi HP270	C-W	2010-04-006	Mean	320	18	254	17	133	126	NA	1149	0.50	0.49	6.2	100	74
				COV (%)	3.5%	NA	6.6%	NA	9.6%	8.2%	NA	7.0%	7.0%	10.1%	0.8%	NA	NA
				MARV	290	NA	255	NA	120	140	NA	1000	0.70	0.60	5.7	80	80
TWB 12/15/2010	Mirafi 140NL	NP-NW	2010-04-007	Mean	121	59	87	103	65	62	NA	267	2.36	0.24	3.5	78	80
				COV (%)	19.7%	NA	13.6%	NA	21.0%	15.6%	NA	12.6%	21.7%	7.0%	8.1%	NA	NA
				MARV	90	NA	90	NA	40	40	NA	250	2.00	0.25	2.8	70	70
TWB 12/15/2010	Mirafi 140N	NP-NW	2010-04-008	Mean	114	61	129	83	56	84	NA	375	1.84	0.18	4.9	Not Tested	Not Tested
				COV (%)	16.1%	NA	10.7%	NA	11.9%	14.2%	NA	6.9%	12.8%	13.1%	7.4%	NA	NA
				MARV	120	NA	120	NA	50	50	NA	300	1.70	0.21	3.0	NA	NA
TWB 12/15/2010	Mirafi FW402	MF-W	2010-04-009	Mean	449	33	212	13	231	103	NA	817	2.06	0.36	6.1	100	100
				COV (%)	5.0%	NA	3.3%	NA	19.3%	10.9%	NA	12.1%	2.1%	13.3%	2.3%	NA	NA
				MARV	365	NA	200	NA	115	75	NA	675	2.10	0.43	5.6	90	90
TWB 12/15/2010	Mirafi FW404	MF-W	2010-04-010	Mean	406	22	386	21	201	395	NA	1328	0.83	0.42	8.7	Not Tested	Not Tested
				COV (%)	6.6%	NA	8.5%	NA	8.2%	10.7%	NA	12.6%	6.6%	0.7%	0.9%	NA	NA
				MARV	400	NA	315	NA	150	165	NA	1150	0.90	0.43	7.8	NA	NA
TWB 12/15/2010	Mirafi MPV600	NP-NW	2010-04-012	Mean	146	65	133	81	73	89	NA	347	1.54	0.20	4.8	Not Tested	Not Tested
				COV (%)	9.5%	NA	10.9%	NA	10.6%	13.6%	NA	12.5%	20.1%	5.5%	9.1%	NA	NA
				MARV	120	NA	120	NA	45	45	NA	320	1.50	0.21	4.6	NA	NA
TWB 12/15/2010	Mirafi S800	NP-NW	2010-04-013	Mean	274	60	246	85	160	168	NA	768	1.46	0.16	8.2	73	73
				COV (%)	6.6%	NA	8.4%	NA	12.5%	16.7%	NA	7.6%	17.0%	8.1%	1.8%	NA	NA
				MARV	230	NA	230	NA	90	90	NA	600	1.36	0.15	8.0	80	80
TWB 12/15/2010	Mirafi S1000	NP-NW	2010-04-014	Mean	324	63	290	80	166	203	NA	972	1.21	0.15	10.4	Not Tested	Not Tested
				COV (%)	8.2%	NA	10.5%	NA	12.7%	16.4%	NA	7.9%	10.4%	2.7%	7.9%	NA	NA
				MARV	265	NA	265	NA	100	100	NA	700	1	0.15	10.0	NA	NA
				Mean													
				COV (%)													

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Thrace-LINQ

Contact Info: Mr. Daniel Selander
 2550 West Fifth North St.
 Summerville, SC 29483-9699
 Phone:(843) 873-5800

Fax:

Email: dselander@thracelinq.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	AOL	NP-NW	07-09-12	Mean	126	67	154	67	50	82	347	2.23	0.2	4.9		
				COV (%)	7.9%		10.4%		10.0%	4.9%	5.8%	5.8%	5.0%	2.0%		
				MARV												
Sep-11	130 EX	NP-NW	07-09-13	Mean	139	76	134	74	53	71	323	2.61	0.19	4.4		
				COV (%)	11.5%		9.7%		17.0%	8.5%	15.5%	18.4%	5.3%	2.3%		
				MARV												
Sep-11	150 EX	NP-NW	07-09-14	Mean	169	69	263	58	75	118	593	1.68	0.17	7.1		
				COV (%)	17.8%		11.8%		25.3%	12.7%	14.8%	23.2%	11.8%	4.2%		
				MARV												
Sep-11	160 EX	NP-NW	07-09-15	Mean	186	80	207	86	98	109	574	2.26	0.21	7.8		
				COV (%)	16.7%		9.2%		13.3%	13.8%	14.5%	5.8%	0.0%	5.1%		
				MARV												
Sep-11	180 EX	NP-NW	07-09-16	Mean	231	82	251	79	119	136	636	1.69	0.18	7.6		
				COV (%)	7.8%		14.3%		16.0%	11.0%	9.7%	15.4%	11.1%	7.9%		
				MARV												
Sep-11	225 EX	NP-NW	07-09-17	Mean	275	77	277	85	120	146	666	1.78	0.2	8.7		
				COV (%)	13.5%		17.0%		20.0%	12.3%	8.7%	7.9%	5.0%	5.7%		
				MARV												
Sep-11	250 EX	NP-NW	07-09-18	Mean	338	70	354	79	170	229	743	1.24	0.17	10.1		
				COV (%)	21.3%		13.8%		26.5%	15.7%	16.8%	16.9%	11.8%	5.9%		
				MARV												
Sep-11	275 EX	NP-NW	07-09-19	Mean	384	76	458	84	193	248	1005	1.25	0.15	11.7		
				COV (%)	18.2%		12.7%		19.2%	10.5%	8.8%	13.6%	6.7%	16.2%		
				MARV												
Sep-11	350 EX	NP-NW	07-09-20	Mean	461	70	564	87	202	224	1362	0.7	0.13	17.2		
				COV (%)	18.0%		6.0%		9.4%	10.7%	7.6%	17.1%	7.7%	8.1%		
				MARV												
Sep-11	GTF-190SF	SF-W	07-09-21	Mean	134	18	113	20	79	74	350	0.14	0.29	2.7		
				COV (%)	11.9%		6.2%		11.4%	8.1%	5.4%	42.9%	17.2%	1.9%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Thrace-LINQ

Contact Info: Mr. Daniel Selander
 2550 West Fifth North St.
 Summerville, SC 29483-9699
 Phone:(843) 873-5800

Fax:

Email: dselander@thracelinq.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	GTF-180SF	SF-W	07-09-22	Mean	134	18	108	24	83	70	363	0.16	0.27	2.8		
				COV (%)	7.5%		15.7%		14.5%	7.1%	3.9%	31.3%	11.1%	0.7%		
				MARV												
Sep-11	GTF-170SF	SF-W	07-09-23	Mean	102	24	91	24	56	47	266	0.15	0.29	2.2		
				COV (%)	15.7%		9.9%		7.1%	4.3%	7.5%	53.3%	24.1%	1.8%		
				MARV												
Sep-11	GTF-195SF	SF-W	07-09-24	Mean	156	19	96	14	73	48	448	0.22	0.23	2.7		
				COV (%)	7.7%		9.4%		8.2%	10.4%	4.2%	22.7%	13.0%	0.7%		
				MARV												
Sep-11	GTF-300	SF-W	07-09-26	Mean	371	24	346	16	150	124	1281	0.14	0.21	6.7		
				COV (%)	4.9%		3.5%		7.3%	5.6%	9.0%	42.9%	19.0%	0.6%		
				MARV												
Sep-11	GTF-270	SF-W	07-09-27	Mean	346	25	344	19	137	131	1171	0.18	0.32	6.2		
				COV (%)	5.2%		4.1%		5.8%	4.6%	2.7%	38.9%	31.3%	0.3%		
				MARV												
Sep-11	GTF-250	SF-W	07-09-29	Mean	336	24	305	15	124	109	1143	0.19	0.19	5.9		
				COV (%)	4.8%		5.6%		3.2%	3.7%	3.7%	31.6%	5.3%	1.7%		
				MARV												
Sep-11	GTF-400	SF-W	07-09-30	Mean	475	24	428	16	216	155	1556	0.23	0.3	9.7		
				COV (%)	4.4%		4.9%		8.3%	7.1%	10.1%	34.8%	6.7%	1.0%		
				MARV												
Sep-11	GTF-500	SF-W	07-09-31	Mean	719	29	691	21	321	222	2200	0.19	0.17	12.7		
				COV (%)	3.5%		3.0%		6.5%	2.3%	10.6%	21.1%	5.9%	0.8%		
				MARV												
Sep-11	GTF-700	SF-W	07-09-32	Mean	875	29	836	26	399	284	2600	0.21	0.19	14.7		
				COV (%)	2.7%		2.0%		7.8%	3.2%	4.5%	19.0%	5.3%	1.4%		
				MARV												
Sep-11	245 EX	NP-NW	07-09-33	Mean	288	79	331	77	177	184	793	1.26	0.17	10.4		
				COV (%)	20.8%		10.6%		18.1%	8.2%	10.7%	9.5%	11.8%	7.7%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Thrace-LINQ

Contact Info: Mr. Daniel Selander
 2550 West Fifth North St.
 Summerville, SC 29483-9699
 Phone:(843) 873-5800

Fax:

Email: dselander@thracelinq.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jun-12	120 EX	NP-NW	09-01-12	Mean	92	62	81	72	40	42	253	3.04	0.24	3.1	83	83
				COV (%)	7.6%		7.4%		12.5%	21.4%	19.8%	12.2%	12.5%	6.8%		
				MARV	80	NA	80	NA	35	35	220	2.20	0.21	2.8	70	70
Jun-12	GTF 200S	SF-W	09-01-13	Mean	219	20	185	14	84	76	799	0.19	0.28	4.2	96	81
				COV (%)	4.1%		6.5%		8.3%	10.5%	4.3%	21.1%	25.0%	1.0%		
				MARV	180	NA	180	NA	70	70	550	0.08	0.43	4.5	80	80
Jun-12	GTF 350	SF-W	09-01-14	Mean	360	27	338	24	149	155	1278	0.31	0.28	6.7	Not Tested	Not Tested
				COV (%)	2.8%		5.9%		4.7%	7.1%	5.1%	12.9%	3.6%	1.2%		
				MARV	350	NA	350	NA	120	120	1000	0.27	0.50	6.9	80	80
Jun-12	AOM	NP-NW	09-01-15	Mean	118	74	140	78	50	60	330	2.30	0.15	4.9	Not Tested	Not Tested
				COV (%)	10.2%		5.7%		12.0%	11.7%	8.5%	6.5%	6.8%	2.7%		
				MARV	105	NA	105	NA	45	45	NA	NA	NA	4.1	70	70
Jun-12	120GEX	NP-NW	09-01-16	Mean	100	59	64	97	40	31	195	3.00	0.13	3.3	91	59
				COV (%)	7.0%		12.5%		10.0%	12.9%	6.7%	12.0%	15.4%	5.5%		
				MARV	100	NA	90	NA	30	30	250	1.50	0.21	3.0	70	70
Jun-12	GTF 404	MF-W	09-01-17	Mean	444	22	358	21	275	298	1361	1.10	0.42	8.8	Not Tested	Not Tested
				COV (%)	7.2%		5.9%		4.7%	12.8%	11.4%	6.4%	0.2%	0.6%		
				MARV	400	NA	315	NA	150	165	1150	0.90	0.43	8.0	90	90
Jun-12	GTF 465	MF-W	09-01-18	Mean	504	24	384	25	196	224	1450	0.63	0.40	8.6	Not Tested	Not Tested
				COV (%)	5.0%		12.5%		7.1%	10.3%	9.0%	14.3%	2.5%	1.4%		
				MARV	450	NA	350	NA	140	175	NA	0.26	0.43	10.1	70	70
Jun-12	GTF 400E	MF-W	09-01-19	Mean	496	36	278	31	192	77	1064	0.76	0.21	6.3	Not Tested	Not Tested
				COV (%)	3.6%		4.3%		6.8%	10.4%	3.5%	5.3%	0.0%	0.3%		
				MARV	370	NA	250	NA	100	60	950	0.28	0.21	5.6	90	90
Jun-12	GTF 400EO	MF-W	09-01-20	Mean	430	35	234	16	191	106	737	2.70	0.44	6.0	94	96
				COV (%)	3.7%		3.4%		11.0%	5.7%	16.4%	7.8%	18.2%	0.7%		
				MARV	365	NA	200	NA	115	75	675	2.10	0.43	5.6	90	90
Jun-12	GTF 370	MF-W	09-01-21	Mean	503	34	301	22	273	150	1565	0.53	0.36	9.8	Not Tested	Not Tested
				COV (%)	3.4%		5.0%		7.0%	7.3%	19.0%	13.2%	8.3%	0.7%		
				MARV	400	NA	250	NA	180	110	NA	0.52	0.60	8.5	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Thrace-LINQ

Contact Info: Mr. Daniel Selander
 2550 West Fifth North St.
 Summerville, SC 29483-9699
 Phone:(843) 873-5800

Fax:

Email: dselander@thracelinq.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jun-12	GTF 570	MF-W	09-01-22	Mean	521	23	484	23	253	343	1389	0.68	0.59	13.9	Not Tested	Not Tested
				COV (%)	6.0%		11.8%		9.5%	16.6%	11.3%	13.2%	0.3%	0.6%		
				MARV	475	NA	440	NA	180	180	NA	0.40	0.60	14.5	70	70
Sep-12	125EX	NP-NW	09-04-13	Mean	125	66	130	71	66	72	390	2.26	0.17	4.6	88	85
				COV (%)	5.9%	NA	6.8%	NA	16.9%	9.8%	3.3%	6.1%	2.6%	2.8%		
				MARV	90	NA	90	NA	40	40	265	2.1	0.212	3.5	70	70
Sep-12	140EX	NP-NW	09-04-14	Mean	144	92	178	82	79	105	426	2.45	0.21	5.5	70	71
				COV (%)	18.6%	NA	11.5%	NA	12.4%	12.8%	9.3%	17.1%	20.1%	4.4%		
				MARV	120	NA	120	NA	50	50	340	1.8	0.212	4.5	70	70
Sep-12	AOH	NP-NW	09-04-15	Mean	125	76	152	77	55	77	414	1.98	0.15	4.9	Not Tested	Not Tested
				COV (%)	9.8%	NA	9.5%	NA	14.7%	12.4%	6.4%	20.4%	1.4%	4.1%		
				MARV	120	NA	120	NA	50	50	NA	NA	NA	4.6	70	70
Apr-13	145EX	NP-NW	09-10-12	Mean	229	73	231	76	97	95	633	1.34	0.13	7.8	Not Tested	Not Tested
				COV (%)	6.0%	NA	8.9%	NA	6.4%	11.0%	4.9%	10.7%	7.6%	2.3%	NA	NA
				MARV	140	NA	140	NA	60	60	360	1.50	0.21	5.5 ave	70	70
Apr-13	GTF200	SF-W	09-10-13	Mean	224	28	261	24	97	117	908	0.23	0.36	5.0	Not Tested	Not Tested
				COV (%)	7.3%	NA	4.4%	NA	5.3%	7.9%	2.2%	34.0%	14.0%	1.2%	NA	NA
				MARV	200	NA	200	NA	75	75	700	0.08	0.42	5.0 ave	80	80
Apr-13	335EX	NP-NW	09-10-14	Mean	371	73	407	87	155	182	1178	0.71	0.10	14.2	Not Tested	Not Tested
				COV (%)	7.6%	NA	8.4%	NA	8.5%	6.9%	4.0%	12.8%	2.9%	1.9%	NA	NA
				MARV	205	NA	205	NA	80	80	535	0.7	0.15	15.0	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: US Fabrics

Contact Info: Mr. Dan Bonn
3904 Virginia Ave
Cincinnati, OH 45227
Phone:

Fax:

Email: dan@usfabricsinc.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	US 230	MF-W	07-04-28	Mean	400	24	358	24	257	435	1114	0.98	0.42	8.3		
				COV (%)	10.3%		7.3%		8.6%	12.4%	8.3%	3.1%	0.0%	0.6%		
				MARV												
Sep-12	US 90NW	NP-NW	2010-02-006	Mean	95	60	111	86	55	70	321	2.14	0.18	3.6	Not Tested	Not Tested
				COV (%)	14.7%	NA	10.8%	NA	9.6%	13.7%	14.4%	20.3%	11.6%	19.4%		
				MARV	90	NA	90	NA	40	40	300	2.2	0.30	3.5	70	70
Apr-13	US 115NW	NP-NW	2010-02-007	Mean	129	122	124	55	84	60	334	2.08	0.22	4.2	Not Tested	Not Tested
				COV (%)	15.4%	NA	13.8%	NA	16.4%	15.3%	17.7%	14.9%	13.4%	5.9%		
				MARV	100	NA	100	NA	50	50	325	2.0	0.212	4.0	70	70
Sep-12	US 120NW	NP-NW	2010-02-008	Mean	135	58	123	78	58	65	406	1.72	0.15	4.4	Not Tested	Not Tested
				COV (%)	9.6%	NA	7.0%	NA	25.3%	12.1%	10.6%	10.9%	1.8%	8.2%		
				MARV	120	NA	120	NA	50	50	350	1.8	0.212	4.2	70	70
Sep-12	US 180NW	NP-NW	2010-02-009	Mean	224	76	232	92	121	141	638	1.31	0.13	7.3	Not Tested	Not Tested
				COV (%)	6.2%	NA	8.1%	NA	21.4%	10.6%	6.6%	4.7%	2.8%	8.7%		
				MARV	180	NA	180	NA	75	75	525	1.5	0.212	7.0	70	70
Sep-12	US 205NW	NP-NW	2010-02-010	Mean	259	76	237	89	122	146	747	1.02	0.11	7.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	7.8%	NA	7.3%	20.3%	5.2%	7.7%	8.4%	7.3%		
				MARV	205	NA	205	NA	85	85	650	1.4	0.180	8.0	70	70
Sep-11	US 270NW	NP-NW	2010-02-011	Mean	315	66	266	90	115	139	728	0.84	0.13	9.9		
				COV (%)	7.6%		8.6%		11.3%	11.5%	6.6%	16.7%	7.7%	4.8%		
				MARV												
Sep-12	US 200	SF-W	2010-02-012	Mean	207	23	216	20	97	104	805	0.11	0.13	4.3	83	64
				COV (%)	3.4%	NA	3.9%	NA	6.1%	3.8%	4.0%	45.6%	6.4%	0.7%		
				MARV	200	NA	200	NA	75	75	450	0.05	0.3	4.0	70	70
Apr-13	US 315	SF-W	2010-02-013	Mean	372	33	379	22	165	128	1472	0.16	0.19	6.8	Not tested	Not Tested
				COV (%)	5.1%	NA	3.5%	NA	9.3%	4.5%	1.6%	27.9%	15.5%	1.5%	NA	NA
				MARV	315	NA	315	NA	120	120	1000	0.05	0.43	6.3	70	70
Sep-11	US 670	MF-W	2010-02-014	Mean	446	27	275	26	183	100	860	0.45	0.17	6		
				COV (%)	2.7%		5.1%		5.5%	9.0%	16.9%	40.0%	11.8%	1.0%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **US Fabrics**

Contact Info: Mr. Dan Bonn
3904 Virginia Ave
Cincinnati, OH 45227
Phone:

Fax:

Email: dan@usfabricsinc.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	US 300NW	NP-NW	2010-02-015	Mean	340	73	327	92	151	134	875	1.03	0.13	11.3		
				COV (%)	9.1%		4.0%		10.6%	6.0%	4.9%	4.9%	15.4%	4.0%		
				MARV												
Sep-11	US 90P	NP-NW	2010-02-016	Mean	114	48	103	71	49	54	318	1.37	0.15	4		
				COV (%)	11.4%		14.6%		16.3%	11.1%	13.8%	23.4%	6.7%	4.0%		
				MARV												
Sep-11	US 100P	NP-NW	2010-02-017	Mean	146	49	122	71	53	59	346	1.16	0.14	4.6		
				COV (%)	12.3%		14.8%		13.2%	10.2%	15.6%	25.9%	0.0%	3.3%		
				MARV												
Sep-11	US 100	SF-W	2010-02-018	Mean	243	24	313	33	144	91	718	2.79	0.76	5.8		
				COV (%)	6.6%		5.1%		9.7%	6.6%	15.5%	6.1%	10.5%	1.4%		
				MARV												
Sep-11	US 250	SF-W	2010-02-019	Mean	318	26	288	22	132	113	1025	0.17	0.26	5.8		
				COV (%)	2.8%		3.1%		6.8%	5.3%	4.8%	5.9%	15.4%	0.5%		
				MARV												
Sep-11	US 1540	MF-W	2010-02-020	Mean	374	36	201	22	117	48	639	1.89	0.39	5.7		
				COV (%)	4.5%		5.0%		4.3%	10.4%	3.3%	3.2%	30.8%	1.2%		
				MARV												
Sep-11	US 380NW	NP-NW	2010-02-021	Mean	547	76	546	99	216	265	1356	0.61	0.12	16.9		
				COV (%)	6.8%		11.4%		11.6%	4.9%	3.7%	13.1%	0.0%	3.9%		
				MARV												
Apr-13	US 80NW	NP-NW	2010-02-022	Mean	86	62	101	87	45	56	296	3.25	0.25	3.2	Pending	Pending
				COV (%)	13.0%	NA	15.1%	NA	9.8%	27.7%	12.1%	9.1%	11.8%	7.7%	NA	NA
				MARV	80	NA	80	NA	30	30	175	2.20	0.30	3.1 ave	70	70
Sep-12	US 160NW	NP-NW	2010-02-023	Mean	196	69	195	80	98	96	511	1.83	0.15	6.0	Not Tested	Not Tested
				COV (%)	16.0%	NA	9.6%	NA	13.3%	9.2%	6.6%	19.5%	0.3%	9.0%		
				MARV	160	NA	160	NA	65	65	450	1.6	0.212	6.0		

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Vantage Partners, LLC

Contact Info: Mr. Randy DeMao
 1000 Buck's Industrial Park
 Statesville, NC 28625
 Phone:(704) 871-8700

Fax: (704) 871-9700

Email: randy@vp-geos.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Jul-11	PRM-1	SF-W	07-06-02	Mean	143	20	146	22	71	70	449	0.15	0.34	3.05		
				COV (%)	9.1%		12.3%		7.0%	5.7%	3.3%	40.0%	14.7%	2.0%		
				MARV												
Jul-11	PRM-1A	SF-W	07-06-03	Mean	153	22	147	22	73	71	516	0.22	0.36	3.2		
				COV (%)	13.1%		10.9%		4.1%	5.6%	5.0%	40.9%	16.7%	1.3%		
				MARV												
Jul-11	PRM-2A	SF-W	07-06-04	Mean	238	22	253	25	104	114	802	0.07	0.24	4.38		
				COV (%)	8.0%		11.1%		5.8%	6.1%	3.4%	71.4%	20.8%	2.1%		
				MARV												
Jul-11	PRM-3A	SF-W	07-06-05	Mean	310	22	337	23	118	134	990	0.17	0.33	5.61		
				COV (%)	6.8%		4.2%		10.2%	6.7%	2.9%	23.5%	15.2%	1.1%		
				MARV												
Jul-11	PRM-3B	SF-W	07-06-06	Mean	299	22	324	24	121	137	982	0.09	0.26	5.29		
				COV (%)	6.7%		5.2%		10.7%	7.3%	4.7%	77.8%	3.8%	0.6%		
				MARV												
Jul-11	PRM-4A	SF-W	07-06-07	Mean	302	24	343	23	131	138	981	0.12	0.22	5.38		
				COV (%)	6.0%		5.2%		6.9%	5.1%	2.0%	25.0%	9.1%	0.6%		
				MARV												
Jul-11	SF-2	SF-W	07-09-34	Mean	84	21	87	26	53	57	221	0.2	0.47	1.8		
				COV (%)	8.3%		10.3%		11.3%	8.8%	5.0%	10.0%	14.9%	1.1%		
				MARV												
Jul-11	SF-3	SF-W	07-09-35	Mean	115	21	99	23	68	54	281	0.15	0.42	2.1		
				COV (%)	5.2%		8.1%		14.7%	7.4%	3.6%	26.7%	4.8%	1.9%		
				MARV												
Feb-12	SF-4	SF-W	09-01-01	Mean	101	21	104	20	51	49	310	0.26	0.5	2.4	Not Tested	Not Tested
				COV (%)	5.9%		11.5%		7.8%	6.1%	5.8%	23.1%	14.0%	0.4%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needle-punched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Western Excelsior**

Contact Info: Luke Snyder
 4505 Booneville Rd
 Evansville IN 47725
 Phone:(866) 540-9810

Fax: (812) 867-8928

Email: lsnyder@dfs.us.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-11	Excel 250W	SF-W	08-01-44	Mean	318	26	288	22	132	113	1025	0.17	0.26	5.8		
				COV (%)	2.8%		3.1%		6.8%	5.3%	4.8%	5.9%	15.4%	0.5%		
				MARV												
Sep-12	Excel 3.5N	NP-NW	09-07-27	Mean	95	60	111	86	55	70	321	2.14	0.18	3.6	Not Tested	Not Tested
				COV (%)	14.7%	NA	10.8%	NA	9.6%	13.7%	14.4%	20.3%	11.6%	19.4%		
				MARV	90	NA	90	NA	40	40	300	2.2	0.30	3.5	70	70
Sep-12	Excel 4.0N	NP-NW	09-07-28	Mean	129	122	124	55	84	60	334	2.08	0.22	4.2	Not Tested	Not Tested
				COV (%)	15.4%	NA	13.8%	NA	16.4%	15.3%	17.7%	14.9%	13.4%	5.9%		
				MARV	100	NA	100	NA	50	50	325	2.0	0.212	4.0	70	70
Sep-12	Excel 4.5N	NP-NW	09-07-29	Mean	135	58	123	78	58	65	406	1.72	0.15	4.4	Not Tested	Not Tested
				COV (%)	9.6%	NA	7.0%	NA	25.3%	12.1%	10.6%	10.9%	1.8%	8.2%		
				MARV	120	NA	120	NA	50	50	350	1.8	0.212	4.2	70	70
Sep-12	Excel 6.0N	NP-NW	09-07-30	Mean	196	69	195	80	98	96	511	1.83	0.15	6.0	Not Tested	Not Tested
				COV (%)	16.0%	NA	9.6%	NA	13.3%	9.2%	6.6%	19.5%	0.3%	9.0%		
				MARV	160	NA	160	NA	65	65	450	1.6	0.212	6.0		
Sep-12	Excel 7.0N	NP-NW	09-07-31	Mean	224	76	232	92	121	141	638	1.31	0.13	7.3	Not Tested	Not Tested
				COV (%)	6.2%	NA	8.1%	NA	21.4%	10.6%	6.6%	4.7%	2.8%	8.7%		
				MARV	180	NA	180	NA	75	75	525	1.5	0.212	7.0	70	70
Sep-12	Excel 8.0N	NP-NW	09-07-32	Mean	259	76	237	89	122	146	747	1.02	0.11	7.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	7.8%	NA	7.3%	20.6%	5.2%	7.7%	8.4%	7.3%		
				MARV	205	NA	205	NA	85	85	650	1.4	0.180	8.0	70	70
Sep-12	Excel 200W	SF-W	09-07-33	Mean	207	23	216	20	97	104	805	0.11	0.13	4.3	Pending	Pending
				COV (%)	3.4%	NA	3.9%	NA	6.1%	3.8%	4.0%	45.6%	6.4%	0.7%		
				MARV	200	NA	200	NA	75	75	450	0.05	0.3	4.0	70	70
Apr-13	Excel 370M	MF-W	2010-01-006	Mean	471	42	334	40	195	107	1079	0.98	0.25	6.4	Pending	Pending
				COV (%)	3.7%	NA	4.0%	NA	7.2%	12.6%	3.1%	4.7%	11.8%	0.3%	NA	NA
				MARV	370	NA	250	NA	100	60	NA	0.28	0.21	5.6 ave	90	90
Apr-13	Excel 3.0N	NP-NW	2010-01-007	Mean	86	62	101	87	45	56	296	3.25	0.25	3.2	83	94
				COV (%)	13.0%	NA	15.1%	NA	9.8%	27.7%	12.1%	9.1%	11.8%	7.7%	NA	NA
				MARV	80	NA	80	NA	30	30	175	2.20	0.30	3.1 ave	70	70

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: **Western Excelsior**

Contact Info: Luke Snyder
 4505 Booneville Rd
 Evansville IN 47725
 Phone:(866) 540-9810

Fax: (812) 867-8928

Email: lsnyder@dfs.us.com

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear	50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2		
					ASTM D4632				ASTM D4533	ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355		
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Apr-13	Excel 315W	SF-W	2010-01-008	Mean	372	33	379	22	165	128	1472	0.16	0.19	6.8	Not tested	Not Tested
				COV (%)	5.1%	NA	3.5%	NA	9.3%	4.5%	1.6%	27.9%	15.5%	1.5%	NA	NA
				MARV	315	NA	315	NA	120	120	1000	0.05	0.43	6.3	70	70
Sep-11	Excel 10.0N	NP-NW	2010-01-009	Mean	315	66	266	90	115	139	728	0.84	0.13	9.9		
				COV (%)	7.6%		8.6%		11.3%	11.5%	6.6%	16.7%	7.7%	4.8%		
				MARV												
Sep-11	Excel 12.0N	NP-NW	2010-01-010	Mean	340	73	327	92	151	134	875	1.03	0.13	11.3		
				COV (%)	9.1%		4.0%		10.6%	6.0%	4.9%	4.9%	15.4%	4.0%		
				MARV												
Sep-11	Excel 16.0N	NP-NW	2010-01-011	Mean	547	76	546	99	216	265	1356	0.61	0.12	16.9		
				COV (%)	6.8%		11.4%		11.6%	4.9%	3.7%	13.1%	0.0%	3.9%		
				MARV												

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needlepunched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Willacoochee Industries Fabrics

Contact Info: Mr. Larry Booth

PO Box 599

Willacoochee, GA 31650

Phone:(912) 534-5757

Fax:

Email: larrylbooth@windstream.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355			
					MD		XD		Strength (lbs)		MD	XD	Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD							MD	XD
Jul-11	3200	SF-W	07-04-26	Mean	107	22	136	20	61	70	492	0.11	0.31	3.1				
				COV (%)	4.7%		6.6%		9.8%	10.0%	2.8%	18.2%	16.1%	1.3%				
				MARV														
Jul-11	1210	SF-W	07-04-27	Mean	113	21	116	14	72	51	500	0.21	0.45	3.4				
				COV (%)	8.0%		8.6%		13.9%	7.8%	3.2%	23.8%	15.6%	0.3%				
				MARV														
Sep-11	1211	SF-W	08-01-22	Mean	152	21	140	13	68	69	559	0.16	0.26	3.7				
				COV (%)	6.6%		6.4%		11.8%	5.8%	4.5%	25.0%	26.9%	0.8%				
				MARV														
Sep-11	100SF	SF-W	08-01-23	Mean	158	16	84	25	73	49	372	0.26	0.33	2.6				
				COV (%)	8.9%		21.4%		6.8%	22.4%	5.6%	42.3%	9.1%	1.9%				
				MARV														
Sep-11	105SF	SF-W	08-01-24	Mean	163	23	143	15	68	67	573	0.22	0.3	3.5				
				COV (%)	3.7%		5.6%		5.9%	4.5%	2.6%	22.7%	16.7%	1.4%				
				MARV														
Sep-11	200W	SF-W	08-01-25	Mean	237	23	250	18	105	92	819	0.15	0.28	5.2				
				COV (%)	7.6%		3.2%		4.8%	6.5%	3.4%	26.7%	17.9%	0.6%				
				MARV														
Sep-11	315W	SF-W	08-01-26	Mean	358	27	390	15	145	114	1230	0.13	0.19	8.2				
				COV (%)	4.7%		1.3%		9.0%	7.0%	1.4%	38.5%	42.1%	0.9%				
				MARV														
Sep-11	77SF	SF-W	08-01-29	Mean	101	19	115	15	63	55	1148	0.21	0.57	3.2				
				COV (%)	8.9%		3.5%		12.7%	9.1%	1.7%	19.0%	14.0%	0.6%				
				MARV														
Sep-11	WINfab 250W	SF-W	08-01-45	Mean	318	26	288	22	132	113	1025	0.17	0.26	5.8				
				COV (%)	2.8%		3.1%		6.8%	5.3%	4.8%	5.9%	15.4%	0.5%				
				MARV														
Sep-11	WINfab 300NP	NP-NW	08-01-46	Mean	114	48	103	71	49	54	318	1.37	0.15	4				
				COV (%)	11.4%		14.6%		16.3%	11.1%	13.8%	23.4%	6.7%	4.0%				
				MARV														

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needleponched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Willacoochee Industries Fabrics

Contact Info: Mr. Larry Booth

PO Box 599

Willacoochee, GA 31650

Phone:(912) 534-5757

Fax:

Email: larrylbooth@windstream.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2			
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355			
					MD		XD		Strength (lbs)		MD	XD	Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD							MD	XD
Sep-11	WINfab 400NP	NP-NW	08-01-47	Mean	146	49	122	71	53	59	346	1.16	0.14	4.6				
				COV (%)	12.3%		14.8%		13.2%	10.2%	15.6%	25.9%	0.0%	3.3%				
				MARV														
Sep-11	WINfab 1000N	NP-NW	08-01-48	Mean	315	66	266	90	115	139	728	0.84	0.13	9.9				
				COV (%)	7.6%		8.6%		11.3%	11.5%	6.6%	16.7%	7.7%	4.8%				
				MARV														
Sep-11	WINfab 1200N	NP-NW	08-01-49	Mean	340	73	327	92	151	134	875	1.03	0.13	11.3				
				COV (%)	9.1%		4.0%		10.6%	6.0%	4.9%	4.9%	15.4%	4.0%				
				MARV														
Sep-11	WINfab 1600N	NP-NW	08-01-50	Mean	547	76	546	99	216	265	1356	0.61	0.12	16.9				
				COV (%)	6.8%		11.4%		11.6%	4.9%	3.7%	13.1%	0.0%	3.9%				
				MARV														
Sep-11	2x2HF	C-W	08-04-14	Mean	433	25	378	19	205	146	1422	0.61	0.39	7.82				
				COV (%)	8.8%		3.2%		7.8%	5.5%	4.4%	11.5%	5.1%	0.8%				
				MARV														
Sep-11	4x4HF	C-W	08-04-15	Mean	469	19	402	16	411	391	834	0.79	0.6	13.6				
				COV (%)	10.0%		11.7%		32.4%	9.7%	16.4%	8.9%	3.3%	0.7%				
				MARV														
Sep-11	4x4	SF-W	08-04-16	Mean	705	32	575	22	373	249	2055	0.3	0.25	14.4				
				COV (%)	5.2%		3.7%		7.2%	8.4%	4.5%	6.7%	8.0%	0.0%				
				MARV														
Sep-11	4x6	SF-W	08-04-17	Mean	617	25	582	17	349	707	1062	0.34	0.34	16.3				
				COV (%)	5.0%		8.1%		13.2%	29.4%	21.9%	14.7%	11.8%	1.0%				
				MARV														
Nov-11	2199	MF-W	08-09-02	Mean	435	42	289	24	157	83	799	1.11	0.21	6.8				
				COV (%)	7.1%		3.8%		15.3%	6.0%	4.0%	4.5%	0.0%	1.0%				
				MARV														
Nov-11	2198	MF-W	08-09-03	Mean	374	43	329	27	177	128	718	2.35	0.43	6.7				
				COV (%)	3.2%		5.5%		7.3%	6.3%	18.8%	2.6%	4.7%	2.1%				
				MARV														

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needleponched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

Manufacturer: Willacoochee Industries Fabrics

Contact Info: Mr. Larry Booth

PO Box 599

Willacoochee, GA 31650

Phone:(912) 534-5757

Fax:

Email: larrylbooth@windstream.net

Notes: (1) MARV's based on submission information. (2): Manufacturer's UV Results are Target values and are not MARV's.

Drop Date	Style	Structure	NTPEP No. GTX-	Statistic	Grab				Trapezoidal Tear		50 mm Puncture	Permittivity	Opening Size	Mass/Area	UV Stability; Note: 2	
					ASTM D4632				ASTM D4533		ASTM D6241	ASTM D4491	ASTM D4751	ASTM D5261	ASTM D4355	
					MD		XD		Strength (lbs)		Strength (lbs)	1/sec.	mm	oz/yd ²	Strength Retained after 500 hrs (%)	
					Strength (lbs)	Strain (%)	Strength (lbs)	Strain (%)	MD	XD					MD	XD
Sep-12	WINfab 350N	NP-NW	09-07-43	Mean	95	60	111	86	55	70	321	2.14	0.18	3.6	Not Tested	Not Tested
				COV (%)	14.7%	NA	10.8%	NA	9.6%	13.7%	14.4%	20.3%	11.6%	19.4%		
				MARV	90	NA	90	NA	40	40	300	2.2	0.30	3.5	70	70
Sep-12	WINfab 400N	NP-NW	09-07-44	Mean	129	122	124	55	84	60	334	2.08	0.22	4.2	Not Tested	Not Tested
				COV (%)	15.4%	NA	13.8%	NA	16.4%	15.3%	17.7%	14.9%	13.4%	5.9%		
				MARV	100	NA	100	NA	50	50	325	2.0	0.212	4.0	70	70
Sep-12	WINfab 450N	NP-NW	09-07-45	Mean	135	58	123	78	58	65	406	1.72	0.15	4.4	Not Tested	Not Tested
				COV (%)	9.6%	NA	7.0%	NA	25.3%	12.1%	10.6%	10.9%	1.8%	8.2%		
				MARV	120	NA	120	NA	50	50	350	1.8	0.212	4.2	70	70
Sep-12	WINfab 600N	NP-NW	09-07-46	Mean	196	69	195	80	98	96	511	1.83	0.15	6.0	Not Tested	Not Tested
				COV (%)	16.0%	NA	9.6%	NA	13.3%	9.2%	6.6%	19.5%	0.3%	9.0%		
				MARV	160	NA	160	NA	65	65	450	1.6	0.212	6.0		
Sep-12	WINfab 700N	NP-NW	09-07-47	Mean	224	76	232	92	121	141	638	1.31	0.13	7.3	Not Tested	Not Tested
				COV (%)	6.2%	NA	8.1%	NA	21.4%	10.6%	6.6%	4.7%	2.8%	8.7%		
				MARV	180	NA	180	NA	75	75	525	1.5	0.212	7.0	70	70
Sep-12	WINfab 800N	NP-NW	09-07-48	Mean	259	76	237	89	122	146	747	1.02	0.11	7.7	Not Tested	Not Tested
				COV (%)	10.4%	NA	7.8%	NA	7.3%	20.3%	5.2%	7.7%	8.4%	7.3%		
				MARV	205	NA	205	NA	85	85	650	1.4	0.180	8.0	70	70
Jan-13	WinFab 2119	C-W	09-10-07	Mean	500	42	506	19	222	184	1642	0.16	0.17	9.4	Not Tested	Not Tested
				COV (%)	6.7%	NA	3.3%	NA	9.1%	11.1%	4.7%	43.4%	5.8%	0.3%	NA	NA
				MARV	350	NA	250	NA	100	100	NA	0.28	0.21	NA	90	90
Jan-13	2098	MF-W	09-10-08	Mean	351	38	208	24	199	83	759	3.17	0.42	5.6	Not Tested	Not Tested
				COV (%)	5.2%	NA	4.3%	NA	9.8%	8.3%	2.6%	3.1%	0.5%	0.5%	NA	NA
				MARV	350	NA	200	NA	65	65	NA	0.50	0.43	NA	80	80
Jan-13	1216	C-W	09-10-09	Mean	173	19	118	20	79	72	564	1.75	0.46	3.5	Pending	Pending
				COV (%)	5.2%	NA	9.1%	NA	8.6%	6.4%	4.1%	7.4%	8.8%	0.9%	NA	NA
				MARV	150	NA	110	NA	60	60	NA	1.00	0.60	NA	80	80

Legend: SF = Slit film; MF = Monofilament; C = Combination; HB = Heatbonded; NP = Needleponched; W = Woven; NW = Nonwoven; MD = Machine Direction; XD = Cross Machine Direction; COV = Coefficient of Variance; MARV = Minimum Average Roll Value

National Transportation Product Evaluation Program (NTPEP)

Chair: Christine Reed, Illinois

Vice Chair: Thomas E. Baker, Washington

AASHTO Staff: Greta Smith, Katheryn Malusky, Evan Rothblatt and Dan Stegmaier

NTPEP Committee

Member	Department	Member/Delegate	Phone Number	Email Address	Voting Member
Alabama					
		Michelle Owens	(334) 353-6940	owensm@dot.state.al.us	<input checked="" type="checkbox"/> Voting Member
Alaska					
		Michael San Angelo	(907) 269-6234	michael.sanangelo@alaska.gov	<input checked="" type="checkbox"/> Voting Member
Arizona					
		Paul Sullivan		psullivan@azdot.gov	<input checked="" type="checkbox"/> Voting Member
Arkansas					
		Mark Bradley	(501) 569-2380	mark.bradley@arkansashighways.com	<input type="checkbox"/> Voting Member
		Michael Benson	(501) 569-2185	michael.benson@arkansashighways.com	<input checked="" type="checkbox"/> Voting Member
		Tony Sullivan	(501) 569-2661	tony.sullivan@arkansashighways.com	<input type="checkbox"/> Voting Member
California					
		L. Janie Spencer		New_Products@dot.ca.gov	<input type="checkbox"/> Voting Member
		Lawrence Orcutt	(916) 654-8877	larry_orcutt@dot.ca.gov	<input checked="" type="checkbox"/> Voting Member
Colorado					
		David Kotzer	(303) 398-6566	david.kotzer@dot.state.co.us	<input checked="" type="checkbox"/> Voting Member
		Jim Zufall		jim.zufall@dot.state.co.us	<input type="checkbox"/> Voting Member
		K.C. Matthews	(303) 757-9543	K.C.Matthews@dot.state.co.us	<input type="checkbox"/> Voting Member
Connecticut					
		Andrew J. Mroczkowski	(860) 258-0304	andrew.mroczkowski@ct.gov	<input type="checkbox"/> Voting Member
		James M. Sime, P.E.	(860) 258-0309	james.sime@ct.gov	<input checked="" type="checkbox"/> Voting Member
Delaware					
		James T. Pappas III, P.E.	(302) 760-2400	jpappas@mail.dot.state.de.us	<input checked="" type="checkbox"/> Voting Member
District of Columbia					
		Wasi U. Khan	(202) 671-2316	wasi.khan@dc.gov	<input checked="" type="checkbox"/> Voting Member
		William P. Carr	(202) 671-1371	williamp.carr@dc.gov	<input type="checkbox"/> Voting Member
Florida					
		Karen Byram	(850) 414-4353	karen.byram@dot.state.fl.us	<input checked="" type="checkbox"/> Voting Member
		Paul Vinik	(352) 955-6649	Paul.Vinik@dot.state.fl.us	<input type="checkbox"/> Voting Member

(updates found at www.ntpep.org)

NTPEP Committee

Member Department	Member/Delegate	Phone Number	Email Address	Voting Member
Georgia				
	Brad Young	(404) 363-7560	byoung@dot.ga.gov	<input type="checkbox"/> Voting Member
	Don Wishon	(404) 363-7632	dwishon@dot.ga.gov	<input type="checkbox"/> Voting Member
	Richard Douds	(404) 362-2545	Rdouds@dot.ga.gov	<input checked="" type="checkbox"/> Voting Member
Hawaii				
	JoAnne Nakamura		joanne.nakamura@hawaii.gov	<input checked="" type="checkbox"/> Voting Member
Idaho				
	Jeff Miles		Jeff.Miles@itd.idaho.gov	<input type="checkbox"/> Voting Member
	Mike Santi		mike.santi@itd.idaho.gov	<input checked="" type="checkbox"/> Voting Member
Illinois				
	David Lippert		david.lippert@illinois.gov	<input checked="" type="checkbox"/> Voting Member
	Matt Mueller		matthew.mueller@illinois.gov	<input type="checkbox"/> Voting Member
Indiana				
	Kenny Anderson	(317) 610-7251	kbanderson@indot.in.gov	<input type="checkbox"/> Voting Member
	Ronald P. Walker	(317) 610-7251	rwalker@indot.in.gov	<input checked="" type="checkbox"/> Voting Member
Iowa				
	Joseph Putherickal	(515) 239-1259	Joseph.putherickal@dot.iowa.gov	<input checked="" type="checkbox"/> Voting Member
	Kurtis Younkin	(515) 239-1184	kurtis.younkin@dot.iowa.gov	<input type="checkbox"/> Voting Member
Kansas				
	David Meggers, PE	(785) 291-3845	dmeggers@ksdot.org	<input type="checkbox"/> Voting Member
	Stacey Lowe	(785) 296-3899	curt@ksdot.org	<input checked="" type="checkbox"/> Voting Member
Kentucky				
	Derrick Castle	(502) 564-3160	derrick.castle@ky.gov	<input checked="" type="checkbox"/> Voting Member
	Ross Mills	(502) 564-3160	ross.mills@ky.gov	<input type="checkbox"/> Voting Member
	Trevor Booker		trevor.booker@ky.gov	<input type="checkbox"/> Voting Member
Louisiana				
	Jason Davis	(225) 248-4131	jason.davis@la.gov	<input type="checkbox"/> Voting Member
	Luanna Cambass	(225) 248-4131	Luanna.Cambas@la.gov	<input checked="" type="checkbox"/> Voting Member
Maine				
	Doug Gayne	(207) 624-3268	doug.gayne@maine.gov	<input checked="" type="checkbox"/> Voting Member
Maryland				
	Dan Sajedi	(443) 572-5162	dsajedi@sha.state.md.us	<input checked="" type="checkbox"/> Voting Member
	Russell A. Yurek	(410) 582-5505	ryurek@sha.state.md.us	<input type="checkbox"/> Voting Member
Massachusetts				
	Clement Fung	(617) 951-1372	Clement.Fung@MHD.state.ma.us	<input type="checkbox"/> Voting Member
	John Grieco	(617) 951-0596	John.Grieco@state.ma.us	<input checked="" type="checkbox"/> Voting Member

(updates found at www.ntpep.org)

NTPEP Committee

Member Department	Member/Delegate	Phone Number	Email Address	Voting Member
Michigan				
	John Staton, P.E.	(517) 322-5701	statonj@michigan.gov	<input checked="" type="checkbox"/> Voting Member
Minnesota				
	David Iverson	(651) 366-5550	david.iverson@state.mn.us	<input type="checkbox"/> Voting Member
	James McGraw	(651) 366-5548	jim.mcgraw@state.mn.us	<input checked="" type="checkbox"/> Voting Member
Mississippi				
	Alan Kegley	(601) 359-1666	akegley@mdot.state.ms.us	<input type="checkbox"/> Voting Member
	Celina Sumrall	(601) 359-7001	csumrall@mdot.state.ms.us	<input checked="" type="checkbox"/> Voting Member
	James S. Sullivan	(601) 359-1454	jssullivan@mdot.state.ms.us	<input type="checkbox"/> Voting Member
Missouri				
	Julie Lamberson	(573) 751-2847	julie.lamberson@modot.mo.gov	<input type="checkbox"/> Voting Member
	Todd Bennett	(573) 751-1045	todd.bennett@modot.mo.gov	<input checked="" type="checkbox"/> Voting Member
Montana				
	Anson Moffett, P.E.	(406) 444-5407	amoffett@mt.gov	<input type="checkbox"/> Voting Member
	Craig Abernathy	(406) 444-6269	cabernathy@state.mt.us	<input type="checkbox"/> Voting Member
	Ross Metcalfe, P.E.	(406) 444-9201	rmetcalfe@mt.gov	<input checked="" type="checkbox"/> Voting Member
Nebraska				
	Mostafa Jamshidi	(402) 479-4750	Moe.Jamshidi@nebraska.gov	<input checked="" type="checkbox"/> Voting Member
Nevada				
	Roma Clewell	(775) 888-7894	RClewell@dot.state.nv.us	<input type="checkbox"/> Voting Member
New Hampshire				
	Alan D. Rawson	(603) 271-3151	arawson@dot.state.nh.us	<input type="checkbox"/> Voting Member
	William Real	(603) 271-3151	wreal@dot.state.nh.us	<input checked="" type="checkbox"/> Voting Member
New Jersey				
	Eileen Sheehy		eileen.sheehy@dot.state.nj.us	<input checked="" type="checkbox"/> Voting Member
	Richard Jaffe	(609) 530-5463	richard.jaffe@dot.state.nj.us	<input type="checkbox"/> Voting Member
New Mexico				
	Ernest D. Archuleta	(505) 827-5525	ernest.archuleta@nmshtd.state.nm.us	<input checked="" type="checkbox"/> Voting Member
New York				
	Jim Curtis	(518) 457-4735	Jcurtis@dot.state.ny.us	<input checked="" type="checkbox"/> Voting Member
	Michael Stelzer	(518) 457-4595	mstelzer@dot.state.ny.us	<input type="checkbox"/> Voting Member
	Patrick Galarza	(518) 457-4599	pgalarza@dot.state.ny.us	<input type="checkbox"/> Voting Member
North Carolina				
	Chris Peoples	(919) 733-3532	cpeoples@ncdot.gov	<input checked="" type="checkbox"/> Voting Member
	Jack E. Cowser	(919) 733-7088	jcowsert@ncdot.gov	<input type="checkbox"/> Voting Member
	Randy Pace		rpace@ncdot.gov	<input type="checkbox"/> Voting Member

(updates found at www.ntpep.org)

NTPEP Committee

Member Department	Member/Delegate	Phone Number	Email Address	Voting Member
North Dakota				
	Ron Horner	(701) 328-6904	rhorner@nd.us	<input checked="" type="checkbox"/> Voting Member
	Scott Wutzke		swwutzke@nd.gov	<input type="checkbox"/> Voting Member
Ohio				
	Brad Young	(614) 351-2882	brad.young2@dot.state.oh.us	<input checked="" type="checkbox"/> Voting Member
	Lloyd M. Welker Jr.	(614) 275-1351	lloyd.welker@dot.state.oh.us	<input type="checkbox"/> Voting Member
Oklahoma				
	Kenny R. Seward	(405) 522-4999	kseward@odot.org	<input checked="" type="checkbox"/> Voting Member
	Reynolds H. Toney	(405) 521-2677	rtoney@odot.org	<input type="checkbox"/> Voting Member
Oregon				
	Ivan Silbernagel, PE	(503) 986-6213	Ivan.p.silbernagel@odot.state.or.us	<input type="checkbox"/> Voting Member
	Mike Dunning	(503) 986-3059	mike.d.dunning@odot.state.or.us	<input checked="" type="checkbox"/> Voting Member
Pennsylvania				
	David H. Kuniega	(717) 787-3966	dkuniega@state.pa.us	<input checked="" type="checkbox"/> Voting Member
	Tim Ramirez	(717) 783-6714	tramirez@state.pa.us	<input type="checkbox"/> Voting Member
Puerto Rico				
	Orlando Diaz-Quirindong	(787) 729-1592	oquirindongo@act.dtop.gov.pr	<input checked="" type="checkbox"/> Voting Member
Rhode Island				
	Colin A. Franco, P.E.	(401) 222-3030	cfranco@dot.ri.gov	<input checked="" type="checkbox"/> Voting Member
	Mark F. Felag, P.E.	(401) 222-2524	mfelag@dot.ri.gov	<input type="checkbox"/> Voting Member
South Carolina				
	Merrill Zwanka, P.E.	(803) 737-6681	ZwankaME@scdot.org	<input checked="" type="checkbox"/> Voting Member
	Terry Rawls	(803) 737-1498	rawlstl@scdot.org	<input type="checkbox"/> Voting Member
South Dakota				
	David L. Huft	(605) 773-3292	dave.huft@state.sd.us	<input type="checkbox"/> Voting Member
	Jason Humphrey	(605) 773-3704	jason.humphrey@state.sd.us	<input type="checkbox"/> Voting Member
	Joe J. Feller	(605) 773-3401	joe.feller@state.sd.us	<input checked="" type="checkbox"/> Voting Member
Tennessee				
	Danny Lane	(615) 350-4175	danny.lane@tn.gov	<input checked="" type="checkbox"/> Voting Member
	Heather Hall	(615) 350-4150	heather.purdy.hall@tn.gov	<input type="checkbox"/> Voting Member
Texas				
	Robert Sarcinella	(512) 506-5933	RSARCIN@dot.state.tx.us	<input checked="" type="checkbox"/> Voting Member
	Scott Koczman	(512) 416-2073	skoczman@dot.state.tx.us	<input type="checkbox"/> Voting Member
USDOT - FHWA				
	Michael Rafalowski	(202) 366-1571	michael.rafalowski@dot.gov	<input type="checkbox"/> Voting Member

(updates found at www.ntpep.org)

NTPEP Committee

Member Department	Member/Delegate	Phone Number	Email Address	Voting Member
Utah				
	Ahmad Jaber		ajaber@utah.gov	<input type="checkbox"/> Voting Member
	Ken Berg, P.E.	(801) 965-4321	kenberg@utah.gov	<input type="checkbox"/> Voting Member
	Michael Fazio		mfazio@utah.gov	<input checked="" type="checkbox"/> Voting Member
Vermont				
	William Ahearn	(802) 828-2561	bill.ahearn@state.vt.us	<input checked="" type="checkbox"/> Voting Member
Virginia				
	C. Wayne Fleming		cw.fleming@viriniadot.org	<input type="checkbox"/> Voting Member
	James R. Swisher	(804) 328-3121	james.swisher@viriniadot.org	<input checked="" type="checkbox"/> Voting Member
	William R. Bailey III	(804) 328-3106	bill.bailey@viriniadot.org	<input type="checkbox"/> Voting Member
Washington				
	Thomas Baker	(360) 709-5401	bakert@wsdot.wa.gov	<input checked="" type="checkbox"/> Voting Member
	Tony Allen	(360) 709-5450	allent@wsdot.wa.gov	<input type="checkbox"/> Voting Member
West Virginia				
	Aaron Gillispie		aaron.c.gillispie@wv.gov	<input checked="" type="checkbox"/> Voting Member
	Bruce E. Kenney III, P.E.	(304) 558-3044	Bruce.E.Kenney@wv.gov	<input type="checkbox"/> Voting Member
	Larry Barker	(304) 558-3160	Larry.R.Barker@wv.gov	<input type="checkbox"/> Voting Member
Wisconsin				
	Peter J. Kemp	(608) 246-7953	peter.kemp@dot.wi.gov	<input checked="" type="checkbox"/> Voting Member
Wyoming				
	Louis Maillet	(307) 777-4075	louis.maillet@dot.state.wy.us	<input checked="" type="checkbox"/> Voting Member

(updates found at www.ntpep.org)

“The National Transportation Product Evaluation Program (NTPEP) was established by the American Association of State Highway and Transportation Officials (AASHTO) in early 1994. The program pools the professional and physical resources of the AASHTO member departments in order to test materials, products and devices of common interest. The primary goals of the program are to provide cost-effective evaluations for the states by eliminating duplication of routine testing by the states; and to reduce duplication of effort by the manufacturers who produce and market commonly used proprietary, engineered products.” 🌀 NTPEP 🌀

-- Rick Smutzer, former NTPEP Chairman (Chief Engineer, Indiana DOT)

To Order Additional Copies
of this NTPEP Report:

call 1.202.624.5800
online www.NTPEP.ORG

ITEM: NTPEP Report 8001.42

