

# Pavement Design for Local Roads and Streets

FINAL REPORT

November, 2020

Submitted by:

David P. Orr, PE, Ph.D.  
Director / Senior Engineer

Nick Kuzmik  
Special Projects Coordinator

Geoffrey R. Scott, PE  
Technical Assistance Engineer

Cornell Local Roads Program  
Cornell University  
416 Riley-Robb Hall  
Ithaca, NY 14853-5701

External Project Managers  
Dennis Davis, Vice President, Oneida County  
Andy Avery, P.E., Chemung County  
New York State County Highway Superintendents Association  
136 Everett Road  
Albany, NY 12205

In cooperation with

Rutgers, The State University of New Jersey  
And  
U.S. Department of Transportation  
Federal Highway Administration

## **Disclaimer Statement**

The contents of this report reflect the views of the authors, who are responsible for the facts and the accuracy of the information presented herein. This document is disseminated under the sponsorship of the Department of Transportation, University Transportation Centers Program, in the interest of information exchange. The U.S. Government assumes no liability for the contents or use thereof.

The Center for Advanced Infrastructure and Transportation (CAIT) is a Regional UTC Consortium led by Rutgers, The State University. Members of the consortium are Atlantic Cape Community College, Columbia University, Cornell University, New Jersey Institute of Technology, Polytechnic University of Puerto Rico, Princeton University, Rowan University, SUNY - Farmingdale State College, and SUNY - University at Buffalo. The Center is funded by the U.S. Department of Transportation.

TECHNICAL REPORT STANDARD TITLE PAGE

1. Report No. <b>CAIT-UTC-REG11</b>	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle <b>Pavement Design for Local Roads and Streets</b>		5. Report Date <b>November, 2020</b>	
		6. Performing Organization Code <b>CAIT/Cornell University</b>	
7. Author(s) David P. Orr, PE, Ph.D., <a href="http://orcid.org/0000-0001-8797-3208">http://orcid.org/0000-0001-8797-3208</a>		8. Performing Organization Report No. <b>CAIT-UTC-REG11</b>	
9. Performing Organization Name and Address <b>Cornell University 416 Riley-Robb Hall, Ithaca, NY 14853</b>		10. Work Unit No.	
		11. Contract or Grant No. <b>69A3551847102</b>	
12. Sponsoring Agency Name and Address <b>Center for Advanced Infrastructure and Transportation Rutgers, The State University of New Jersey 100 Brett Road, Piscataway, NJ 08854</b>		13. Type of Report and Period Covered <b>Final Report 10/1/2018 – 12/31/2019</b>	
		14. Sponsoring Agency Code	
15. Supplementary Notes U.S. Department of Transportation/OST-R 1200 New Jersey Avenue, SE Washington, DC 20590-0001			
16. Abstract Low-volume roads (LVRs) make up more than half the centerline mileage in the United States, most of which are not designed. The Cornell University Local Roads Program worked with local highway agencies New York State to develop a mechanistic-empirical pavement design tool that overcomes the limitations of expertise and time of most LVR highway officials but takes advantage of the knowledge of their own LVRs. The tool developed, RoadPE: LHI, uses two common pavement fatigue criteria, surface tensile strain and subgrade vertical strain, with simplified inputs, and built-in trend analysis to determine the thickness of the asphalt layers for overlaid, mill and filled, rehabilitated, and reconstructed LVRs.			
17. Key Words Low-volume, pavement design, seasonality, farm equipment, mechanistic-empirical		18. Distribution Statement	
19. Security Classification (of this report) <b>Unclassified</b>	20. Security Classification (of this page) <b>Unclassified</b>	21. No. of Pages <b>21</b>	22. Price

# Pavement Design for Local Roads and Streets

David P. Orr, P.E., Ph.D.  
(Corresponding Author)  
Director / Senior Engineer  
Cornell University Local Roads Program  
416 Riley-Robb Hall  
Ithaca, NY 14853  
Tel: 607-255-8033  
Fax: 607-255-4080  
Email: [david.orr@cornell.edu](mailto:david.orr@cornell.edu)  
ORCID Number: 0000-0001-8797-3208

Geoffrey R. Scott, P.E.  
Technical Assistance Engineer  
Cornell University Local Roads Program  
416 Riley-Robb Hall  
Ithaca, NY 14853  
Tel: 607-255-8033  
Fax: 607-255-4080  
Email: [grs78@cornell.edu](mailto:grs78@cornell.edu)

Nick Kuzmik  
Program Support Specialist  
Cornell University Local Roads Program  
416 Riley-Robb Hall  
Ithaca, NY 14853  
Tel: 607-255-8033  
Fax: 607-255-4080  
Email: [nwk23@cornell.edu](mailto:nwk23@cornell.edu)

Figure 1. RoadPE:LHI - Existing Pavement Inputs.....	6
Figure 2. Average Expected Frost Depth Under LVR (ft).....	11
Figure 3. Trend Line for Asphalt Thickness.....	13
Figure 4. Results of Overlay Analysis.....	14

Table 1. LVR Design over weak subgrade, NYSDOT CPDM .....	3
Table 2. Intermediate Light and Single-trailer Truck Route Truck Class Distribution (%) and Trucks per day at 2,000 vpd .....	9
Table 3. Example Site Inputs in Road PE: LHI.....	10

## **Abstract**

Low-volume roads (LVRs) make up more than half the centerline mileage in the United States, most of which are not designed. The Cornell University Local Roads Program worked with local highway agencies New York State to develop a mechanistic-empirical pavement design tool that overcomes the limitations of expertise and time of most LVR highway officials but takes advantage of the knowledge of their own LVRs. The tool developed, *RoadPE: LHI*, uses two common pavement fatigue criteria, surface tensile strain and subgrade vertical strain, with simplified inputs, and built-in trend analysis to determine the thickness of the asphalt layers for overlaid, mill and filled, rehabilitated, and reconstructed LVRs.

## **Acknowledgement**

The authors would like to acknowledge to financial support of the USDOT Region 1 University Transportation Center.

## **Description of the Problem**

Local roads are a majority of centerline mileage, but pavement design is not usually done. (1) Instead, most local agencies just use a default design for all of the roads in their system. In some cases, the pavement may have the correct thickness, but in many other cases, the pavement is not thick enough for the site and traffic conditions or the pavement is thicker than necessary. An excess thickness is preferred since it will last longer, but at an average of \$100,000 per inch per mile for a new hot mix asphalt pavement, the excess costs can become problematic. If the pavement is too thin, then the road fails prematurely and there are excess costs due to rough roads that are borne by the traveling public.

Small highway agencies are managed by non-engineers who have good knowledge of their road system. They need a simple tool that gives a reasonable design that accounts for the traffic conditions in their municipality.

## **Pavement Design Methods**

When designing any highway, the first question is what is a road pavement? (2) A road spreads out the forces of passing vehicles such that the subgrade does not fail prematurely. (1) The majority of the current design tools available use empirical methodologies or require overly complicated data inputs. (3-6) There are four general pavement design methods: experience, catalog, empirical, and mechanistic-empirical.

## **Experience**

Experience-based methods are still very commonly used, especially by smaller agencies. They use only a few different designs for the pavements in their system. For example, an agency might have one thickness for residential streets, one for commercial streets, and another for other roads in the system.

If the highway manager has enough experience, this method can be successful as it slowly evolves to the thicknesses that work in a particular community. However, it typically overdesigns the thickness to be sure it will not fail or is too thin because the manager paves as much as they can afford with the limited funds available in the budget. An experience-based design cannot handle large variations in traffic volume and there is generally no rational basis for the thickness.

## Catalog

A catalog-based design is usually the result of one of the other methods. The highway manager prepares a table of designs for various conditions and inputs. These may be experience-based, or utilize an engineering tool to develop the table of designs.

The New York State Department of Transportation (NYSDOT) Comprehensive Pavement Design Manual (CPDM) is a catalog-based design that uses the AASHTO '93 Pavement Design Guide as the engineering model determination of the thicknesses. (3; 7) The NYSDOT used the AASHTO '93 guide and generated a series of default values to create a chart of design thicknesses for various subgrade conditions, traffic loading, and surface types. (8)

To use the CPDM, the designer needs to decide if the surface is to be asphalt concrete (HMA) or Portland Cement Concrete (PCC), calculate a 50-year count of Equivalent Single Axle Loads (ESALs) using a simplified formula, and determine the subgrade resilient modulus,  $M_r$ . Then using the proper table for HMA or PCC, the designer can select the thickness of the new pavement.

For example, if a new road has a subgrade modulus of 5,950 psi (41 MPa) and a 50-year traffic count of less than 6 million ESALs, the designer uses the proper figure and table and would select final thicknesses as shown in Table 1.

**Table 1. LVR Design over weak subgrade, NYSDOT CPDM**

Layer	Thickness	Notes
Hot Mix Asphalt Concrete (HMA)	165 mm (6.5 inches)	Table 4-5 in CPDM
Asphalt treated permeable base	100 mm (4.0 inches)	Only shown in figure
Granular subbase	300 mm (12 inches)	Only shown in figure

Therefore, the minimum thickness for an LVR is 22.5 inches (565 mm). Such a catalog system can be an effective way to generate an initial design, but it may not be precise enough or have enough variations to deal with real-world site conditions. For most local agencies, such a design is almost impossible to build, with the HMA asphalt layers alone projected to cost over \$650,000 per mile.

## Empirical

As mentioned, the NYSDOT CPDM uses the AASHTO '93 Pavement Design Guide which is an empirical design tool and is still very commonly used for pavement design. For the AASHTO '93 Guide, the equations were derived using the results of the AASHO Road Test in Ottawa, Illinois. (9-11)

Tables and information are available to determine the expected values for the variables including  $M_R$ , the subgrade resilient modulus. The subgrade is the only layer that has a seasonal component in the AASHTO '93 Guide. To determine the seasonality, the designer uses an equation to calculate the relative damage on the subgrade modulus, determines the average relative damage, and from this, the average roadbed resilient modulus.

Chapter 4 of the AASHTO '93 *Pavement Design Guide* discusses Low-Volume Road Design and includes a catalog "when the more detailed design approach is not possible." (7) For the northeastern U.S., the characteristic design is a wet hard-freeze, spring thaw condition.

Using default values for the structural layer coefficients from NYSDOT and assuming a 12-inch

granular base, the HMA thickness can be calculated. The range of HMA thickness for an LVR road ranges from 1.7-6.4 inches in New York State, which is significantly less than the 10.5 inches of asphaltic material for the lowest volume roads in the NYSDOT CPDM.

### **Mechanistic-Empirical**

The last of the pavement design methods is mechanistic-empirical (M-E) design. While some think a fully mechanistic design is possible (12), most realize that the problem is too complex and a combined approach is the most likely to be successful. (13-15)

The concept is to use a mechanistic approach to determine the critical stresses and strains and empirical methods for a fatigue failure model. The mechanistic approach requires the calculation of the stresses and strains due to various traffic loading for the pavement layer structure. While a non-linear approach may be used, for LVR pavements a linear approach is acceptable. (16; 17)

The overall cost and complexity of the AASHTO ME Design is a barrier to its use. While the concepts in the ME Design are valid and useful for higher volume roads, Irwin and Orr recommended removing the LVR section from the new ME-Guide. There are too many details for the occasional use typically done by LVR designers. (18)

### **Why Develop a New Design Method**

While an experience or catalog-based approach may work for many small agencies, when reviewing what local agencies were actually using, the authors found that the variations in traffic and environment were greater than the limited ranges available in the current design tools. A new tool was needed to allow for agencies to account for the conditions and properly account for the seasonality of low-volume pavements. A tool utilizing mechanistic-empirical methods was chosen as it had the most capability. The tool has to balance the accuracy of the design with the accuracy of the actual design.

### **Development Process**

The Cornell University Local Roads Program (Cornell) worked with local agencies to understand their capacity for data collection for the critical factors in pavement thickness design. For those design factors not accounted for by a local agency, defaults needed to be set up.

The research was focused on the development of a simple to use tool that would allow a small, local agency to develop a mechanistic-empirical design for low volume roads and streets. After speaking with the anticipated users of the tool in small towns and counties in New York State and working with them on the development of a frost depth modeling tool, the primary focus for the tool was for pavement overlays and rehabilitation, but new road design was also included.

The final product is a tool in a spreadsheet form that allows an LVR highway manager without an engineering background to determine a reasonable pavement design. The tool also provides information for a professional engineer should they become involved due to site conditions, traffic, or other critical factors.

The project tool allows the end-users to design the thickness of an LVR that will meet their needs using the tools and information they have readily at hand. Where this project stands out is in its use of mechanistic-empirical methods, but in a simple, user-friendly way. The design inputs were selected in consultation with the local highway community. This means the user will not need extensive tests from outside labs. It also means the tool is likely to be less precise than more

sophisticated tools. However, the local agencies involved in reviewing the tool made it clear a simple tool that they could use would be better than a more precise tool which was so complicated or expensive that it did not get used. Flexible Pavements of Ohio (FPO) also showed that simple design tools for LVRs would be more likely to be used. (19) A simple tool with less precision is better than a tool that is not used due to its complexity.

### **Pavement Design Tool Development**

In the previous decades, Cornell had been developing seasonal models of pavement analysis and evaluation. Orr and Irwin showed how a representative year could be used to account for the seasonality of every layer in a pavement design. (20) Duffy, Orr, and Miller updated the frost model used to improve the timing of the thawing period. (21) Orr, Mug, and Duffy used the updated frost model to develop a simple-to-use spreadsheet tool that would allow local agencies to determine when to post their highways for spring load restrictions. (22) It was during this time, during discussions with the local agencies using the frost depth model, that Cornell realized most local agencies would not design a pavement unless the inputs were simple and the outputs were reasonable. Using this strategy, Orr showed how a simple tool could allow local agencies to determine when to post local roads. (23)

A draft spreadsheet-based tool was developed that incorporated the lessons learned from both direct feedback from the local highway community, and the experience with the frost depth tool. During this phase, a set of agencies were selected to provide feedback and testing of the beta version of the tool. Agencies were sent draft copies of the tool and provided feedback on the ease of use and the applicability of the model.

### **Limitations of LVR Design**

As the tool was being finalized, the discussion centered around two issues: would an LVR design tool be used and what is the upper limit of the traffic volume where the tool should be used.

- Would the tool be used?

When sharing the draft tool with local agencies, the answer was yes. Local agencies wanted a simple and easy to use design tool, but it could not require a large amount of new testing. It would need to evaluate existing roads, and calculate the thickness of overlays and mill and fill overlays as they are the most common major work done. If possible, the tool should include rehabilitation of the base. None of the local agencies were worried about replacing the subgrade. In cases where this needed to be done, an engineer is usually involved, and a more sophisticated design could be used.

The other issue was time. The tool needed to be easy to use and not take a lot of time to learn to use or to obtain a pavement design.

- Upper limit on traffic volume?

As most agencies do not know the percentage of trucks, the total number of vehicles per day was a better measure of the upper limit to use with the new design tool. The initial draft of the tool had a limit of 1,000 vehicles per day (vpd), but county agencies needed to account for a little more traffic. Preliminary results showed that the calculations would still be precise enough at a higher level of traffic.

In the summer of 2019, AASHTO released the 2<sup>nd</sup> Edition of the *Guidelines for Geometric Design of Low-Volume Local Roads* (24) with an upper limit of 2,000 vpd. This value fit



into both the need and capability of the new tool and was chosen as the recommended upper limit.

## Final Tool

The tool was built in Microsoft Excel (25) and the primary output from the project is named *RoadPE: LHI*. *RoadPE* is the name of a series of pavement analysis tools developed by Cornell over the past 20 years. The *LHI* stands for Low-volume Highway Inputs as a reminder that these inputs are only valid for low-volume roads. All the primary calculations and data are available for inspection and review by users. The spreadsheet tool is available for download from the New York State LTAP Center. A screen shot of the existing pavement inputs from the tool is shown in Figure 1.

RoadPE: LHI - Low-volume Highway Inputs for Pavement Design					
Location:	Input all known data.				
Route:	Blue cells must be filled out.				
Designer:	Green cells are drop down list to be chosen by the user.				
Date:	Yellow cells are optional inputs.				
Purple cells are defaults that may be changed by the user.					
Orange cells are calculated.					
Existing Pavement					
Layer	Layer type	Thickness			
#		in			
1			Cold Mix Asphalt, Gravel surface, Hot Mix Asphalt		
2			Crushed gravel/stone (clean), Dirty unbound base (wet), Stabilized, Uncrushed gravel (clean)		
3		∞	Clayey subgrade, Gravelly subgrade, Sandy subgrade, Silty subgrade		
Drainage Quality			Good, Fair, Poor		
Age of current pavement (last major work)			years		
Site Inputs					
Seasonal Inputs		Winter	Thaw	Spring	Summer
Length of Season (days)					
Avg. Air Temperature (°F)					
Traffic					
Design Life			year		
Current vehicles / day			vehicles per day		
Growth Rate		1.0%	NYSDOT Default = 1%		
Traffic Type			Standard LVR, Agricultural, Industrial, Residential, Commercial		

Figure 1. RoadPE:LHI - Existing Pavement Inputs

The choice of Excel was done for three reasons. First, while macros may be disabled by some IT departments, most of the local agencies felt this would not be an issue. Secondly, by using Excel, all the calculations are available for anyone to review and provide improvements. The protection on the sheets is only there to keep a user from accidentally deleting a critical calculation. Third, by using a tool many local agencies are already using, the instructions for use could utilize the common forms for use of any spreadsheet tool. If there was a demand in the future, a self-standing version could be developed.

## Low Volume Pavement Design Inputs

Since very few LVRs are new, the first steps are the evaluation of the existing pavement and identifying the critical variables for LVR Design. To make the new tool, *RoadPE: LHI*, work, defaults for the detailed data, which could not be provided by the local highway community, had to be obtained or calculated. The input data needed and obtained by the local agency for an LVR include the pavement structure, traffic, design life, and site conditions. There are many assumptions in using the tool, but these variations were reviewed to reduce the errors to a

reasonable level. The tool is not a replacement for a more sophisticated tool such as the ME-PDG which is needed for higher volume roads.

### **Pavement structure**

Almost every LVR consists of no more than three layers, including the subgrade if the asphalt surface is counted as a single layer. For each of these three layers in the existing pavement, the user needs to input the layer type and the thickness, with the exception for the subgrade which is considered a semi-infinite half-space. Default seasonal moduli and Poisson's ratio value are included for each material type. User inputs include the thickness of the pavement layers as well as the quality of drainage. All the defaults are provided to the user on various pages within the spreadsheet tool. The four seasons in the representative seasonal year are shown below and derived from maps developed by Orr and Irwin (20) and updated by Orr, Mung, and Duffy (22). The development of the seasonal maps is outlined in those two references. Weather data for the previous 20 years was obtained from the Northeast Regional Climate Center (NRCC) and used to generate the seasons for a grid of data provided. The average seasonal lengths and frost depths for each point were then kriged using ArcGIS to produce the maps for the area in and around New York State. Generating a similar map is feasible for any location. NRCC also provided climate prediction data for the next 20 years to determine the effects of climate change. The 20 year average data is slightly conservative with regard to pavement thickness design.

- **Winter** is the period when at least 4 inches of the subgrade is frozen and there is no thaw in any unbound layer. This is not a continuous season. During January thaws, the upper unbound layers may be thawed with a frozen layer below. This condition is considered part of the thaw season.
- **Thaw** occurs whenever there is any thaw in the unbound layers and some lower portion of the pavement is still frozen.
- **Spring** is the period after the pavement has completely thawed until evaporation exceeds precipitation.
- **Summer** is the period after evaporation exceeds precipitation until winter. Due to a lag in the movement of moisture, it is not expected to start until one month after the evaporation exceeds precipitation.

### **Material Type**

Local agencies can choose between hot-mix asphalt concrete (HMA), cold-mix asphalt concrete (Cold mix), or gravel surfaces. The tool works for gravel surfaces but only utilizes the rutting fatigue failure criteria. For the base, they usually know if it is clean or dirty, crushed or uncrushed, and if the layer has been stabilized with asphalt or concrete in the past. The subgrade is not tested and most agencies do not use soil maps. (26; 27) The most an agency is usually able to state about the subgrade is the general classification of gravelly, sandy, silty, or clayey.

A table of default values was developed for these choices of material types using results from the AASHTO ME PDG, default data collected by Irwin, and results from the seasonal in-situ pavement analysis study carried out by Cornell. (24)

### **Thickness**

Thickness is one of the outputs of the design, but it is also necessary to know the thickness of the existing pavement structure. Variation in the surface can be a significant issue so a conservative

approach is recommended. (28) For existing pavements, the thickness can be determined using cores, test pits, or GPR.

While the user is only required to input the subgrade material type, the tool uses the frost depth input to adjust the modulus of the lower subgrade below the active frost zone. While the depth of frost varies from year to year, the effect on the design is limited if the deeper, and typically stiffer, lower subgrade is considered. For a deep fill, the user should use a gravelly subgrade.

### **Drainage**

The local highway official usually knows if the drainage is good, fair, or poor in quality. The default moduli are modified using a simple multiplier from the defaults based upon the material type.

### **Age of Pavement**

The age is not accurately known in many cases, but a general estimate can be obtained by the local highway official.

### **Traffic**

Traffic counts for LVRs are not usually done and while it is recommended, it is not likely to be as detailed as is needed for the AASHTO ME PDG. Instead, estimation methods are typically used.

### **Traffic Volume**

The NYS LTAP Center has a *Quick Answer* on traffic counts which provides three ways to obtain a quick count of the traffic without a traffic counter. (29) This method works since the busiest time of the day sees 15 percent of the traffic in rural areas and 11 percent in urban areas. (30) Combined with local knowledge of traffic it is possible to obtain a good estimate of total volume.

### **Traffic Spectra**

The traffic spectra have a major influence on the life of the pavement. Using information from LTPP (31) and the new AASHTO ME PDG, it is possible to develop default traffic spectra for LVR roads using the groups from the ME PDG and LTPP.

The starting point for the analysis is the Intermediate light and single-trailer truck route from the AASHTO ME PDG. The details for the trucks in that traffic distribution is shown in Table 2. The amount of trucks is typically about 12.5 percent (1/8<sup>th</sup>) of the overall traffic. For an LVR with 2,000 vpd, or 250 trucks per day, this equates to the following breakdown of the number of trucks per day in each class as shown.

LVRs are very unlikely to see the multi-unit trucks except for agricultural equipment. Calculations were run to determine the change in the design using the small percentage of trucks in classes 7 and 10-13. Except for some agricultural equipment scenarios, there was no difference found in the overall design if instead of the breakdown shown in Table 2, the counts for classes 7 and 10-13 were assumed to be class 9.

The loads for the various truck configurations vary in real traffic, but for an LVR, a standard axle load and number of axles per truck were set up using a report on the verification of the LTPP vehicle classification rules from FHWA Research and Technology. Triple axles were not included but might be included in future versions of the tool.

**Table 2. Intermediate Light and Single-trailer Truck Route Truck Class Distribution (%) and Trucks per day at 2,000 vpd**

Group and Description		Truck Class Distribution (%) (FHWA Designations)									
		4	5	6	7	8	9	10	11	12	13
12	Percentage by Class	3.9	40.8	11.7	1.5	12.2	25.0	2.7	0.6	0.3	1.3
	Trucks per day at 2,000 vpd	10	102	29	4	31	63	7	2	<1	3

One of the traffic challenges is the large variation in the percentage of trucks in the traffic flow. Discussing the possible types of traffic, the four types of traffic noted by the local highway community are agricultural, commercial, industrial, and residential.

- Agricultural  
A mix of twice as many trucks as typical with more dual-axle single-unit trucks, but also more single-axle trucks with trailers.
- Commercial  
Almost one-third trucks, with fewer single-axle, single-unit trucks, and more semi-trucks with dual-axle trailers.
- Industrial  
Almost 50 percent of trucks with a large percentage of dual-axle single-unit trucks.
- Residential  
Very small percentage of trucks, more buses for schools, and less dual-wheel semi-trucks with trailers.

Including the Standard LVR traffic distribution, these are the five traffic distributions available in *RoadPE: LHI*.

### **Growth**

Most LVRs experience very little growth in traffic and the NYSDOT default of 1 percent is usually adequate and probably conservative for most LVRs.

### **Wheel Wander**

The AASHTO ME PDG default is also considered adequate. While LVRs are typically narrower which might reduce wheel wander, the lack of traffic lines on most local roads tends to counter this effect. The AASHTO ME PDG default of 10 inches is used in *RoadPE: LHI*.

For each traffic loading, the wheel wander must be accounted for while balancing computing time and accuracy. After several analyses, it was determined that four-wheel offsets would be enough to complete the task. The wheel wander is broken into 7 bins (three on each side of the wheel centerline) with the outer bin assumed to have all the traffic not included in the central bin locations.

### **Design Life**

While NYSDOT is designing for 50-years, most LVRs are designed for a much shorter lifespan, even for a new road. (1) A new road may be designed for a 25-year life, but a 10-year life is more common for an overlay or mill and fill operation. This is a user input value.

## Weather and Site Conditions

When rolling out its frost depth tool, Cornell found many agencies may be able to download or obtain short term data for a given year to use in the daily frost depth model. However, obtaining more than that would be unlikely. Also, many agencies are not aware of the pavement seasons other than spring thaw. Maps showing the various seasonal lengths and associated temperatures using a representative year concept were generated and included with the tool.

Orr showed that there is a need to include seasonality in every layer in a pavement, not just the subgrade as is varied in the AASHTO '93 Guide. (32) This is not a new concept and many others have made this conclusion and it is also part of the new AASHTO ME PDG.

### Site Inputs


As mentioned, *Road PE: LHI* uses a representative year approach. A user needs to select eight seasonal inputs, four seasonal average air temperatures, and the depth of frost as shown in Table 3. The length of the summer season is calculated automatically.

**Table 3. Example Site Inputs in Road PE: LHI**

Seasonal Inputs	Winter	Thaw	Spring	Summer	Depth Frost
Length of Season (days)	23	16	88	238.3	3.2 ft
Avg. Air Temperature (°F)	19	33	46	57	

Figures for the average seasonal lengths and average air temperatures were generated by Orr and Irwin for a typical LVR road and are provided for the user. The frost depth data was updated by Orr, Mung, and Duffy as part of the development of the frost depth tool (Figure 1).

Using these data and maps, it is possible to calculate the effect of changing seasonal lengths in different locations. For instance, a pavement in Rockland County, where the typical spring thaw length is 7 days long, might lead to a total number of allowable load repetitions of 660,000 ESALs. The same pavement with the same initial inputs, but in Albany County where the expected number of days of thaw is 28, would only have an allowable number of load repetitions of 490,000 ESALs. This is a 26.2 percent decrease in lifespan!

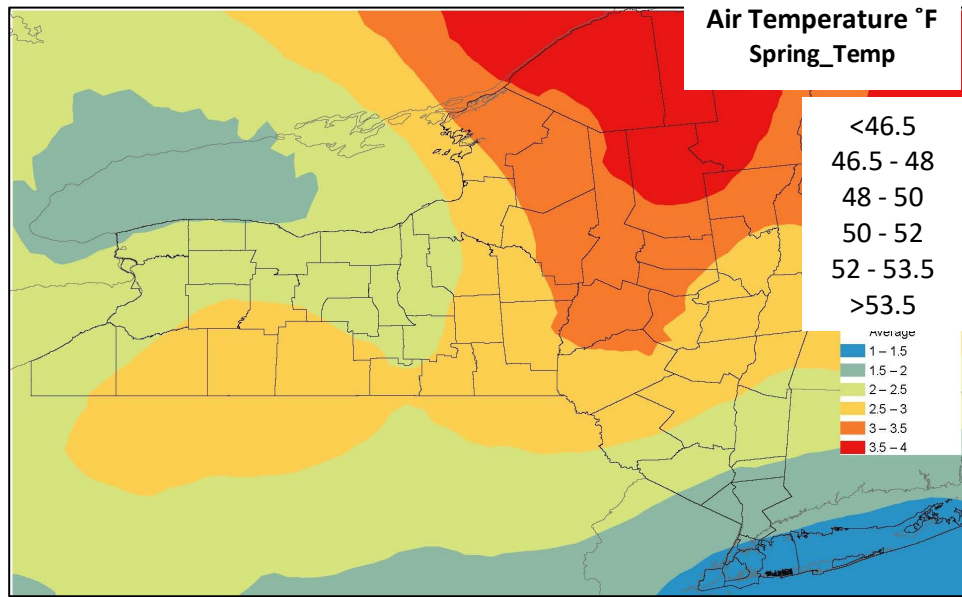

**Figure 2. Average Expected Frost Depth Under LVR (ft)**

## Running an LVR Analysis

Once the design inputs are collected and put into *RoadPE: LHI*, the user is ready to run an analysis of the existing pavement or a possible new design. The tool calculates the critical strains at the bottom of the asphalt layers (and overlay if one exists) and at the top of the subgrade using the inputs from the user to gather critical values about the pavement structure.

## Failure Criteria

While there are numerous fatigue failure modes, the two most commonly used are the tensile strain in the surface which leads to cracking and the vertical strain on the subgrade which leads to rutting. (33) For an LVR, these two criteria were determined to be adequate for a pavement design.

Irwin (33) collected a series of failure curves from various agencies including the Asphalt Institute, Transportation Research Laboratory (TRL) from the UK, Shell Oil, Denmark Technical University (DTU), NAASRA (formerly National Association of Australian State Road Authorities and today Austroads), and Dorman & Metcalf. The average value for the surface equation is very similar to the new ME-PDG.

The average values of Irwin and the new AASHTO Guide are listed below.

$$N_{fsurface}(10^6) = \left( 219.90 \left( \frac{E}{435,000 \text{ psi}} \right)^{-0.85} \frac{1}{\varepsilon_t} \right)^{4.263}$$

$$N_{fsubgrade}(10^6) = \left( 618.60 \frac{1}{\varepsilon_v} \right)^{3.902}$$

Where

$N_f$  = number of cycles to failure (usually in millions of cycles)  
 $E$  = modulus of the surface layer  
 $E'$  = reference modulus for the bound surface layer  
 $\varepsilon_t$  or  $\varepsilon_p$  = critical strain (microstrain)

These average values are used in the final tool.

## Invoking the Forward Calculation Engine

The forward calculation engine is CHEVLAY3, a Windows 10 version of the CHEVLAY2 engine developed by the Chevron Oil Corporation and upgraded to a 16 point quadrature by Irwin to improve accuracy. (34) For dual-wheel loads, supposition is used to determine the critical stresses and strains. The offset data due to wheel wander are determined in a similar fashion.

For each of the 52 calls, the surface and subgrade strains are determined and the allowable number of load repetitions,  $N_f$ , are calculated. The number of expected or actual traffic load repetitions,  $n_f$ , are also calculated and damage factors,  $D$ , are determined. All the  $D$  factors are summed, and a final  $D$  value is determined using Miner's Hypothesis for both the surface and subgrade layers.

$$D_{analysis} = \sum_{i=1, j=1, \dots}^{T, season, \dots} D_{i, j, \dots}$$


## Existing Pavement

Designing a pavement repair requires an initial run to determine the amount of current damage already consumed by the existing pavement. If the  $D_{existing}$  is greater than 1.0, the existing pavement is already failed, and a reconstruction or rehabilitation is needed.

Four types of work are available to the user of *RoadPE*: *LHI*, overlay, mill and fill, rehabilitation, and reconstruction. How these are invoked is listed below, but the tool is primarily focused on the design of the asphalt layer thickness. The user can modify the granular layers, but defaults are provided.

## Calculating the AC Thickness

The asphalt thickness can be determined in three analyses using an idea discovered by Richter *et al.* (28; 35) The relationship between an overlay thickness and the percentage of life used,  $D$ , in a semi-log space is very close to linear. It is slightly curvilinear but is conservative. Figure 2 shows the trend line for an LVR pavement with 78 percent of the life already consumed for the existing pavement. The x-axis shows the total life used assuming various overlay thicknesses.

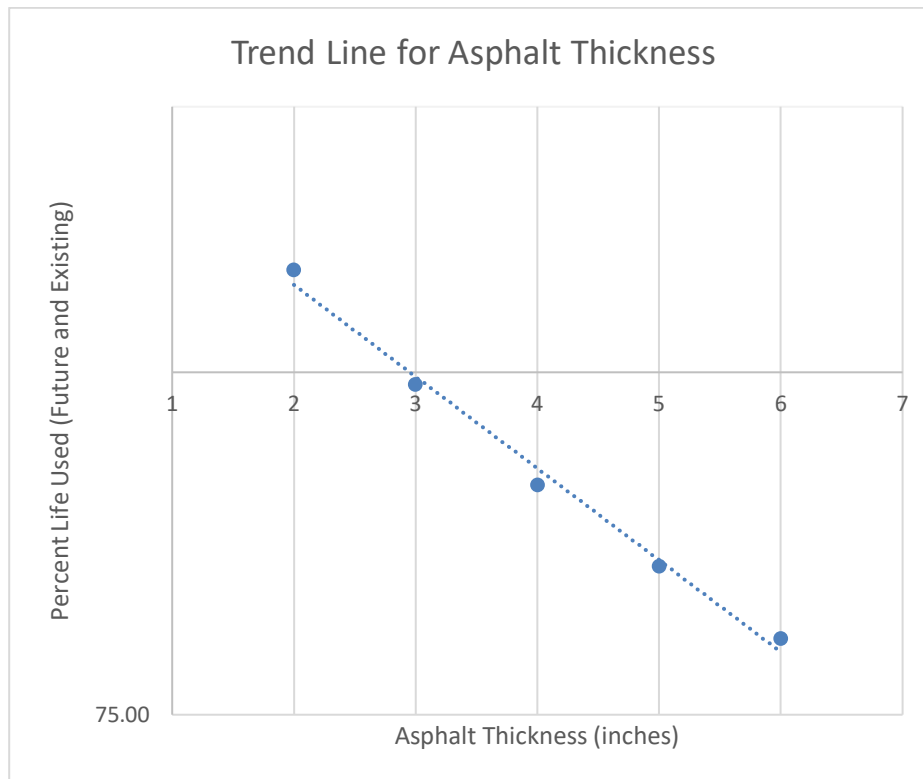

**Figure 3. Trend Line for Asphalt Thickness**

Using a bracketing approach, the tool calculates the expected life consumed for a thin lift of asphalt (2 inches) and a thick lift (6 inches) and calculates the thickness needed to have the total life consumed ( $D$ ) to be less than 1. In this case, the 2-inch lift reduces consumption over the life of the pavement and only another 31 percent is consumed, but this is still too much with a total  $D$  value of 109%. A 6-inch lift consumes only 2 percent and is too conservative with a total  $D$  value of 80%.

Assuming a straight line in a semi-log space, the overlay thickness is determined to be 3.08 inches. Since pavements are not built to that level of tolerance, the tool rounds up the thickness to the closest  $\frac{1}{2}$  inch; 3.5 inches of asphalt concrete is needed. The tool does one final check to confirm the 3.5-inch lift is adequate. This entire operation of three trials takes only about a minute on a moderately powerful computer.

The minimum thickness of the asphalt layer is 1.5 inches since anything thinner is more of a membrane than something providing structural strength. Three locations in the pavement need to be reviewed in the final check, the existing bottom of the asphalt layers, the bottom of any overlay layers, and the top of the subgrade.

### **Type of Work**

Four types of work are included based upon conversations with the local highway community.

- Overlay  
An overlay assumes a new lift of asphalt over the existing asphalt surface.
- Mill & Fill



In this case some or all the asphalt surface is removed.

- Rehab

In this case, the asphalt is either removed or blended into the existing base. The default thickness is 8-inches of rehabbed material which will be assumed to have the same quality as a high-quality stone base. The user may input a different thickness for the rehabilitation layer.

- Reconstruct

Assumes existing pavement will be removed to the subgrade and the subgrade will be treated and repaired such that the existing life consumed can be ignored.

### Case Study

After inputting all the existing pavement information, the user first checks the capacity of the existing pavement. If there is existing capacity, the user selects the type and work and the tool calculates the effects of the 2 and 6 inch final asphalt surface and then uses the bracketing approach discussed above to determine the final calculated thickness. The tool does a final check of the thickness rounded up to the closest ½ inch. Figure 4 shows the results of the overlay analysis. The calculated thickness was 5.22 inches, but after rounding the thickness is 5.5 inches.

Program will supply design thickness of the new asphalt concrete layer.					
	Trial	1	2	3	4
		Existing	2"	6"	Calculated
Layer	Layer type	Thickness	Thickness	Thickness	Thickness
#		in	in	in	in
	New Asphalt Layer		2.0	6.0	<b>5.5</b>
1	Cold Mix Asphalt	3.0	3.0	3.0	3.0
2	Uncrushed gravel base (clean)	12.0	12.0	12.0	12.0
3	Silty soil subgrade	23.4	23.4	23.4	23.4
	Life (years)	13	25	25	25
	Drainage	Poor	Fair	Fair	Fair
		3	2	2	2
Lifespan consumed	AC Overlay		0%	1%	1%
	AC Existing	91%	39%	3%	4%
	Subgrade	61%	7%	1%	1%
	Life Used (percentage) (Existing + Future)		130%	94%	95%
	Trend		0.11	-0.03	
					5.22
	Life (Calculated in years)	1			26

**Figure 4. Results of Overlay Analysis**

### Conclusions

Low-volume roads (LVRs) make up more than half the centerline mileage in the United States, but most are not designed. Experience, history, and what the elected board will fund are by far the most common design methods for LVRs. Some agencies have catalogs or standard designs, but these tend to be over or under-designed as they do not consider the actual traffic and site conditions. There is a clear need for a design tool for LVRs.

The other major impediments to doing an actual design on an LVR are expertise and time. Most LVR highway officials have no training in pavement design and even those that do have very little time to spare. If there was a good design tool that worked with the expertise of LVR managers and would allow designs to be done quickly, it would be more likely to be used.

Modern pavement design uses a mechanistic-empirical (ME) design approach, but the AASHTO *ME Pavement Design Guide* (ME PDG) is relatively complex and requires both time and expertise that most LVR managers do not have. While the ME PDG considers many different failure criteria, the two common pavement fatigue criteria of surface tensile strain and subgrade vertical strain are adequate for LVRs.

The available inputs for an LVR road are generally less extensive than a major road, but if well thought out, are still adequate for a design. The LVR pavement only needs to be within the closest ½ inch for an asphalt layer and even if the design is slightly non-conservative it will still serve the public better than the existing methods for choosing the thickness of the pavement layers.

*RoadPE: LHI* overcomes most of the conclusions found during the project and listed above. It is not as precise as the ME PDG, but it meets the needs of LVR highway officials on their level. It includes smart features to take advantage of the needs of the LVR community and the knowledge and expertise of LVR managers.

This first edition of *RoadPE: LHI* will need to be updated as more knowledge is gained and as the tool is used. The tool is not static and should adapt over time to meet the needs and wants of the LVR community.

## Bibliography

- (1) Douglas, R. A. *Low-Volume Road Engineering*. CRC Press, Boca Raton, FL, 2016.
- (2) Orr, D. P. *Pavement Maintenance*. Cornell Local Roads Program, Ithaca, NY, 2006.
- (3) NYSDOT. *Comprehensive Pavement Design Manual*. New York State Department of Transportation, Albany, NY, 2000.
- (4) *Asphalt Pavement Design Guide for Low-Volume Roads and Parking Lots*. South Carolina Asphalt Pavement Association, Columbia, SC, 2016.
- (5) Vitillo, N. *DARWIN-ME Pavement Analysis and Design Manual for NJDOT*. *Rutgers - CAIT Pavement Resource Program*, Rutgers University, 2012.
- (6) AASHTO. *Mechanistic-Empirical Pavement Design Guide*. American Association of State Highway and Transportation Officials, 2020.
- (7) ---. *AASHTO Guide for Design of Pavement Structures*. American Association of State Highway and Transportation Officials, Washington, D.C., 1993.
- (8) NYSDOT. *The New York State Thickness Design Manual for New and Reconstructed Pavements*. New York State Department of Transportation, Albany, NY, 1993.
- (9) Luhr, D. R., B. F. McCullough, and A. F. Stock. *Development of a Rationally Based Aasho Road Test Algorithm*. 1980.
- (10) AASHO. *AASHO Interim Guide for Design of Pavement Structures*. American Association of State Highway Officials, Washington, D.C., 1963.
- (11) Painter, L. J. *Analysis of AASHO Road Test Asphalt Pavement Data by the Asphalt Institute*. Transportation Research Board, Washington, DC, 1965. pp. 15-38.
- (12) US GAO. *Highway Pavement Design Guide is Outdated*. United States General Accounting Office, Washington, DC, 1997.
- (13) James, R. S., L. A. Cooley, and R. C. Ahlrich. *Summary of Lessons Learned from the MDOT MEPDG Materials Library Study*, Jackson, MS, 2010.
- (14) Puppala, A. J. *Estimating Stiffness of Subgrade and Unbound Materials for Pavement Design*. Publication NCHRP Synthesis 382, Washington, DC, 2008.
- (15) NCHRP. *2002 Pavement Design Guide Home - Using Mechanistic Principles to Improve Pavement Design*. National Cooperative Highway Research Program, 2002, [www.2002designguide.com/](http://www.2002designguide.com/).
- (16) Irwin, L. H. *Practical Realities and Concerns Regarding Pavement Evaluation*. *4th International Conference of the Bearing Capacity of Roads and Airfields*, Minnesota Department of Transportation, St Paul, MN, 1994.

- (17) Ishibashi, I., L. H. Irwin, and W. S. Lee. Resilient Behavior of Base and Subgrade Materials. Cornell University, Ithaca, NY, 1984.
- (18) Irwin, L. H., and D. P. Orr. Independent Review of The Recommended Mechanistic-Empirical Design Guide and Software: Low Volume Road Design: Memorandum of Findings. *No. Project No. 1-40A (04)*, Transportation Research Board, Washington, DC, 2006.
- (19) Flexible Pavements of Ohio Pavement Standards for Local Roads & Streets. *Ohio Asphalt, No. Summer 2007*, Columbus, OH, 2007.
- (20) Orr, D. P., and L. H. Irwin. Developing Seasonal Pavement Design Models Using Falling Weight Deflectometer Testing. *13th International Conference on Cold Regions Engineering*, American Society of Civil Engineers, Orono, ME, 2006.
- (21) Duffy, B., D. Orr, and H. J. Miller. Enhancements to a Simple Pavement Frost Model. *Transportation Research Record*, Vol. 2579, 2016,
- (22) Orr, D. P., P. Mung, and B. Duffy. Cornell Spring Thaw Predictor for Local Highway Agencies in New York State. Cornell Local Roads Program, Ithaca, NY, 2018.
- (23) Orr, D. P. When Should Agencies Post Weight Limits on Local Highways in New York State. *Transportation Research Record*, Vol. 2673, 2019,
- (24) AASHTO. *Guidelines for Geometric Design of Low-Volume Local Roads*. American Association of State Highway and Transportation Officials, Washington, DC, 2019.
- (25) Microsoft Excel for Office 365. Microsoft Corporation, Redmond, WA, 2020, [www.microsoft.com](http://www.microsoft.com).
- (26) Cline, M. G., and R. L. Marshall. General Soil Map of New York State. Cornell University Agricultural Experiment Station, Ithaca, NY, 1976.
- (27) Neeley, J. A. *Soil Survey of Tompkins County, New York*. United States Department of Agriculture, Washington, DC, 1961.
- (28) Richter, H. H., and F. T. Hsia. Consideration of Seasonal Pavement Damage for Timber Haul Roads. 1987, Link to Holdings [http://library10.library.cornell.edu/cgi-bin/Pwebrecon.cgi?DB=local&BOOL1=as%2Ba%2Bphrase&FLD1=ISSN%2B\(ISSN\)&CNT=10&SAB1=0361-1981](http://library10.library.cornell.edu/cgi-bin/Pwebrecon.cgi?DB=local&BOOL1=as%2Ba%2Bphrase&FLD1=ISSN%2B(ISSN)&CNT=10&SAB1=0361-1981).
- (29) *How can I get a quick estimate of traffic volume on my highways without traffic counters or a speed trailer?* Cornell Local Roads Program, Ithaca, NY. <http://www.clrp.cornell.edu/q-a/212-TrafficCounts.html2020>.
- (30) Oglesby, C. H., and R. G. Hicks. *Highway Engineering*. John Wiley & Sons, Inc., Chichester, Sussex England, 1982.
- (31) *Verification, Refinement, and Applicability of Long-Term Pavement Performance Vehicle Classification Rules*. Publication FHWA-HRT-13-091, Washington, DC, 2014.
- (32) Orr, D. P. Seasonal Variations of In Situ Materials Properties in New York State. Cornell

University, Ph.D., Ithaca, NY, 2005.

(33) Irwin, L. H. Backcalculation: an Overview and Perspective. *6th International Conference on the Bearing Capacity of Roads, Railways, and Airfields: FWD / Backcalculation Workshop*, Instituto Superior Technico, Lisbon, Portugal, 2002.

(34) Irwin, L. H. CHEVLAY2. Cornell Local Roads Program, Ithaca, NY, 1994.

(35) Richter, C. A. Seasonal Monitoring of Pavements - A Whole More. *Road and Airport Pavement Response Monitoring Systems*, American Society of Civil Engineers, Hanover, NH, 1991.