

CT  
87  
16

**COPY 2**



**FEDERAL AVIATION ADMINISTRATION**

**MAR 23 Rec'd**

**TECHNICAL CENTER LIBRARY  
ATLANTIC CITY, N.J. 08405**

**DOT/FAA/CT-87/16**

**FAA Technical Center  
Atlantic City International Airport  
N.J. 08405**



# **The Effect of Weathering on Octane Quality for Winter-Grade and Summer-Grade Gasolines**

**Richard N. Wares**

**IIT Research Institute  
NATIONAL INSTITUTE FOR PETROLEUM AND ENERGY RESEARCH  
P.O. Box 2128  
Bartlesville, OK 74005  
(928) 336-2400**

**December 1987**

**Final Report**

**This document is available to the U.S. public  
through the National Technical Information  
Service, Springfield, Virginia 22161.**



**U.S. Department of Transportation  
Federal Aviation Administration**



00013478

**This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.**

|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |                                      |                                                                                                                                                             |           |
|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|--------------------------------------|-------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------|
| 1. Report No.<br>DOT/FAA/CT-87/16                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                     | 2. Government Accession No.          | 3. Recipient's Catalog No.                                                                                                                                  |           |
| 4. Title and Subtitle<br><br>The Effect of Weathering on Octane Quality for Winter-Grade and Summer-Grade Gasolines                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                   |                                      | 5. Report Date<br>December 1987                                                                                                                             |           |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |                                      | 6. Performing Organization Code                                                                                                                             |           |
| 7. Author(s)<br>Richard N. Wares                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                      |                                      | 8. Performing Organization Report No.                                                                                                                       |           |
| 9. Performing Organization Name and Address<br><br>National Institute for Petroleum and Energy Research (NIPER)<br>P.O. Box 2128, Bartlesville, OK 74005                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                              |                                      | 10. Work Unit No. (TRAIS)                                                                                                                                   |           |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |                                      | 11. Contract or Grant No. Coop Agrmt<br>DE-FC22-83FE60149                                                                                                   |           |
| 12. Sponsoring Agency Name and Address<br>U.S. Department of Transportation<br>Federal Aviation Administration<br>Technical Center<br>Atlantic Ceity Airport, New Jersey 08405                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                        |                                      | 13. Type of Report and Period Covered<br><br>Final Report                                                                                                   |           |
|                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                       |                                      | 14. Sponsoring Agency Code                                                                                                                                  |           |
| 15. Supplementary Notes                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                               |                                      |                                                                                                                                                             |           |
| 16. Abstract<br><br><p>Weathering tests were conducted to examine the effects on fuel volatility and octane characteristics. The commercially available gasolines utilized in the study represented a wide geographic distribution for both winter and summer fuels. Aging was accomplished by heating the fuel samples to 110 degrees F and maintaining that temperature for 48 hours. Time histories of Reid Vapor Pressure (RVP) were conducted. Fuel octane evaluations, both MON and RON, were done. Component characterization by gas chromatography were made to identify components lost during the aging process.</p> <p>The time histories of vapor pressure changes depended to a limited measure on the initial fuel vapor pressure as well as to differences in composition. Butanes and isopentanes were the primary constituents lost due to the weathering. For the most part octane changes due to fuel weathering were minimal.</p> |                                      |                                                                                                                                                             |           |
| 17. Key Words<br>Volatility Changes<br>Octane Changes<br>Aging<br>Gas Chromatography<br>Automobile Gasoline<br>Distillation                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                           |                                      | 18. Distribution Statement<br>This document is available to the U.S. public through the National Technical Information Service, Springfield, Virginia 22161 |           |
| 19. Security Classif. (of this report)                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                                | 20. Security Classif. (of this page) | 21. No. of Pages                                                                                                                                            | 22. Price |



## ACKNOWLEDGMENT

The work described in this report was performed in partial fulfillment of the requirements of the Cooperative Agreement DE-FC22-83FE60149 between the U.S. Department of Energy and the IIT Research Institute with primary sponsorship by the Federal Aviation Administration. In particular, the efforts of Mr. Gus Ferrara who provided direction for the FAA and assistance in the effort is acknowledged. Mr. Alex Crawley of the Bartlesville Project Office in Bartlesville, Oklahoma, coordinated the effort for the U.S. Department of Energy.



## TABLE OF CONTENTS

|                           | <u>Page</u> |
|---------------------------|-------------|
| Acknowledgment.....       | iii         |
| Executive Summary.....    | vii         |
| Introduction.....         | 1           |
| Experimental Program..... | 1           |
| Test Fuels.....           | 1           |
| Test Procedures.....      | 1           |
| Results.....              | 4           |
| Winter-Grade Fuels.....   | 4           |
| Summer-Grade Fuels.....   | 5           |
| Conclusions.....          | 6           |
| References.....           | 6           |
| Appendix A                |             |
| Distribution List.....    | A-1         |

## TABLES AND ILLUSTRATIONS

### Table

|    |                                                       |    |
|----|-------------------------------------------------------|----|
| 1  | Vapor pressure versus time.....                       | 7  |
| 2  | Octane ratings.....                                   | 7  |
| 3  | Fuel composition summary, New Orleans, winter.....    | 23 |
| 4  | Fuel composition summary, Chicago, winter.....        | 24 |
| 5  | Fuel composition summary, Ft. Lauderdale, winter..... | 25 |
| 6  | Fuel composition summary, Philadelphia, winter.....   | 26 |
| 7  | Fuel composition summary, San Diego, winter.....      | 27 |
| 8  | Fuel composition summary, Rockville, winter.....      | 28 |
| 9  | Fuel composition summary, Sacramento, winter.....     | 29 |
| 10 | Fuel composition summary, Houston, winter.....        | 30 |
| 11 | Fuel composition summary, Wichita, winter.....        | 31 |
| 12 | Fuel composition summary, Denver, winter.....         | 32 |
| 13 | Vapor pressure versus time, summer fuels.....         | 33 |
| 14 | Octane ratings, summer fuels.....                     | 33 |
| 15 | Fuel composition summary, Denver, summer.....         | 44 |
| 16 | Fuel composition summary, Wichita, summer.....        | 45 |
| 17 | Fuel composition summary, Washington DC, summer.....  | 46 |
| 18 | Fuel composition summary, San Diego, summer.....      | 47 |
| 19 | Fuel composition summary, Houston, summer.....        | 48 |
| 20 | Fuel composition summary, Sacramento, summer.....     | 49 |
| 21 | Fuel composition summary, Ft. Lauderdale, summer..... | 50 |
| 22 | Fuel composition summary, Duluth, summer.....         | 51 |
| 23 | Fuel composition summary, New Orleans, summer.....    | 52 |
| 24 | Fuel composition summary, Chicago, summer.....        | 53 |

### Figure

|   |                                                                                |   |
|---|--------------------------------------------------------------------------------|---|
| 1 | Vapor pressure history, winter fuels from<br>Houston and Sacramento.....       | 8 |
| 2 | Vapor pressure history, winter fuels from<br>Philadelphia and New Orleans..... | 9 |

# TABLE OF CONTENTS--CONTINUED

| <u>Figure</u> |                                                                                              | <u>Page</u> |
|---------------|----------------------------------------------------------------------------------------------|-------------|
| 3             | Vapor pressure history, winter fuels from<br>Rockville and San Diego.....                    | 10          |
| 4             | Vapor pressure history, winter fuels from<br>Denver and Wichita.....                         | 11          |
| 5             | Vapor pressure history, winter fuels from<br>Ft. Lauderdale and Chicago.....                 | 12          |
| 6             | Changes in distillation character due to weathering,<br>winter fuels from Philadelphia.....  | 13          |
| 7             | Changes in distillation character due to weathering,<br>winter fuels from New Orleans.....   | 14          |
| 8             | Changes in distillation character due to weathering,<br>winter fuels from Denver.....        | 15          |
| 9             | Changes in distillation character due to weathering,<br>winter fuels from Wichita.....       | 16          |
| 10            | Changes in distillation character due to weathering,<br>winter fuels from Houston.....       | 17          |
| 11            | Changes in distillation character due to weathering,<br>winter fuels from Sacramento.....    | 18          |
| 12            | Changes in distillation character due to weathering,<br>winter fuels from Rockville.....     | 19          |
| 13            | Changes in distillatopm character due to weathering,<br>winter fuels from San Diego.....     | 20          |
| 14            | Changes in distillation character due to weathering,<br>winter fuels from Ft.Lauderdale..... | 21          |
| 15            | Changes in distillation character due to weathering,<br>winter fuels from Chicago.....       | 22          |
| 16            | Changes in distillation character due to weathering,<br>summer fuel from New Orleans.....    | 34          |
| 17            | Changes in distillation character due to weathering,<br>summer fuels from Houston.....       | 35          |
| 18            | Changes in distillation character due to weathering,<br>summer fuels from Washington DC..... | 36          |
| 19            | Changes in distillation character due to weathering,<br>summer fuel from Denver.....         | 37          |
| 20            | Changes in distillation character due to weathering,<br>summer fuel from Duluth.....         | 38          |
| 21            | Changes in distillation character due to weathering,<br>summer fuel from Ft. Lauderdale..... | 39          |
| 22            | Changes in distillation character due to weathering,<br>summer fuel from Chicago.....        | 40          |
| 23            | Changes in distillation character due to weathering,<br>summer fuel from Sacramento.....     | 41          |
| 24            | Changes in distillation character due to weathering,<br>summer fuel from San Diego.....      | 42          |
| 25            | Changes in distillation character due to weathering,<br>summer fuel from Wichita.....        | 43          |



## EXECUTIVE SUMMARY

This report describes studies conducted at the National Institute of Petroleum and Energy Research (NIPER) for the Federal Aviation Administration (FAA) under a cost sharing agreement with the U.S. Department of Energy. In these studies, the effect of aging automobile gasoline on its volatility and its octane rating was measured.

The samples tested in this program represented a wide geographic distribution for both winter and summer blends of automobile gasoline. Aging was accomplished by heating the samples to 110° F in vented containers and keeping the fuel sample at that temperature for 48 hours. The change in the volatility of the fuel was measured using the Reid Vapor Pressure (or an equivalent test and correcting it to the Reid Vapor Pressure). The research and motor octane numbers were measured before and after aging. The distillation curve of each fuel was determined for both the initial and aged samples. The constituents of each fuel were identified for both the initial and aged samples using gas chromatography and the principle constituents lost during aging were identified.

The changes in the distillation curve and the Reid Vapor Pressure were greater for the winter-grade fuels than the summer-grade fuels. This was expected since the winter-grade fuels contain a larger percentage of low molecular weight constituents (e.g., butane and isopentane) and these are the principle components lost during the aging process.

The changes in octane as a consequence of aging were, for the most part, negligible. The principle exception was for the winter-grade sample of fuel from Philadelphia which contained an unusually high percentage of butane. The change in octane rating was similar for both the winter grade and the summer grade fuels.



## WEATHERING EFFECTS ON FUEL QUALITY

### INTRODUCTION

The mandated reduction in fuel lead level and an increasing demand for high octane quality fuels necessary for maximum performance of vehicles require refineries to consider all possible means to produce acceptable quality fuels at competitive costs.

In the light aircraft industry, concerns exist that the substitution of motor gasoline for aviation gasoline might result in engine failure during maximum power demands. Weathered fuels which have lost higher volatility components will have qualities that are more closely related to the remaining lower volatility components. The bulk of the remaining portion lies in the distillation range that would be produced from alternative feedstocks and these tend to be the lower octane components. Requests to the Federal Aviation Administration (FAA) for autogas certification have raised questions concerning current regulations. The fuel certification procedures require aircraft fuel tests to be conducted at 110° F. Concerns are related to the higher volatility characteristics of autogas compared to aviation gas and the possibility of inducing vapor lock at high temperatures. There is also inadequate information regarding the weathering effect of fuel storage at high temperature and resultant effects on fuel octane quality.

### EXPERIMENTAL PROGRAM

The experimental program at the National Institute for Petroleum and Energy Research (NIPER) was initiated to provide information to aid in making technical judgments on fuel, fuel specifications, and fuel conditioning requirements for a range of fuels that could be utilized in current light aircraft. This portion of the work is centered on determining the acceptability of motor fuels that have been weathered, causing loss of volatile components.

#### TEST FUELS.

Commercial auto gasolines from various locations were surveyed for volatility and octane quality--in both as-received and after-weathering conditions. Antiknock quality was evaluated to assess the suitability of this variety of auto fuels for aviation applications. Experiments have been conducted with ten winter (January-February) and ten summer (July-August) fuels that were obtained from commercial suppliers representing various geographic (refining) areas in the contiguous 48 states. The fuels were tested in as-received condition with no modifications to the existing vapor pressures. Specific fuel properties will be presented in the section dealing with test results.

#### TEST PROCEDURES.

Prior to testing, all fuels were stored in air tight sealed drums at 50° F and equilibrated at that temperature for a minimum of one week. The fuel weathering tests involved transferring the fuels to vented test tanks, heating

the fuel to 110° F and maintaining that fuel temperature for a 48-hour period. This time period was chosen to ensure noticeable aging effects following equilibration at 110° F. Fuel samples were taken within one hour of the time required for the fuel to equilibrate at 110° F and at 12, 24, and 48 hours afterward for determination of vapor pressures. In addition, fuel samples were taken both from the initial or fresh fuel and at the 48-hour point following temperature equilibration. These samples were analyzed for distillation characteristics (ASTM D 86), research octane number (RON) (ASTM D2699) and motor octane number (MON) (ASTM D2700). An attempt to identify specific components of the gasolines which are lost due to weathering at this temperature was conducted using gas chromatographic techniques.

Two fuel tanks representative of light aircraft were used. These were rectangular shaped with low height and large bottom surfaces. The total tank volumes were nominally 13 gallons. Each tank was vented through fill ports and this area was less than 2 percent of the tank top area. The tanks were placed on stands in a test cell having a temperature control range of 50° to 120° F  $\pm$  1°. Thermocouples were placed in the tanks approximately one inch above the bottom surface to monitor fuel temperature, and additional monitoring for temperature history was made with a chart recorder. The tank levels specified were a minimum of 90 percent full.

The test procedure consists of the following:

1. Fuels were stored at an ambient temperature 50° F and an initial (fresh fuel) sample was taken under these conditions.
2. Test fuel tanks were filled with 50° F fuel to the 12-gallon (92 percent full) level.
3. Tank vents were left open to the atmosphere.
4. The tanks were then placed in the soak area and heated to a fuel temperature of 110° F. This fuel temperature was controlled by room ambient temperature throughout the test to  $\pm$  1° F.
5. Fuel samples were taken within one hour of attaining the desired temperature. This was referred to as time = 0.
6. Additional samples were taken at 12, 24, and 48 hours following equilibration at 110° F.

As mentioned earlier, additional measurements were made with the initial and 48-hour samples. These included:

1. Distillation characteristics by ASTM D 86 technique.
2. Fuel octane evaluations--both RON and MON.
3. Component characterization by gas chromatographic analyses.

Vapor pressure measurements were made from all samples taken. The fuel samples for vapor pressure analyses were stored and equilibrated at 50° F. Vapor pressure measurements for the ten winter grade fuels were made at NIPER using the ASTM microvapor pressure (MVP) procedure D 2551-71. The MVP was measured with a model "G" vapor pressure gauge from Manufacturers Engineering and Equipment Corporation.

The micro method was developed as an alternative to the standard RVP procedure ASTM D 323 to offer an advantage in speed and size of sample required. The RVP method consisted of filling a gasoline chamber of vapor pressure apparatus with a chilled sample of gasoline. The gasoline chamber was connected to an air chamber maintained at 100° F, and the apparatus was immersed in a bath at 100° F and shaken periodically until a constant pressure was observed on a gauge attached to the apparatus. The gauge reading, suitably corrected, was reported as Reid vapor pressure.

The microvapor pressure consisted of introducing a liquid sample into an evacuated chamber fitted with means of measuring pressure in the chamber before and after sample introduction. The apparatus was immersed in a constant temperature bath of 100° F. Both the RVP and MVP procedures used vapor/liquid volume ratios of about 4:1.

When a sample of volatile hydrocarbons is saturated with air and introduced into a chamber and allowed to equilibrate, the increase in pressure is equal to the sum of the following four pressures:

1. The vapor pressure of the liquid at the temperature of the chamber.
2. The partial pressure of the dissolved air that comes out of solution.
3. The partial pressure of the dissolved water.
4. The compression effect of the liquid volume on initial air within the chamber.

The only significant pressures of these four which contribute to the total pressure are the first two, the vapor pressure of the sample and partial pressure of the dissolved air.

By nature of the systems, the evacuated chamber associated with the MVP presumes that all dissolved air will come entirely out of the solution and be measured and corrected; whereas, the Reid method (above atmospheric pressure) automatically compensates for the effect of dissolved air. Therefore, the RVP of a given sample will always be lower than the MVP of the same sample. For conversion of MVP results to RVP, the MVP may be corrected for the effect of dissolved air or empirically correlated with Reid values.

The samples were saturated with air at 50° F and pressures measured by mercury manometer at 100° F by mercury manometer. The empirical mathematical relationship of MVP and RVP was supplied with the test apparatus.

The equation:

$$\text{ERVP, psi} = 0.019 (\text{MVP, mmHg}) - 0.66$$

allows the measured MVP to be expressed as an equivalent Reid vapor pressure (ERVP).

The summer fuel vapor pressure measurements were made using the Reid procedure. A Herzog semi-automatic Reid vapor pressure apparatus was used. The change in vapor pressure apparatus for the summer measurements was made primarily for purpose of faster turnaround. Results from the two types of vapor pressure measurements were examined at NIPER for a variety of fuels in the pressure range of interest and were found to be very comparable.

## RESULTS

### WINTER-GRADE FUELS.

Table 1 shows a tabular history of the fuel vapor pressure changes due to weathering effects at 110° F. The fuels are identified by the city of origin. These data are presented as ERVP. The vapor pressure samples were taken within the previously defined time limits. As a group, the original or unweathered pressures had (with Philadelphia as an exception) an approximate range of 12.5 to 14 psi. The Philadelphia fuel had a value of 16.1 psi. The weathered values varied from about 10 to 11 psi indicating losses in ERVP ranging from about 2.0 to 3.0 psi for the 48-hour period.

Figures 1 through 5 are the plotted vapor pressure results for fuels which were tested simultaneously. It should be noted that the differences in equilibration time (from initial sample to  $t = 0$ ) are due to changes in test cell heating capabilities. An initial malfunction in the system was responsible for longer equilibration periods as seen in the Denver-Wichita plot (figure 4). These times were reduced to around 10 hours following repairs. Cell temperatures at times reached 130° F during this period, but careful modulation assured no fuel temperature excursions from the target values. A linear regression analysis was conducted on the results for the winter grade fuels. From these results there appears to be a strong relationship between the change in vapor pressure and the initial RVP; that is, the higher the initial RVP, the greater the change due to aging. However, this relationship is also affected by fuel compositional differences. The data suggest that fuels with similar initial vapor pressures, i.e., Denver-Wichita and Rockville-San Diego, do not necessarily weather similarly. These differences would appear to be attributable to compositional differences. In general, most of the vapor pressure decreases occurred before the 12-hour weathering point.

Table 2 presents octane changes (both RON and MON) for these ten high vapor pressure winter fuels. Decreases in octane quality due to weathering appeared to be minimal and were generally less than 0.3 octane number. Most of these data were within experimental repeatability. An exception is seen with the winter Philadelphia regular unleaded fuel. A decrease of 0.7 in MON was noted and as can be seen in the compositional data, is attributed to the high initial content of butane.

Figures 6 through 15 show changes in the fuels' distillation character due to the controlled weathering conditions. The fuels all exhibited similar trends, with the major effect due to loss of volatile front-end components.

Increases in fuel initial boiling point (IBP) attributable to the 110° F soak ranged from 3° to 8° F. Ten-volume percent distilled level changes varied from a low of 7° F for the Sacramento fuel to a high of 16° F for the unleaded fuel from Wichita.

All of the fuels showed similar trends for the most part, with the high vapor pressure Philadelphia fuel exhibiting the largest changes in boiling character. Distillation temperature increases for this fuel ranged to more than 30° F between the 5- and 50-volume percent distilled points. Again, the larger changes in this fuel are attributable to losses of a large amount of butane contained in the original fuel.

Tables 3 through 12 are fuel compositions for the individual fuels. These are results of gas chromatographic analyses conducted on the initial and 48- hour samples. These GC data are presented as volume percent summations as a function of both carbon number and compound class. A listing of compound specific analyses for each summer and winter fuel, original and weathered, are contained in reference 1. In general, as might be expected, most of the changes occur in the C<sub>1</sub> to C<sub>5</sub> range containing the most volatile materials, i.e., butanes, and pentanes. Note that when reviewing tables 3 through 12, relative changes should be kept in mind; as one component decreases, the relative percentage of the others increase.

As an example, the 16.1 psi Philadelphia fuel exhibited the largest changes in vapor pressure, octane, and distillation character. Table 4 presents the compositional summaries from samples taken before and after weathering. By far, the largest total change is with the C<sub>4</sub> compounds. The very high initial vapor pressure would suggest that the volatile materials lost were butane and isopentane. The specific component listing in reference 1 indicates a high initial butane content.

#### SUMMER-GRADE FUELS.

The summer fuels tested were procured from geographic locations similar to those of the winter fuels. Both regular and premium unleaded gasolines were obtained, and as would be discovered, a gasohol fuel was included. Table 13 shows the effect of a controlled 110° F soak on the vapor pressures. Unweathered fuel RVP values were from about 8.5 to 11 psi. Decreases in vapor pressures due to weathering ranged from a low of 0.5 psi for Wichita samples to a high of 2.5 psi for Duluth. As with the winter fuels, most of the decreases occurred within 12 hours, and the drop in RVP appears to be marginally dependent on the initial RVP of the summer grade blends, with the fuel composition affecting the overall decline.

Octane quality changes are presented in table 14. Motor octane results showed no degradation for most of the fuels. Only the premium unleaded Sacramento fuel tests indicated a significant octane decrease of 0.7.

Figures 16 through 25 contain information on the summer fuel distillation character before and after weathering. For most cases, there were barely discernible differences in fuel boiling range due to weathering. IBP changes were minimal. The Houston fuel exhibited the most change with 5, 10, and 20 percent points increasing by about 10° F after weathering. This is not unexpected for these fuels since they contain far lower quantities of the more volatile front-end components normally used for vapor pressure enhancement. Specific alcohol analysis was conducted with the New Orleans fuel. Results showed 10-volume percent ethanol, thus accounting for the unusual shape of the distillation curves--the boiling point for ethanol is 173° F.

Tables 15 through 25 contain fuel compositional summaries for the summer fuels. As with the winter fuel results, the changes occur mostly in the front ends, from C<sub>1</sub> to C<sub>5</sub>. Again, the specific component results for these fuels are contained in reference 1. It should be noted that the relatively small component losses for these fuels had essentially no effects on their octane and distillation characteristics.

## CONCLUSIONS

Tests were conducted to measure the effect of aging automobile gasoline on fuel volatility and octane characteristics. Winter and summer grade fuels were acquired from various locations in the contiguous 48 states.

It can be concluded that in most cases changes in automobile gasoline octane quality due to aging fuels at 110° F for 48 hours would be negligible for both summer and winter fuels. The only exceptions noted in these tests were due in one case to a relatively high butane concentration in the fuel and in another a sample container leaked following aging but prior to testing for the octane rating.

The magnitude of decrease in volatility, as characterized by Reid Vapor Pressure (RVP) was somewhat dependent on the initial test fuel RVP. However, fuels with similar initial vapor pressures do not necessarily age in a similar manner. Volatility decreases due to aging are dependent on the type and quantity of light hydrocarbon components found in the fuel.

Decreases in RVP due to aging, for both summer and winter fuels, occurred primarily during the 12-hour period following equilibration at 110° F. Changes occurring between 24 and 48 hours were within method repeatability.

Aging of the summer-grade fuels produced only minor increases in the distillation temperatures. Increases in the initial boiling point and distillation curve were more pronounced for the winter-grade fuels. These increases were most evident in the front end (low molecular weight-low boiling) point range of the distillation curve. The winter grade Philadelphia gasoline, which contained a very high butane concentration, exhibited the greatest loss in volume. The changes measured in these experiments are similar to results from similar studies contained in references 2, 3, and 4.

## REFERENCES

1. Tabulation of Gas Chromatography Data from Fuel Aging Studies, DOT/FAA/CT-TN87/, Richard Wares, National Institute for Petroleum and Energy Research, to be published.
2. Weathering Effects on Autogas, DOT/FAA/CT-TN86/54, Richard Wares and Jerry Allsup, National Institute for Petroleum and Energy Research, October 1985.
3. Effects of Heating and Agitation upon Autogas Volatility, DOT/FAA/CT-TN86/32, Leslie G. Rice, Federal Aviation Administration Technical Center, December 1986.
4. Autogas in General Aviation Aircraft, DOT/FAA/CT-87/05, H. Stewart Byrnes, William C. Cavage and Augusto M. Ferrara, Federal Aviation Administration Technical Center, April 1987.



TABLE 1. - Vapor pressure versus time

| Fuel               | Equivalent Reid Vapor Pressure (psi) |       |       |       |       |
|--------------------|--------------------------------------|-------|-------|-------|-------|
|                    | Original                             | Time  |       |       |       |
|                    |                                      | 0     | 12    | 24    | 48    |
| Houston, TX        | 12.51                                | 11.69 | 11.31 | 10.97 | 10.65 |
| Sacramento, CA     | 12.51                                | 11.46 | 10.99 | 11.10 | 10.61 |
| Philadelphia, PA   | 16.14                                | 12.11 | 11.37 | 11.16 | 10.78 |
| New Orleans, LA    | 12.66                                | 11.61 | 11.10 | 11.03 | 10.80 |
| Rockville, MD      | 12.85                                | 10.99 | 10.70 | 10.32 | 10.13 |
| San Diego, CA      | 12.98                                | 11.48 | 11.18 | 10.95 | 10.87 |
| Denver, CO         | 14.06                                | 12.36 | 11.73 | 11.27 | 10.84 |
| Wichita, KS        | 14.08                                | 12.08 | 11.69 | 11.54 | 11.37 |
| Ft. Lauderdale, FL | 11.98                                | 10.19 | 10.15 | 10.04 | 9.81  |
| Chicago, IL        | 13.93                                | 11.82 | 11.44 | 11.37 | 10.87 |

TABLE 2. - Octane ratings

| Fuel               | RON     |       |       | MON     |       |       |
|--------------------|---------|-------|-------|---------|-------|-------|
|                    | Initial | Final | Diff. | Initial | Final | Diff. |
| Houston, TX        | 91.6    | 91.5  | 0.1   | 82.6    | 82.4  | 0.2   |
| Sacramento, CA     | 92.0    | 91.7  | 0.3   | 82.6    | 82.4  | 0.2   |
| Philadelphia, PA   | 92.1    | 91.7  | 0.4   | 81.5    | 80.8  | 0.7   |
| New Orleans, LA    | 92.3    | 92.3  | 0.0   | 86.2    | 86.1  | 0.1   |
| Rockville, MD      | 91.7    | 91.4  | 0.3   | 82.3    | 82.2  | 0.1   |
| San Diego, CA      | 92.3    | 92.1  | 0.2   | 82.8    | 82.5  | 0.3   |
| Denver, CO         | 89.0    | 88.6  | 0.4   | 80.5    | 80.1  | 0.4   |
| Wichita, KS        | 91.8    | 91.7  | 0.1   | 82.8    | 82.5  | 0.3   |
| Ft. Lauderdale, FL | 91.6    | 91.6  | 0.0   | 82.2    | 82.1  | 0.1   |
| Chicago, IL        | 91.3    | 91.3  | 0.0   | 82.4    | 82.3  | 0.1   |

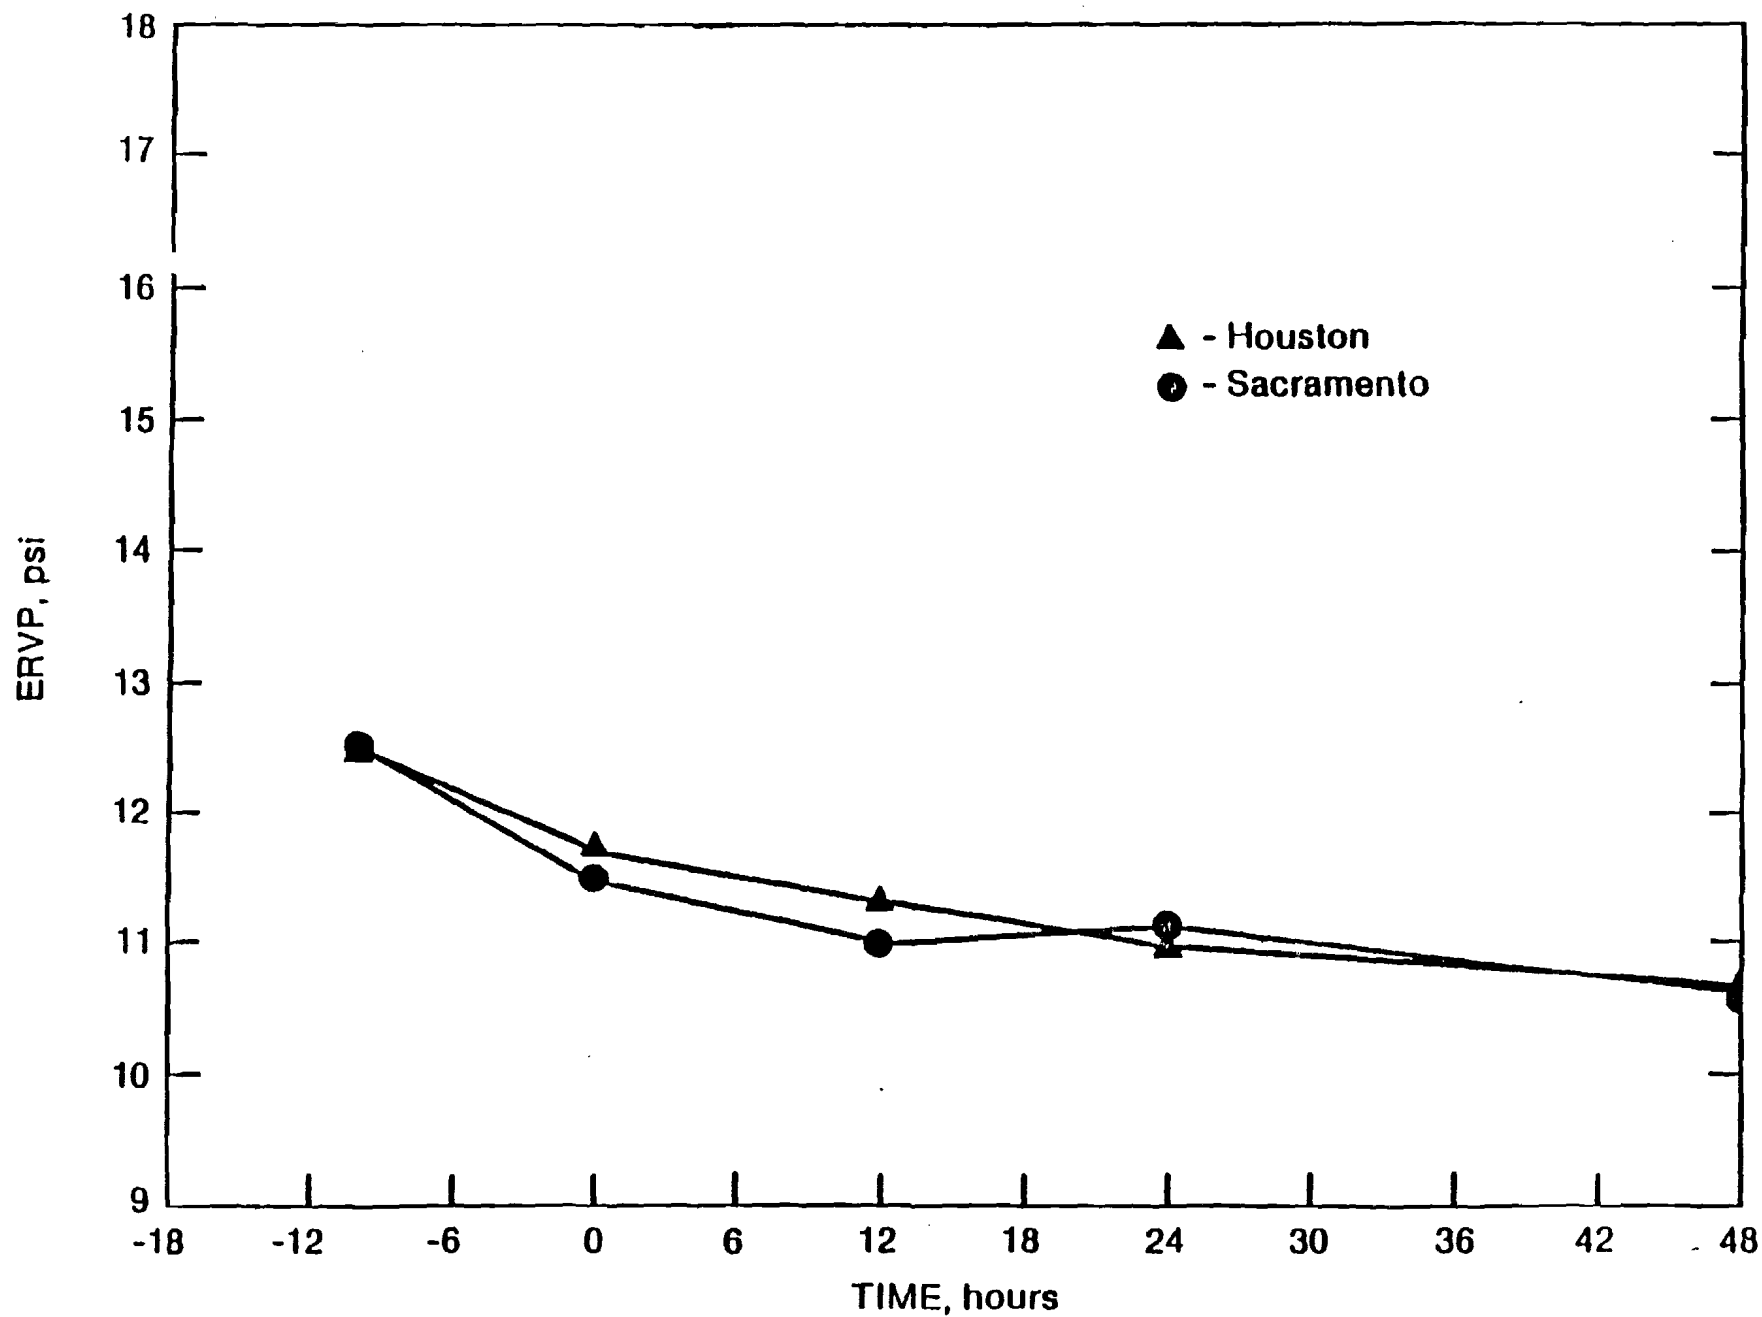


FIGURE 1. - Vapor pressure history, winter fuels from Houston and Sacramento.

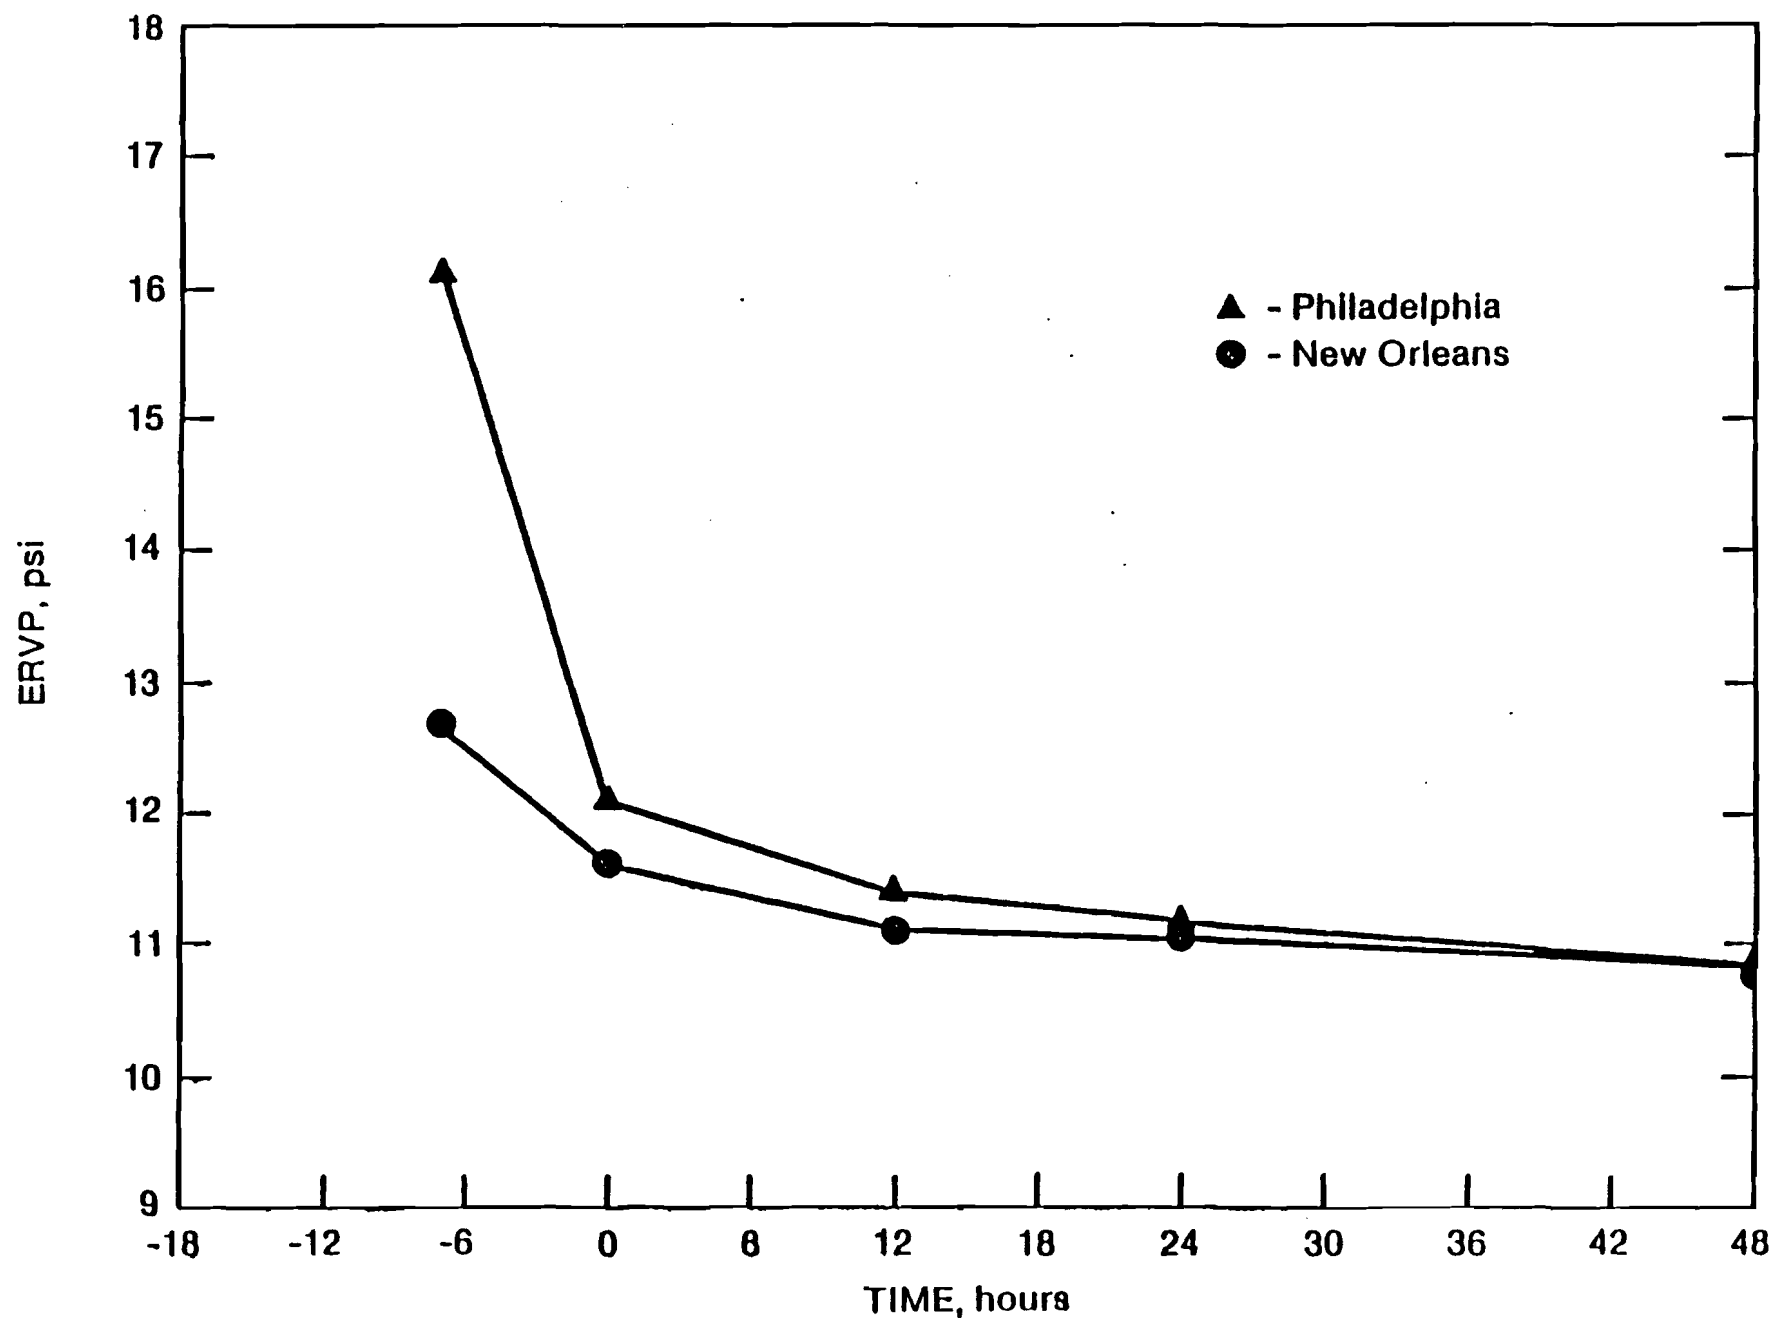


FIGURE 2. - Vapor pressure history, winter fuels from Philadelphia and New Orleans.

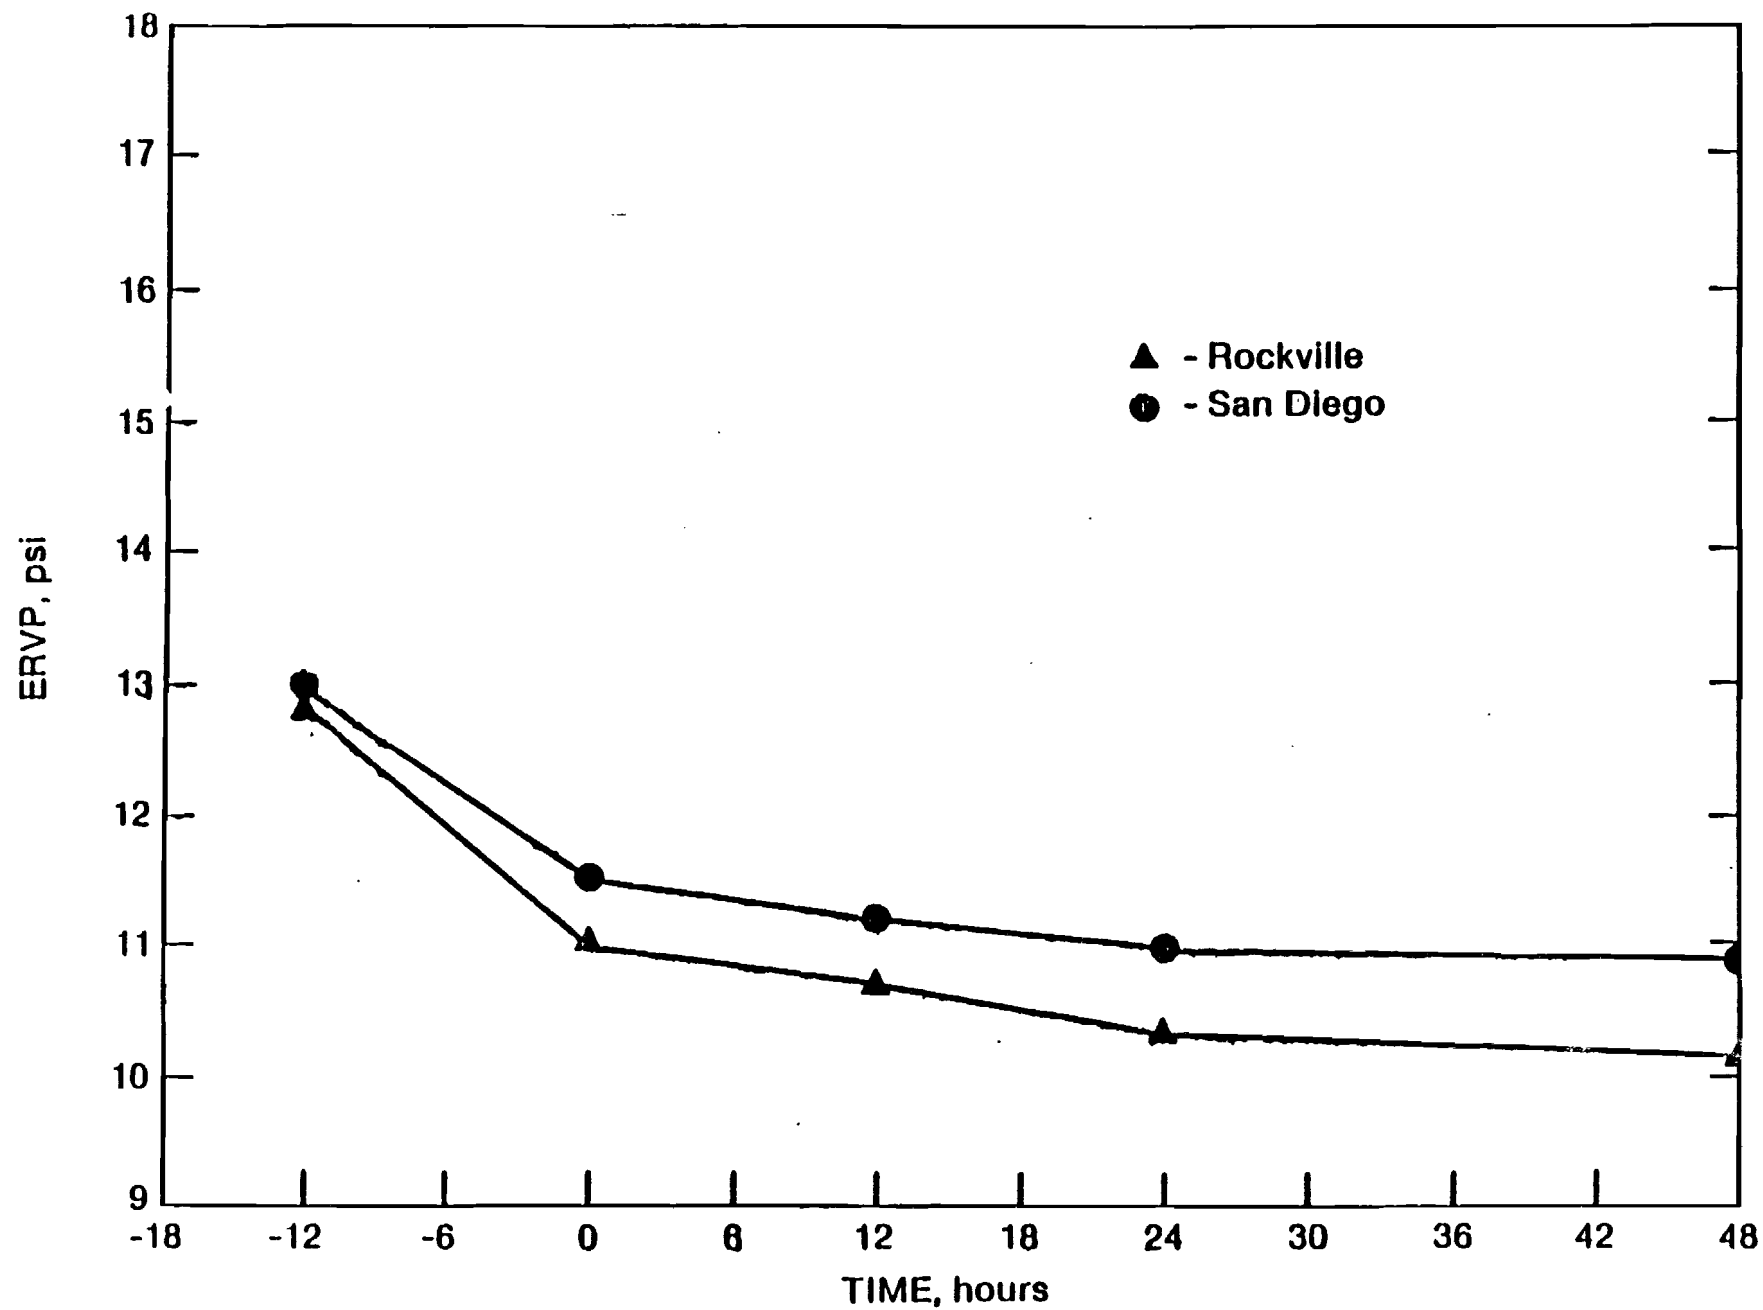


FIGURE 3. - Vapor pressure history, winter fuels from Rockville and San Diego.

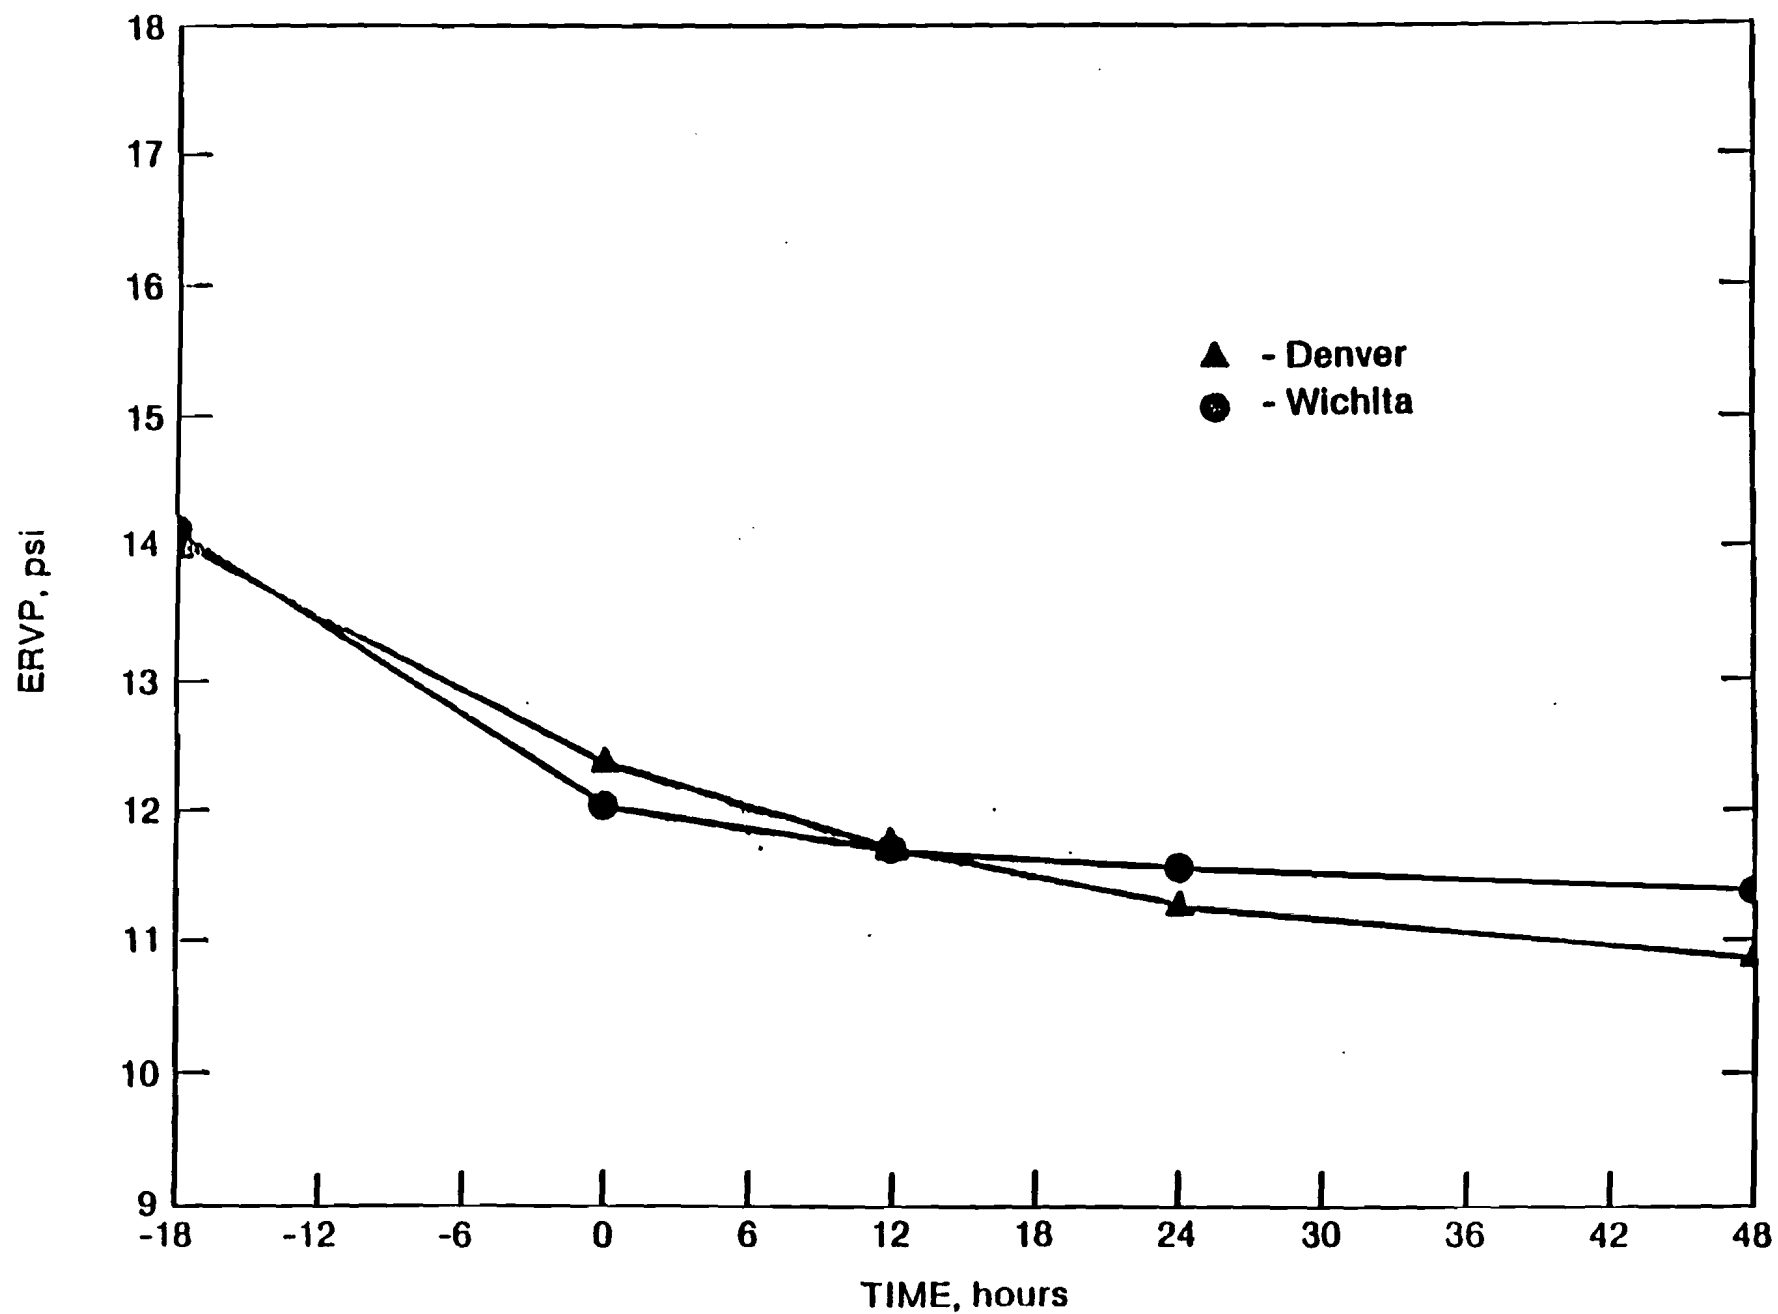


FIGURE 4. - Vapor pressure history, winter fuels from Denver and Wichita.

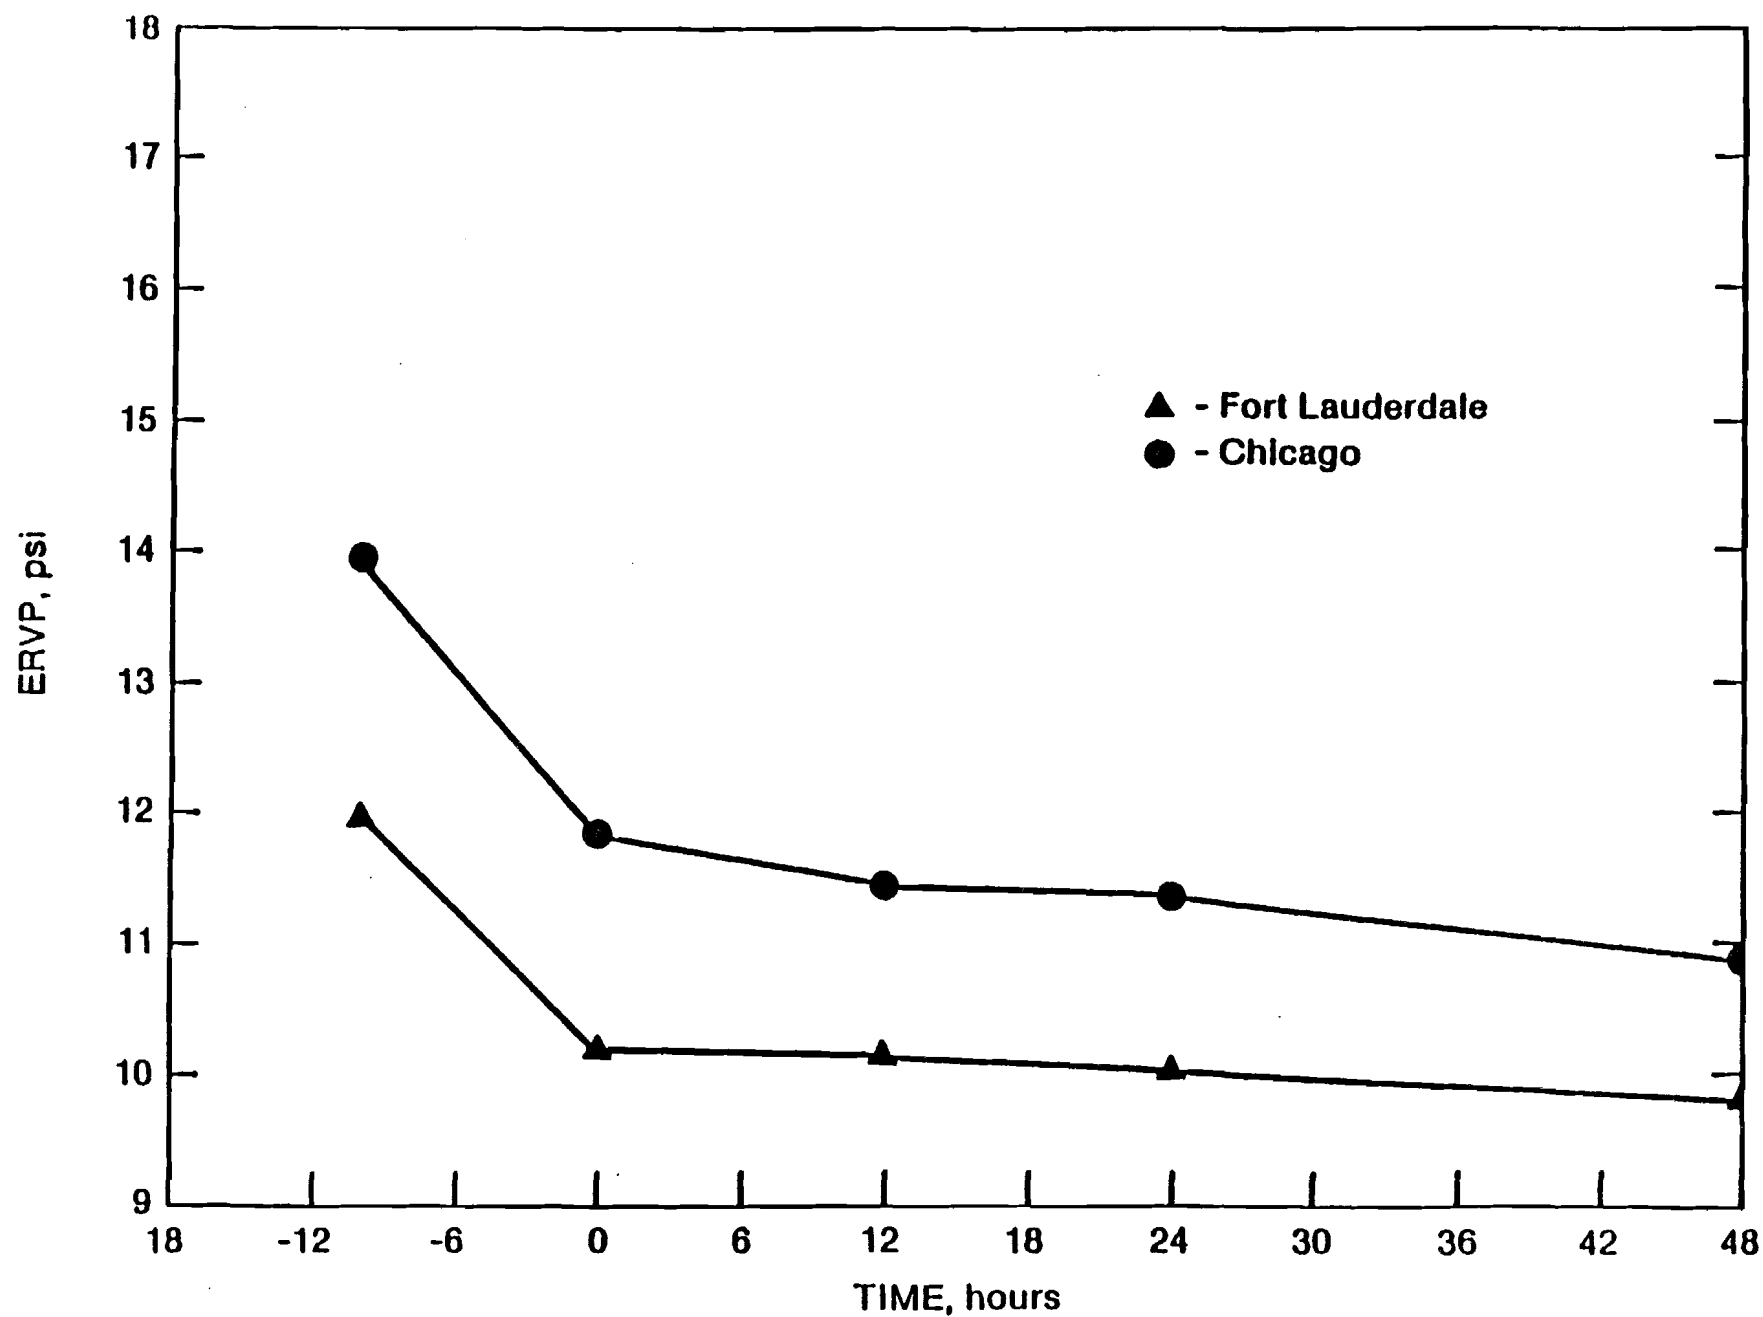


FIGURE 5. - Vapor pressure history, winter fuels from Ft. Lauderdale and Chicago.

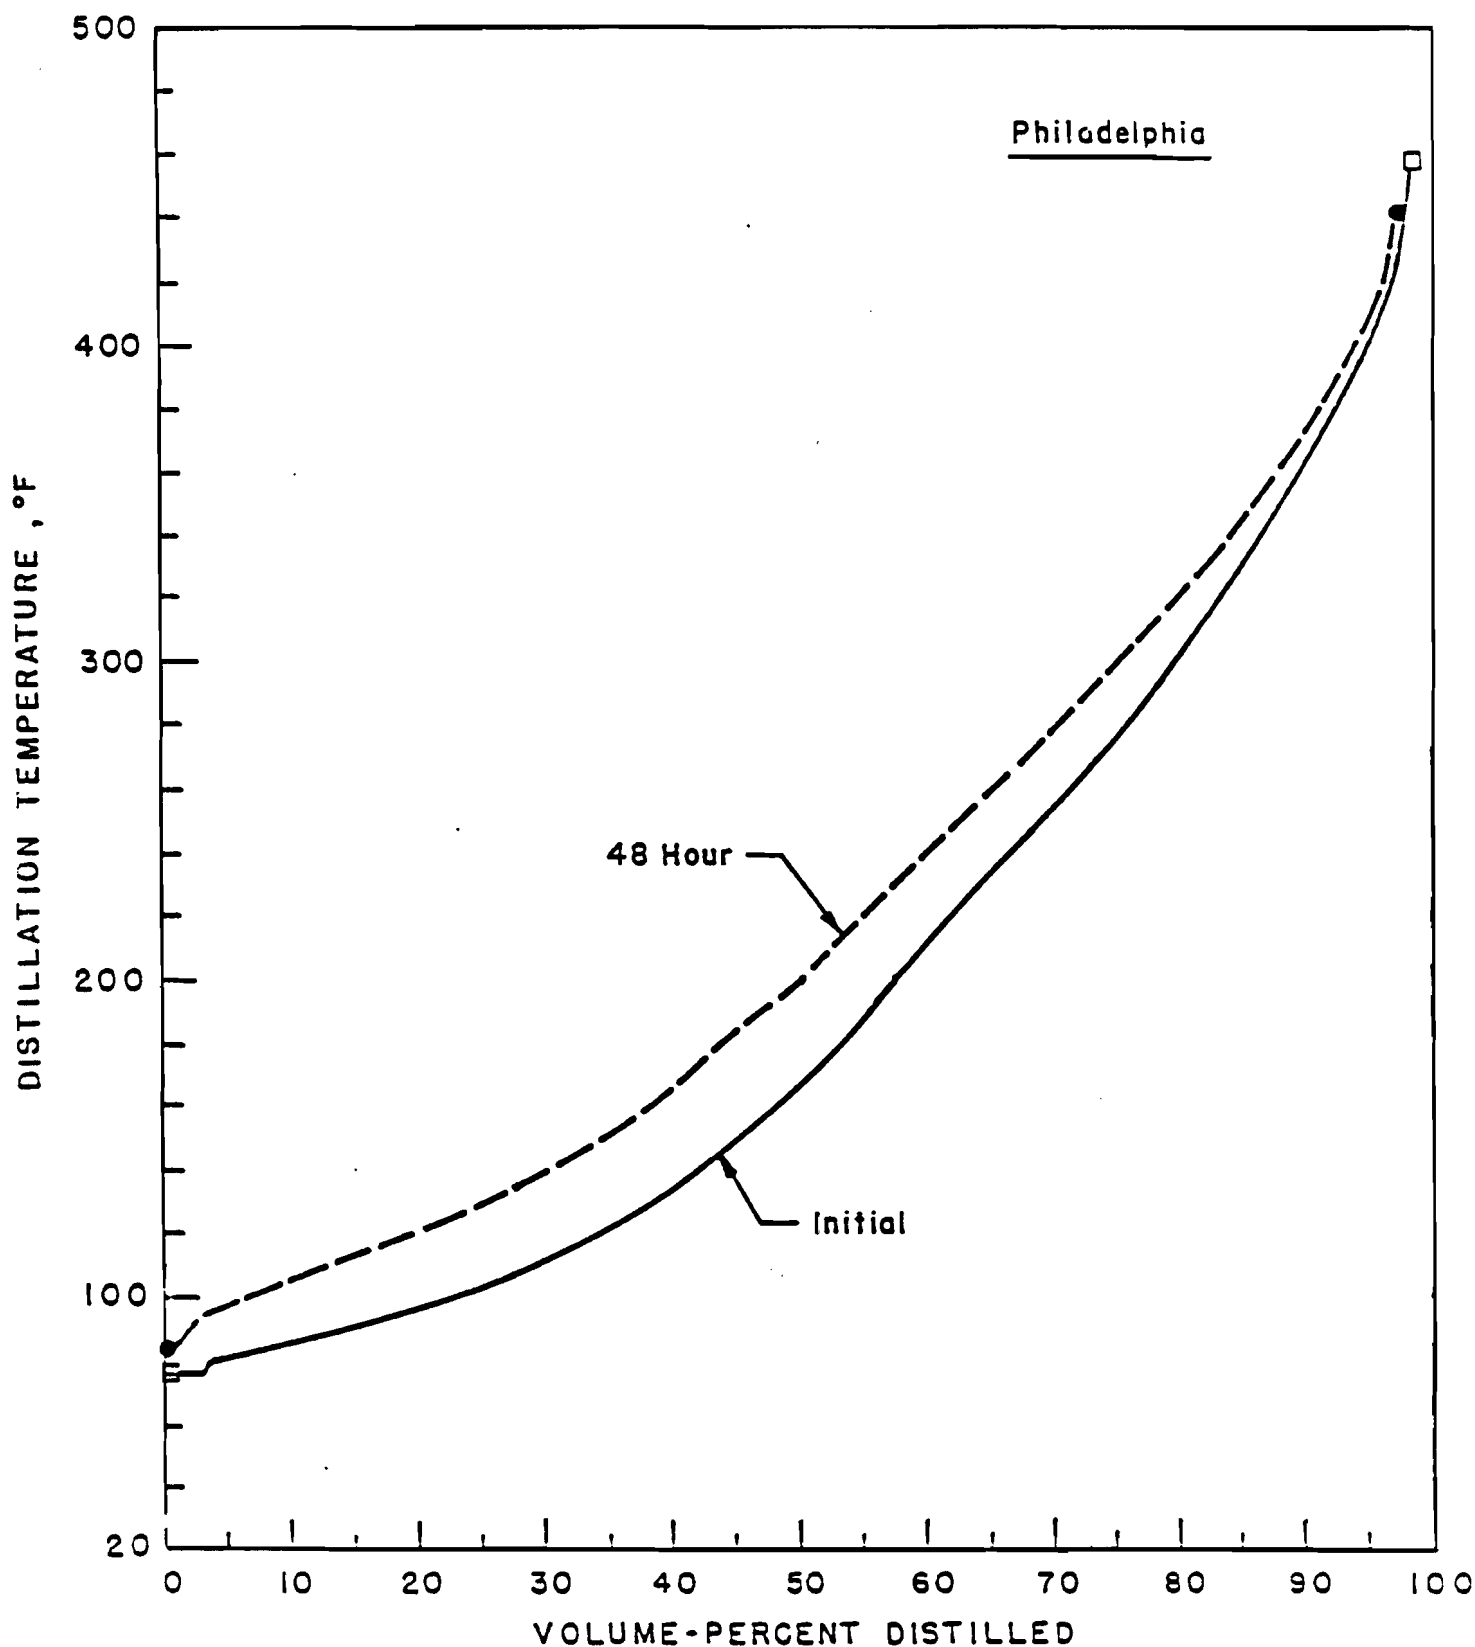


FIGURE 6. - Changes in distillation character due to weathering, winter fuels from Philadelphia.

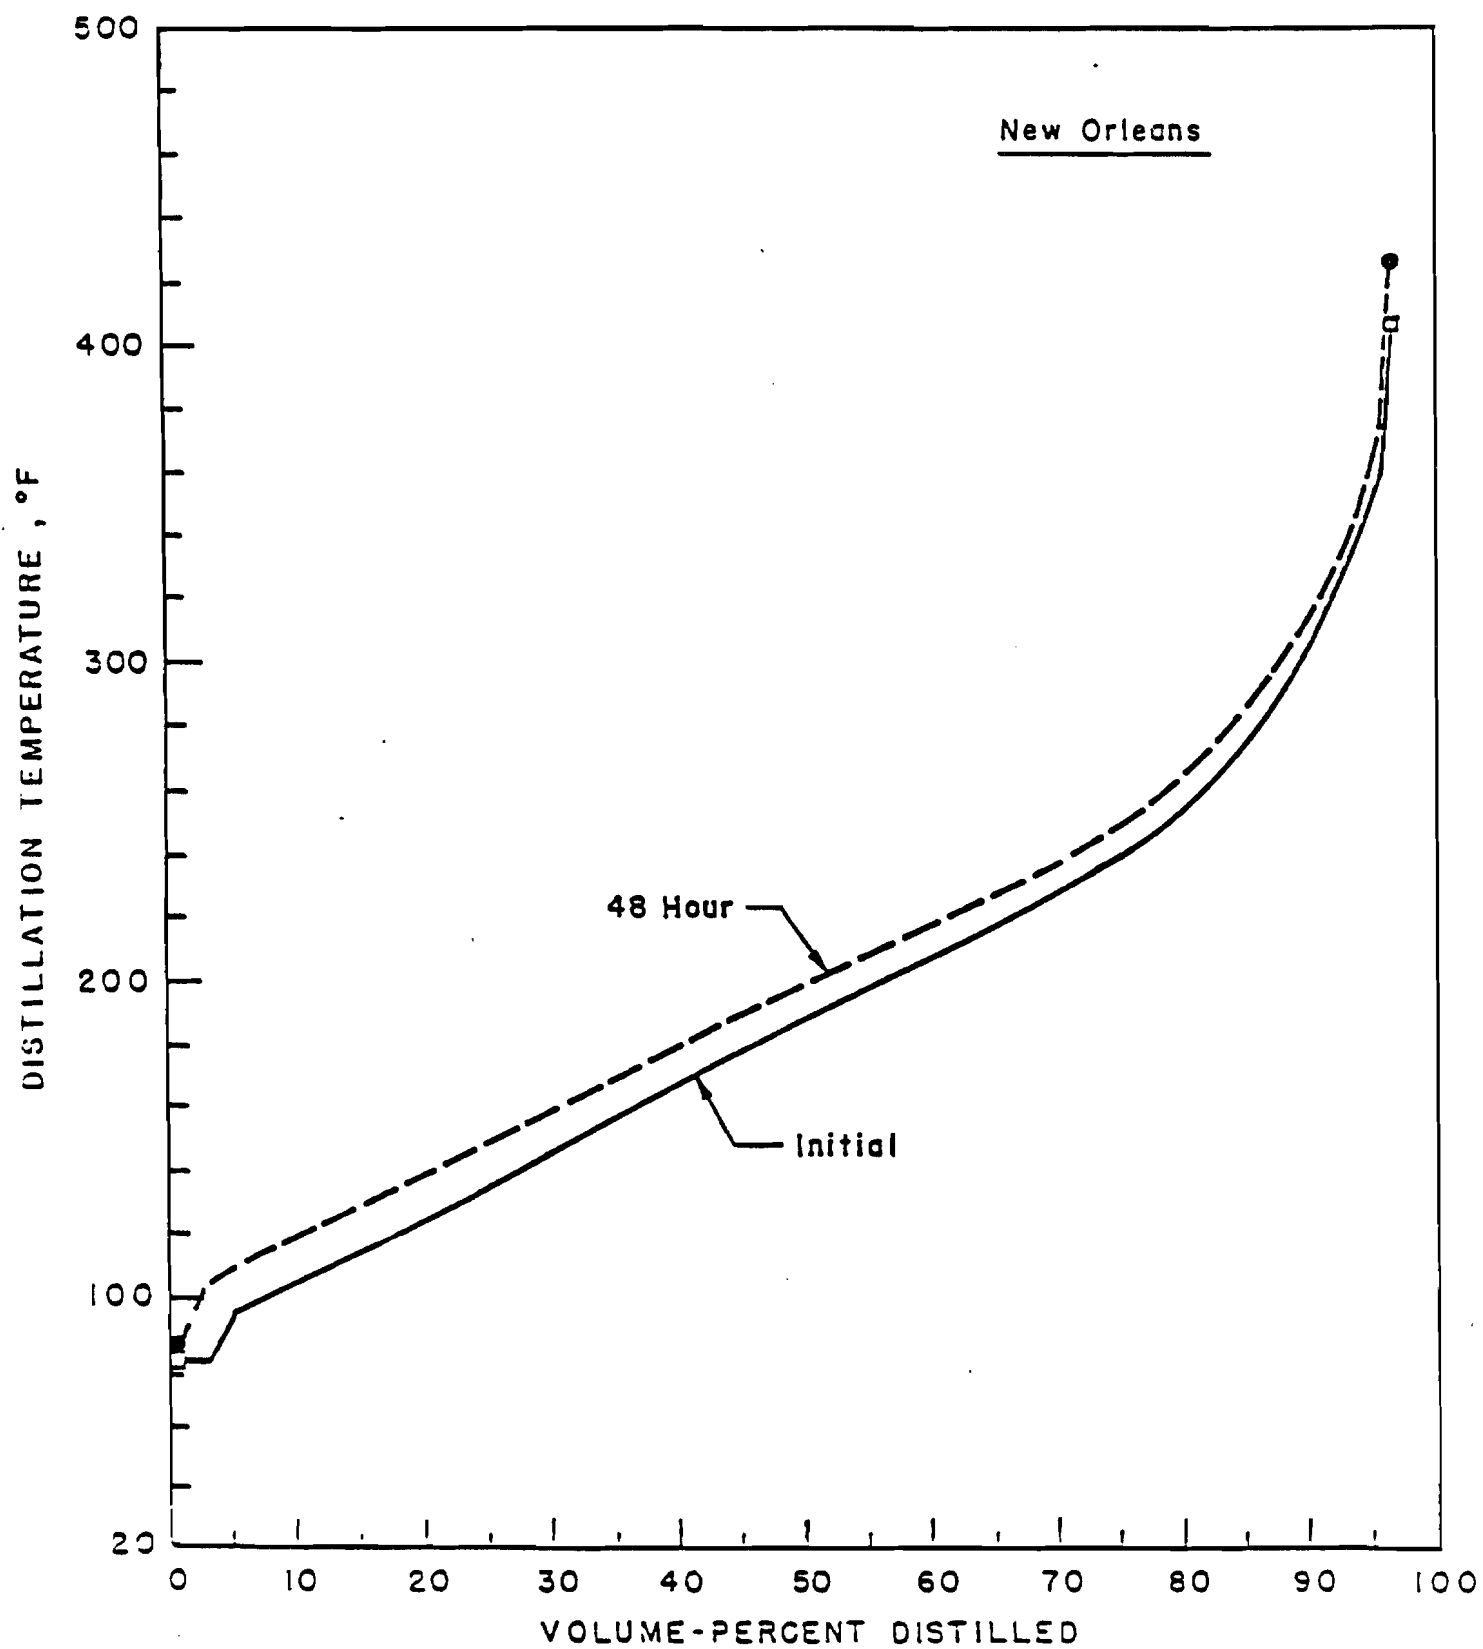


FIGURE 7. - Changes in distillation character due to weathering, winter fuels from New Orleans.



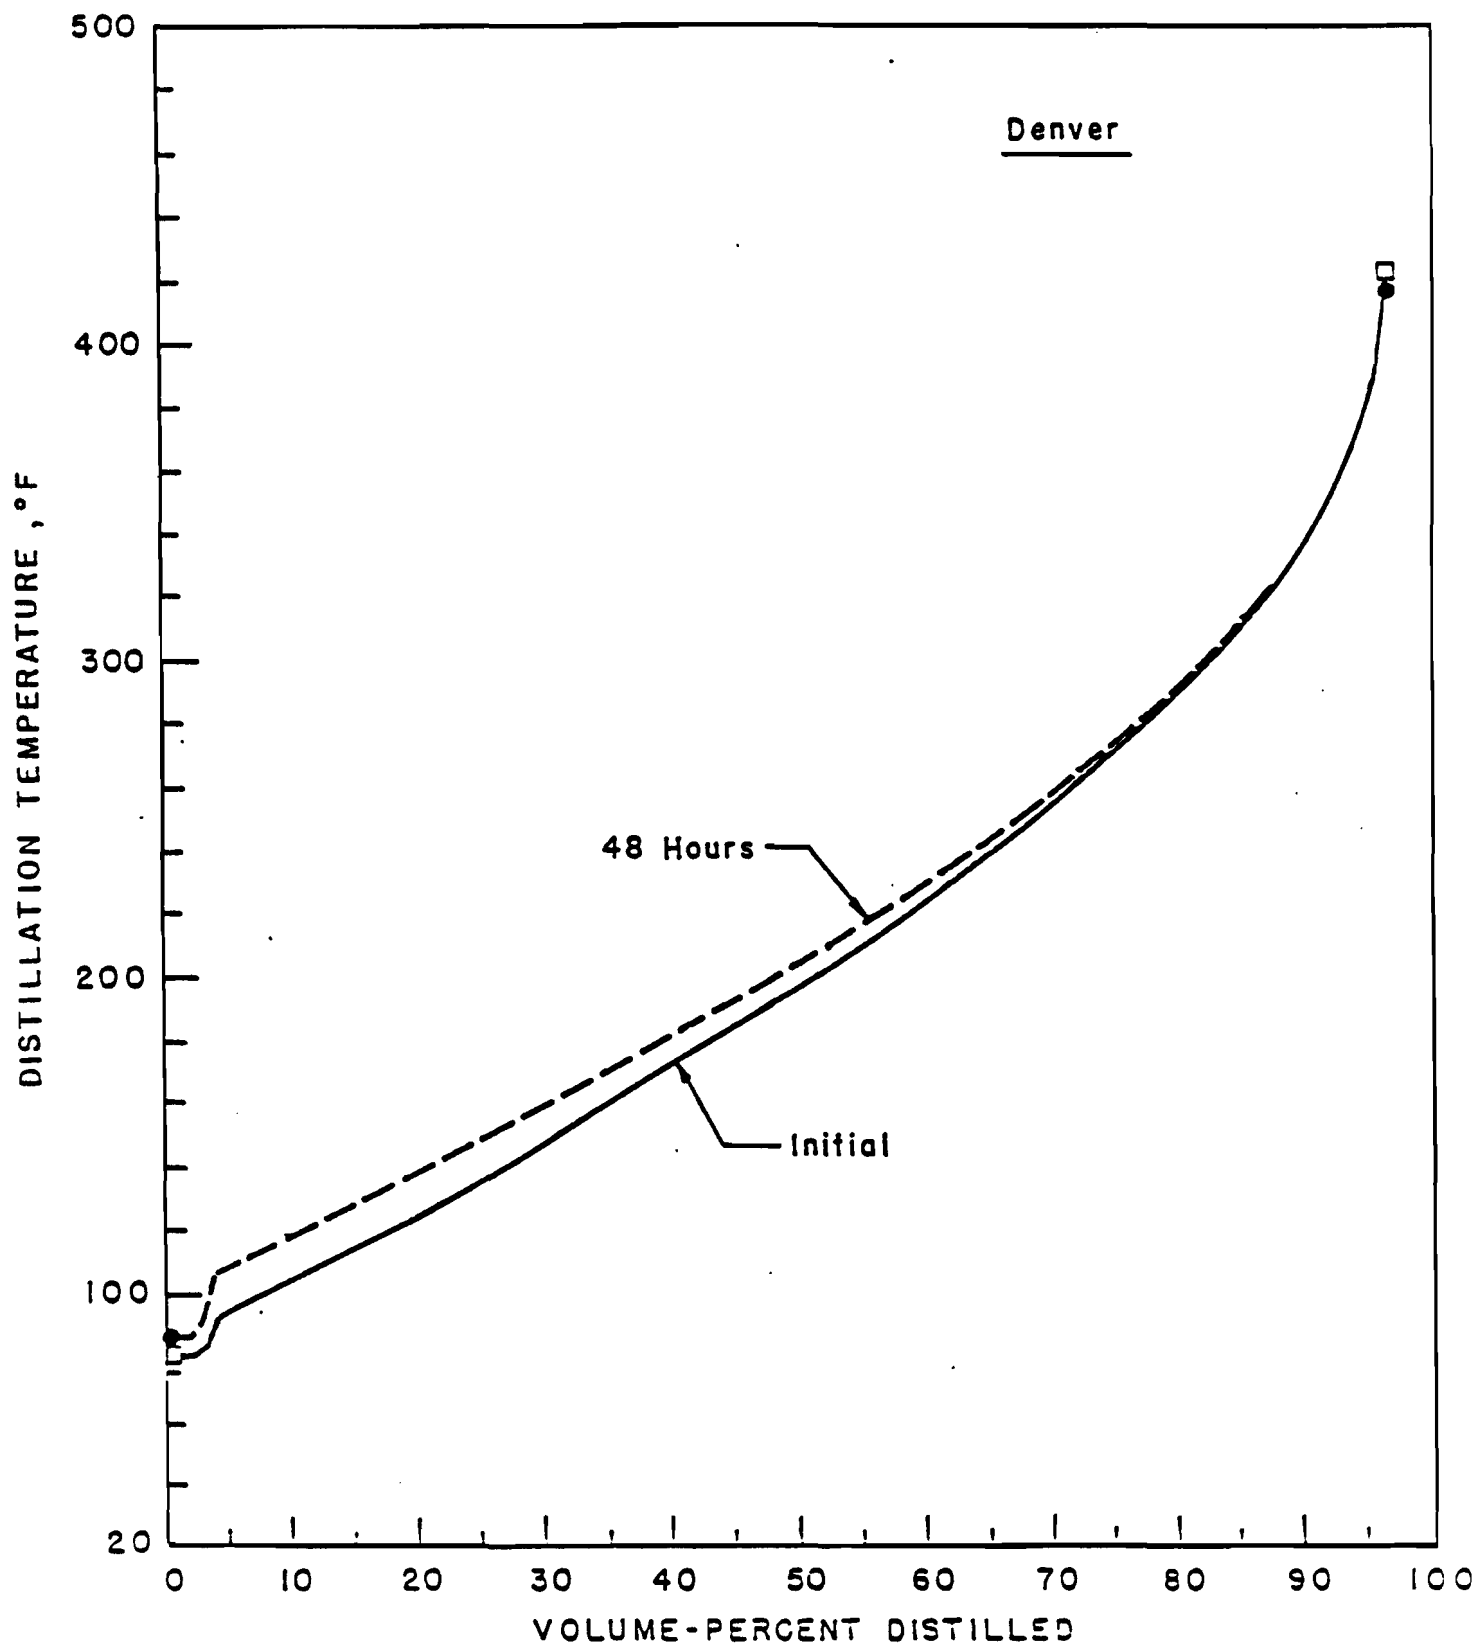


FIGURE 8. - Changes in distillation character due to weathering, winter fuels from Denver.

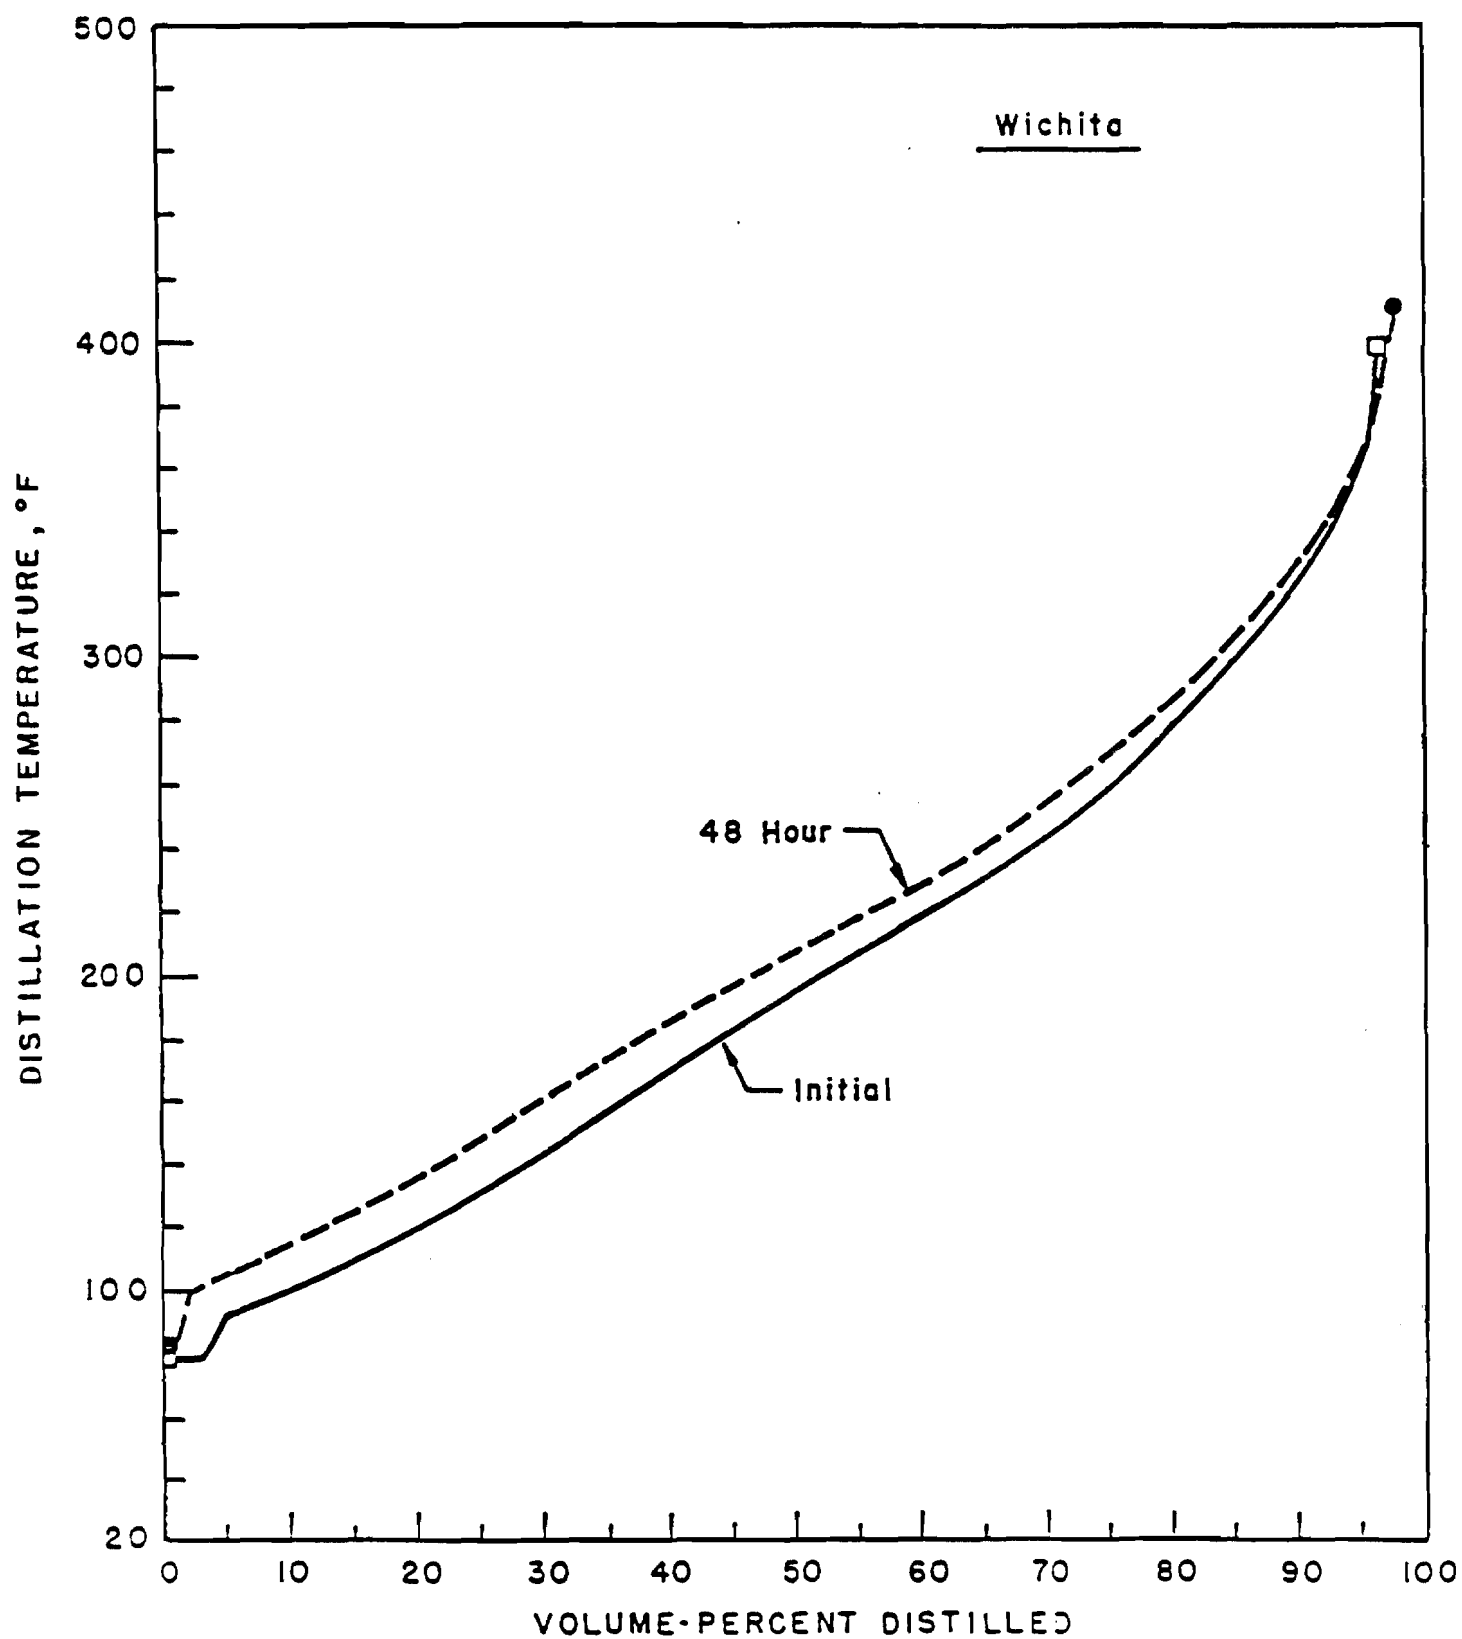


FIGURE 9. - Changes in distillation character due to weathering, winter fuels from Wichita.

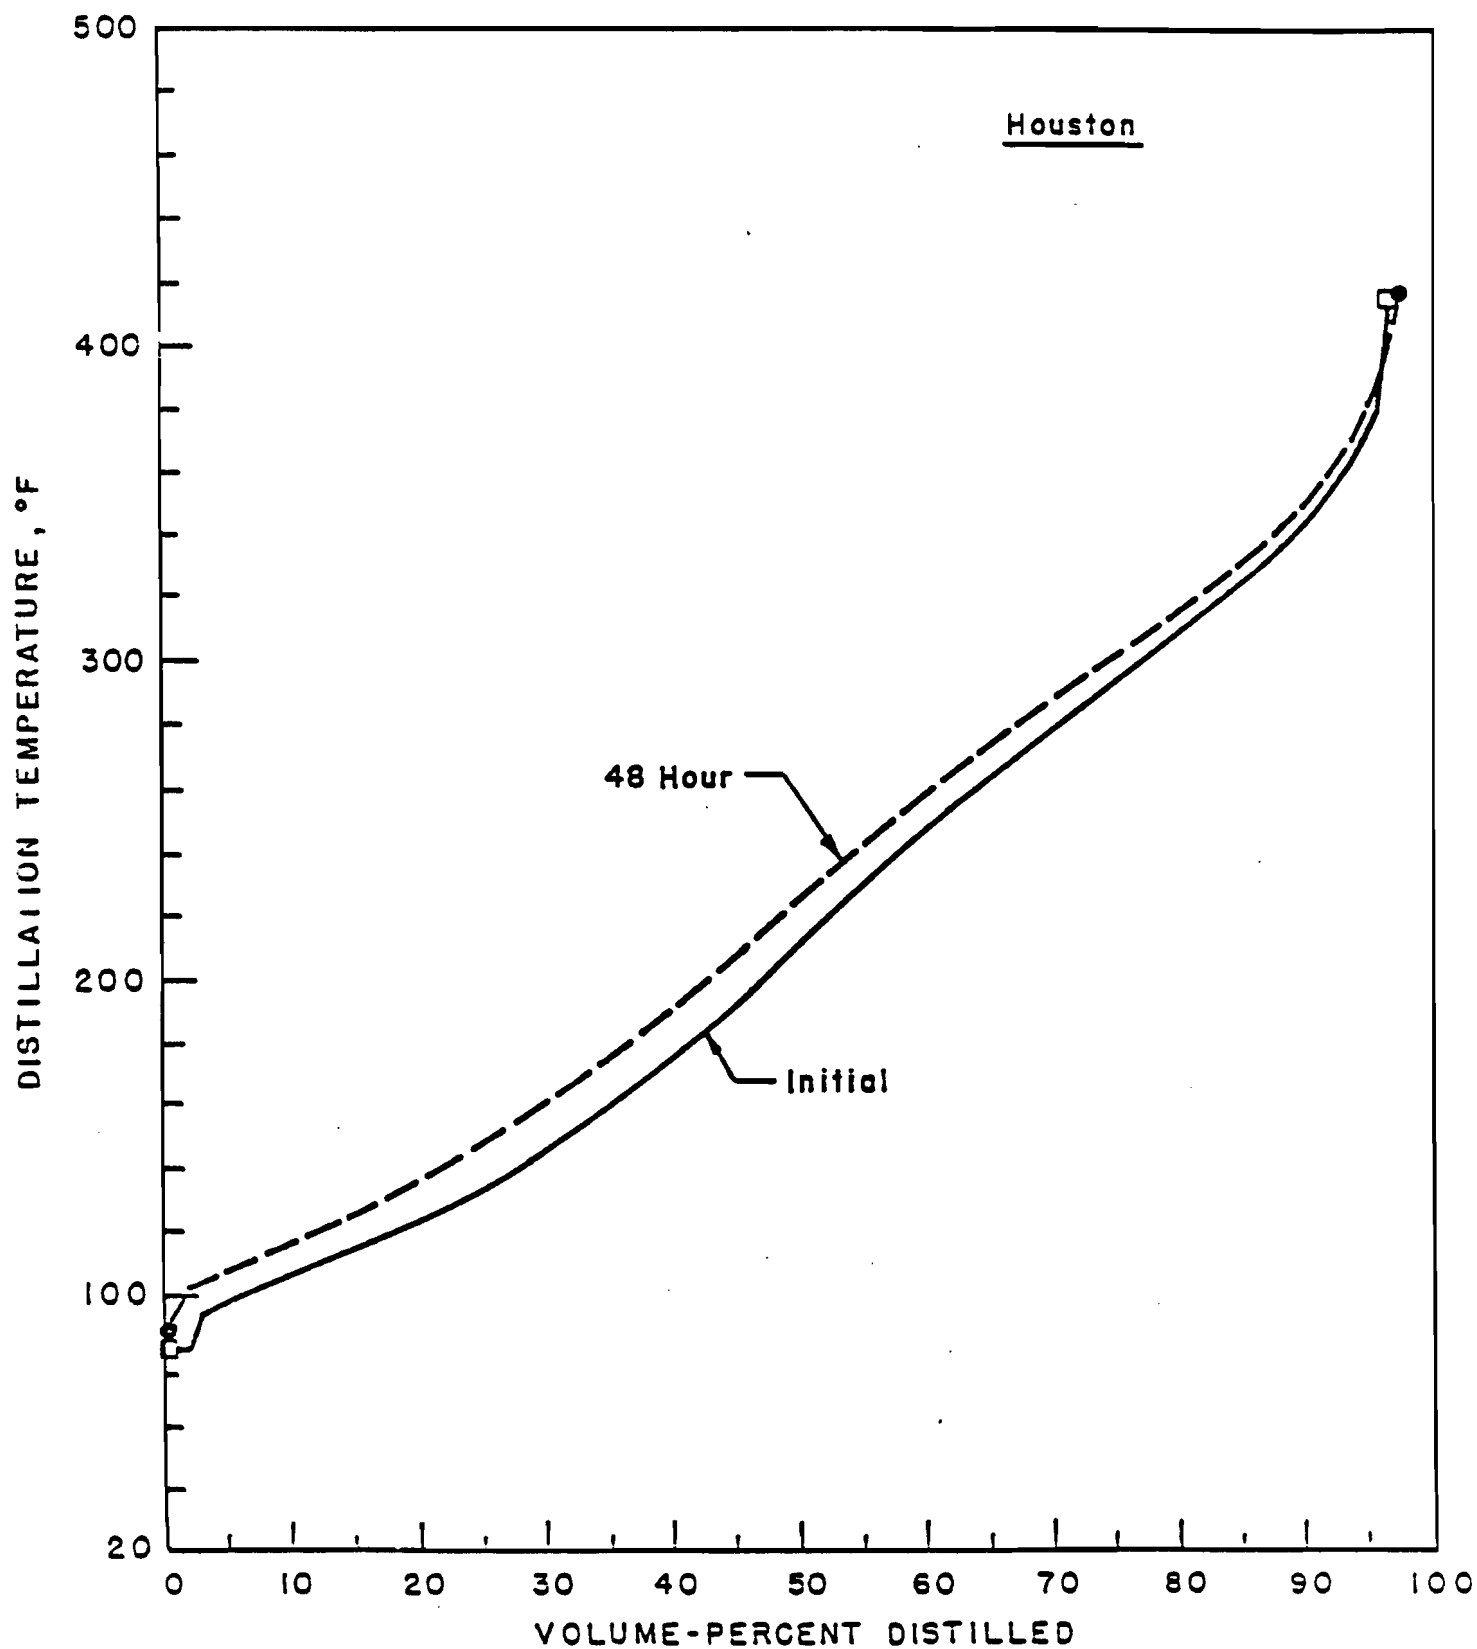


FIGURE 10. - Changes in distillation character due to weathering, winter fuels from Houston.

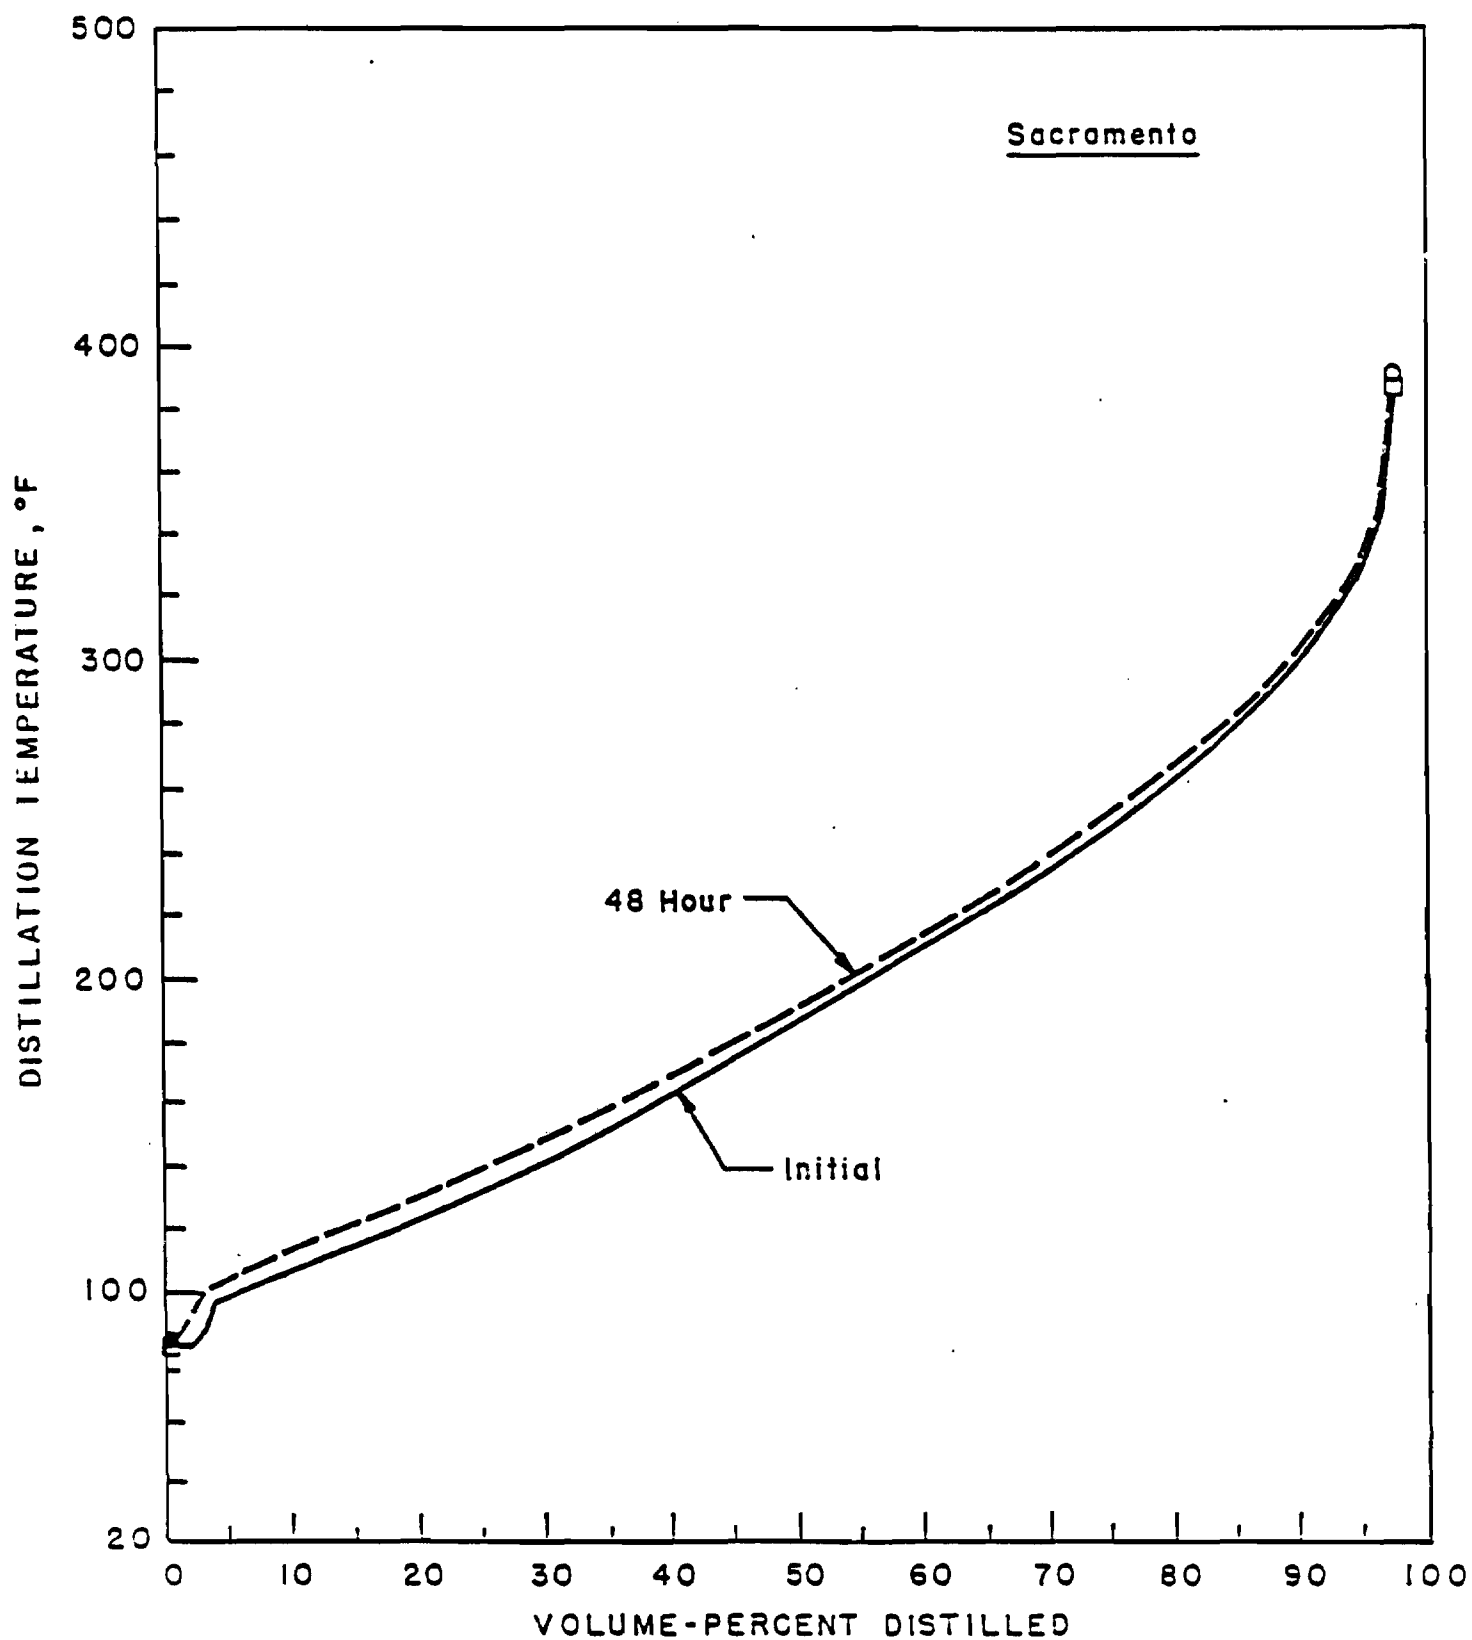


FIGURE 11. - Changes in distillation character due to weathering, winter fuels from Sacramento.

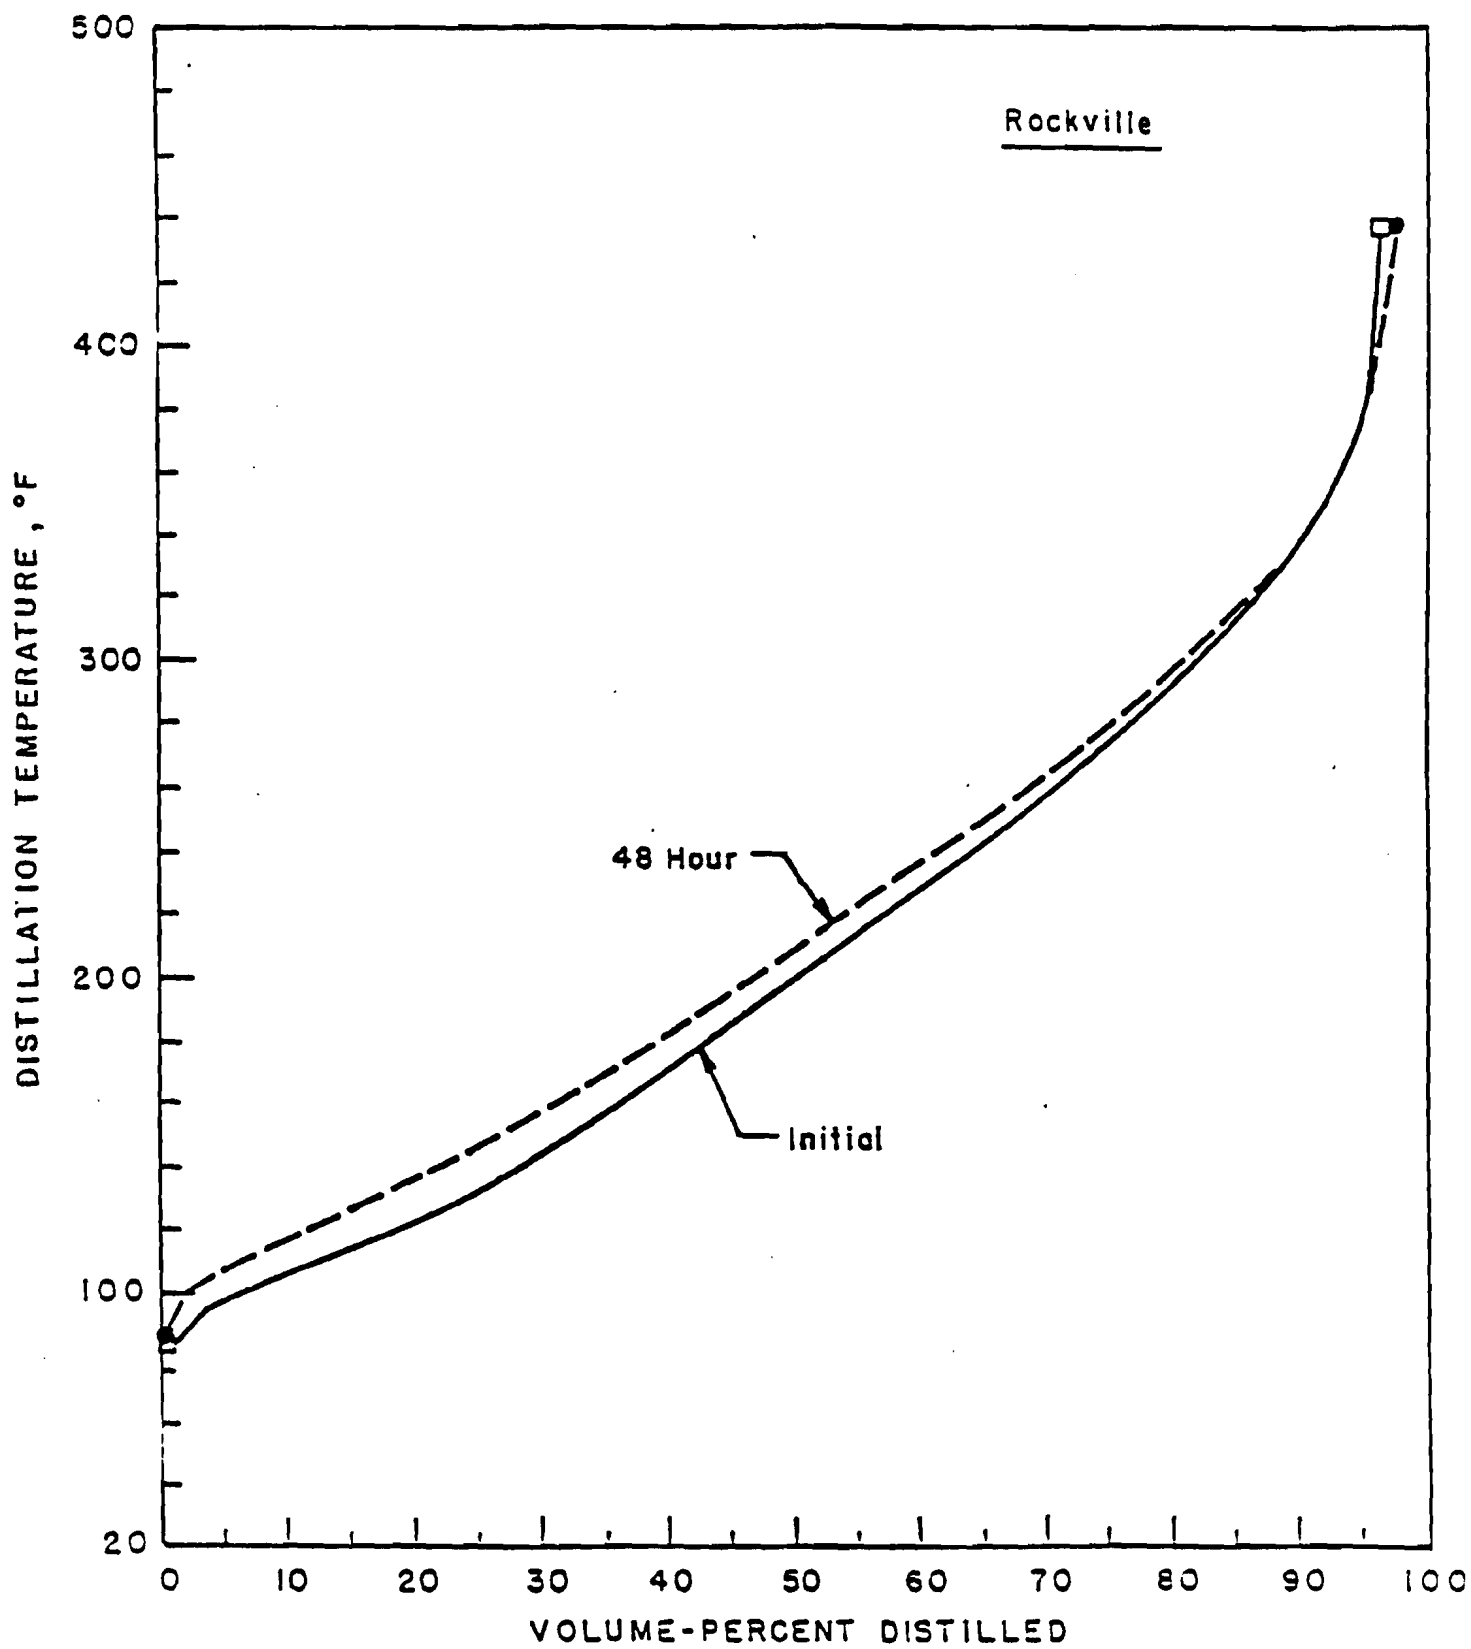


FIGURE 12. - Changes in distillation character due to weathering, winter fuels from Rockville.

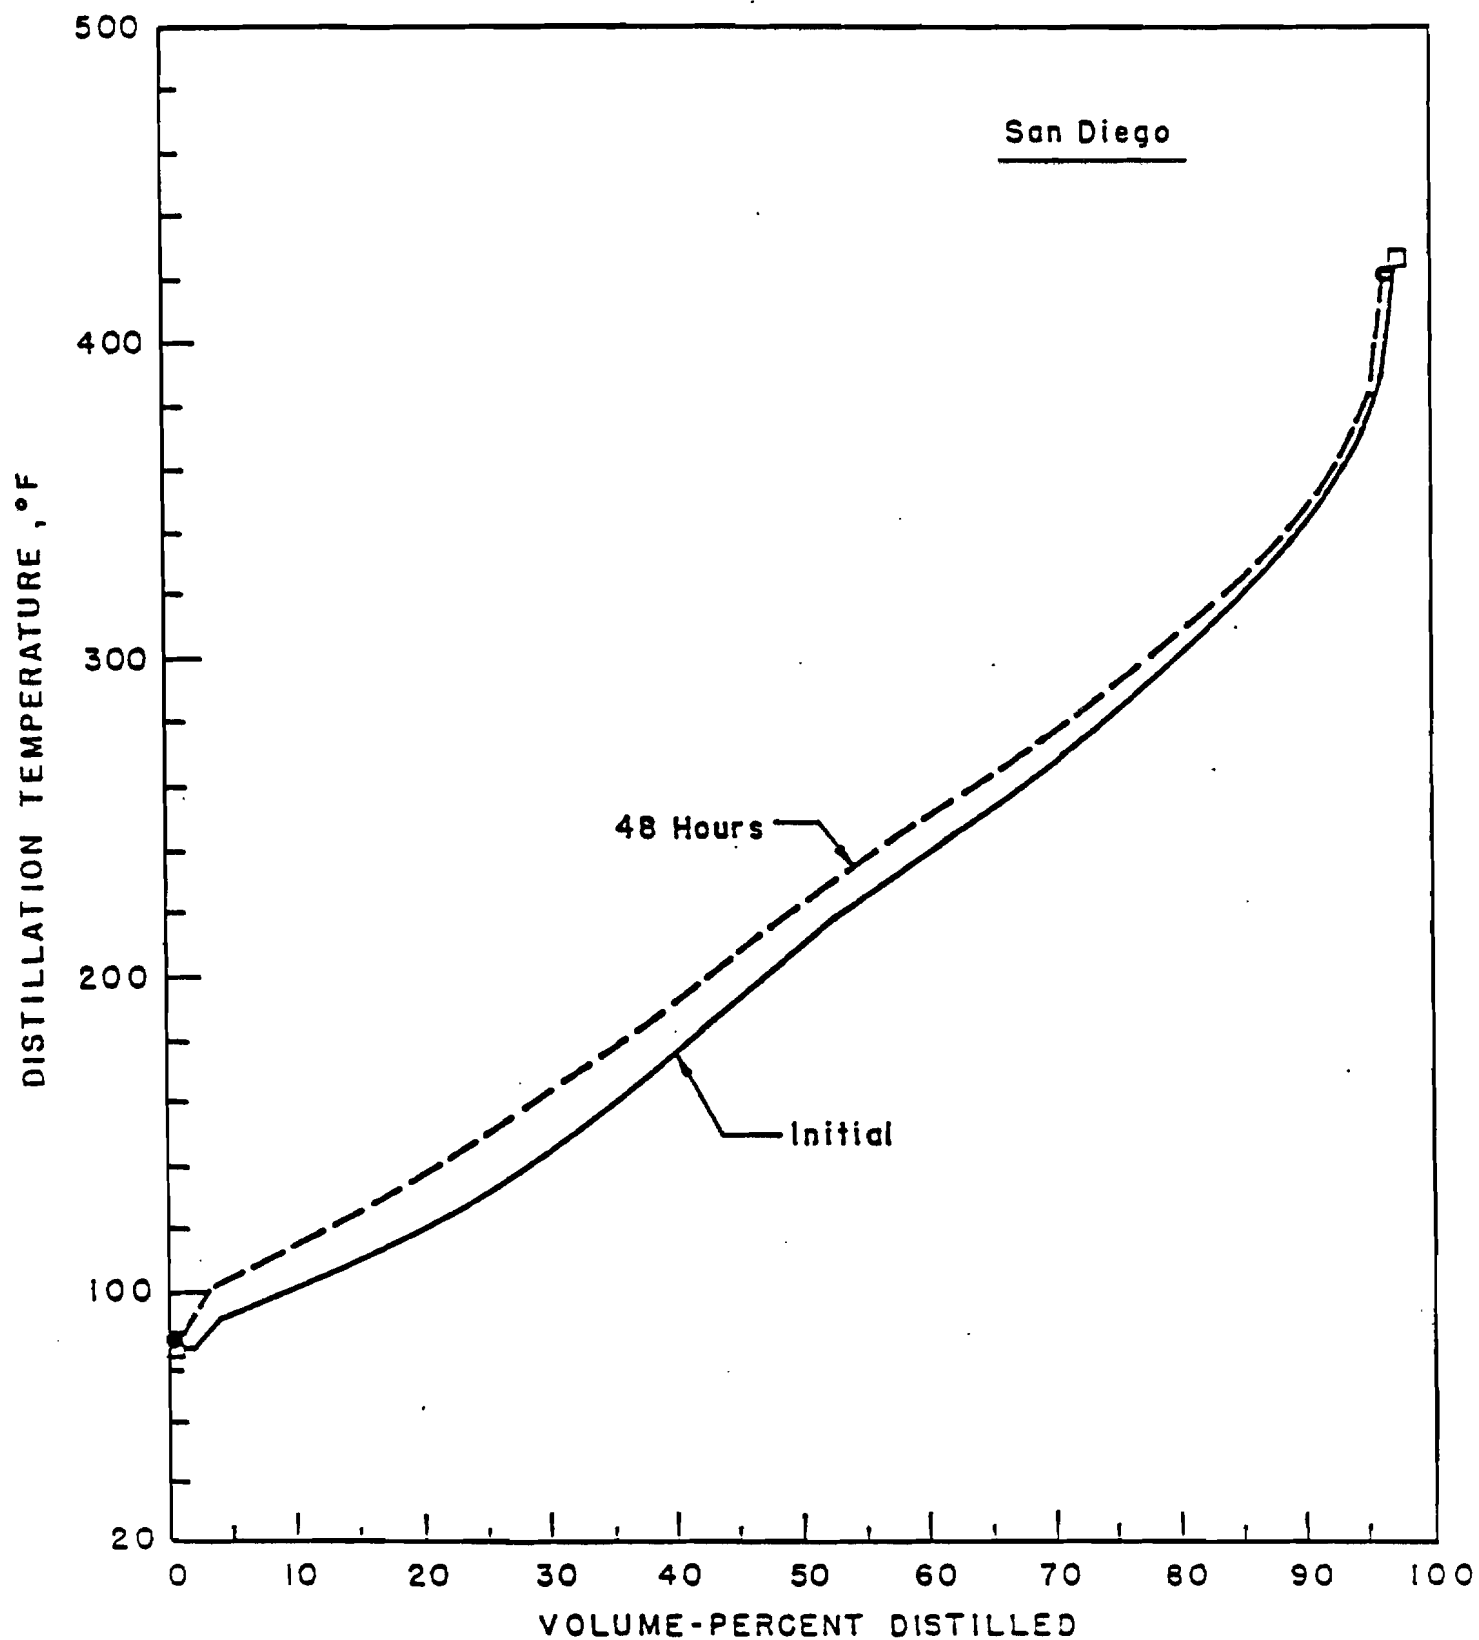


FIGURE 13. - Changes in distillation character due to weathering, winter fuels from San Diego.

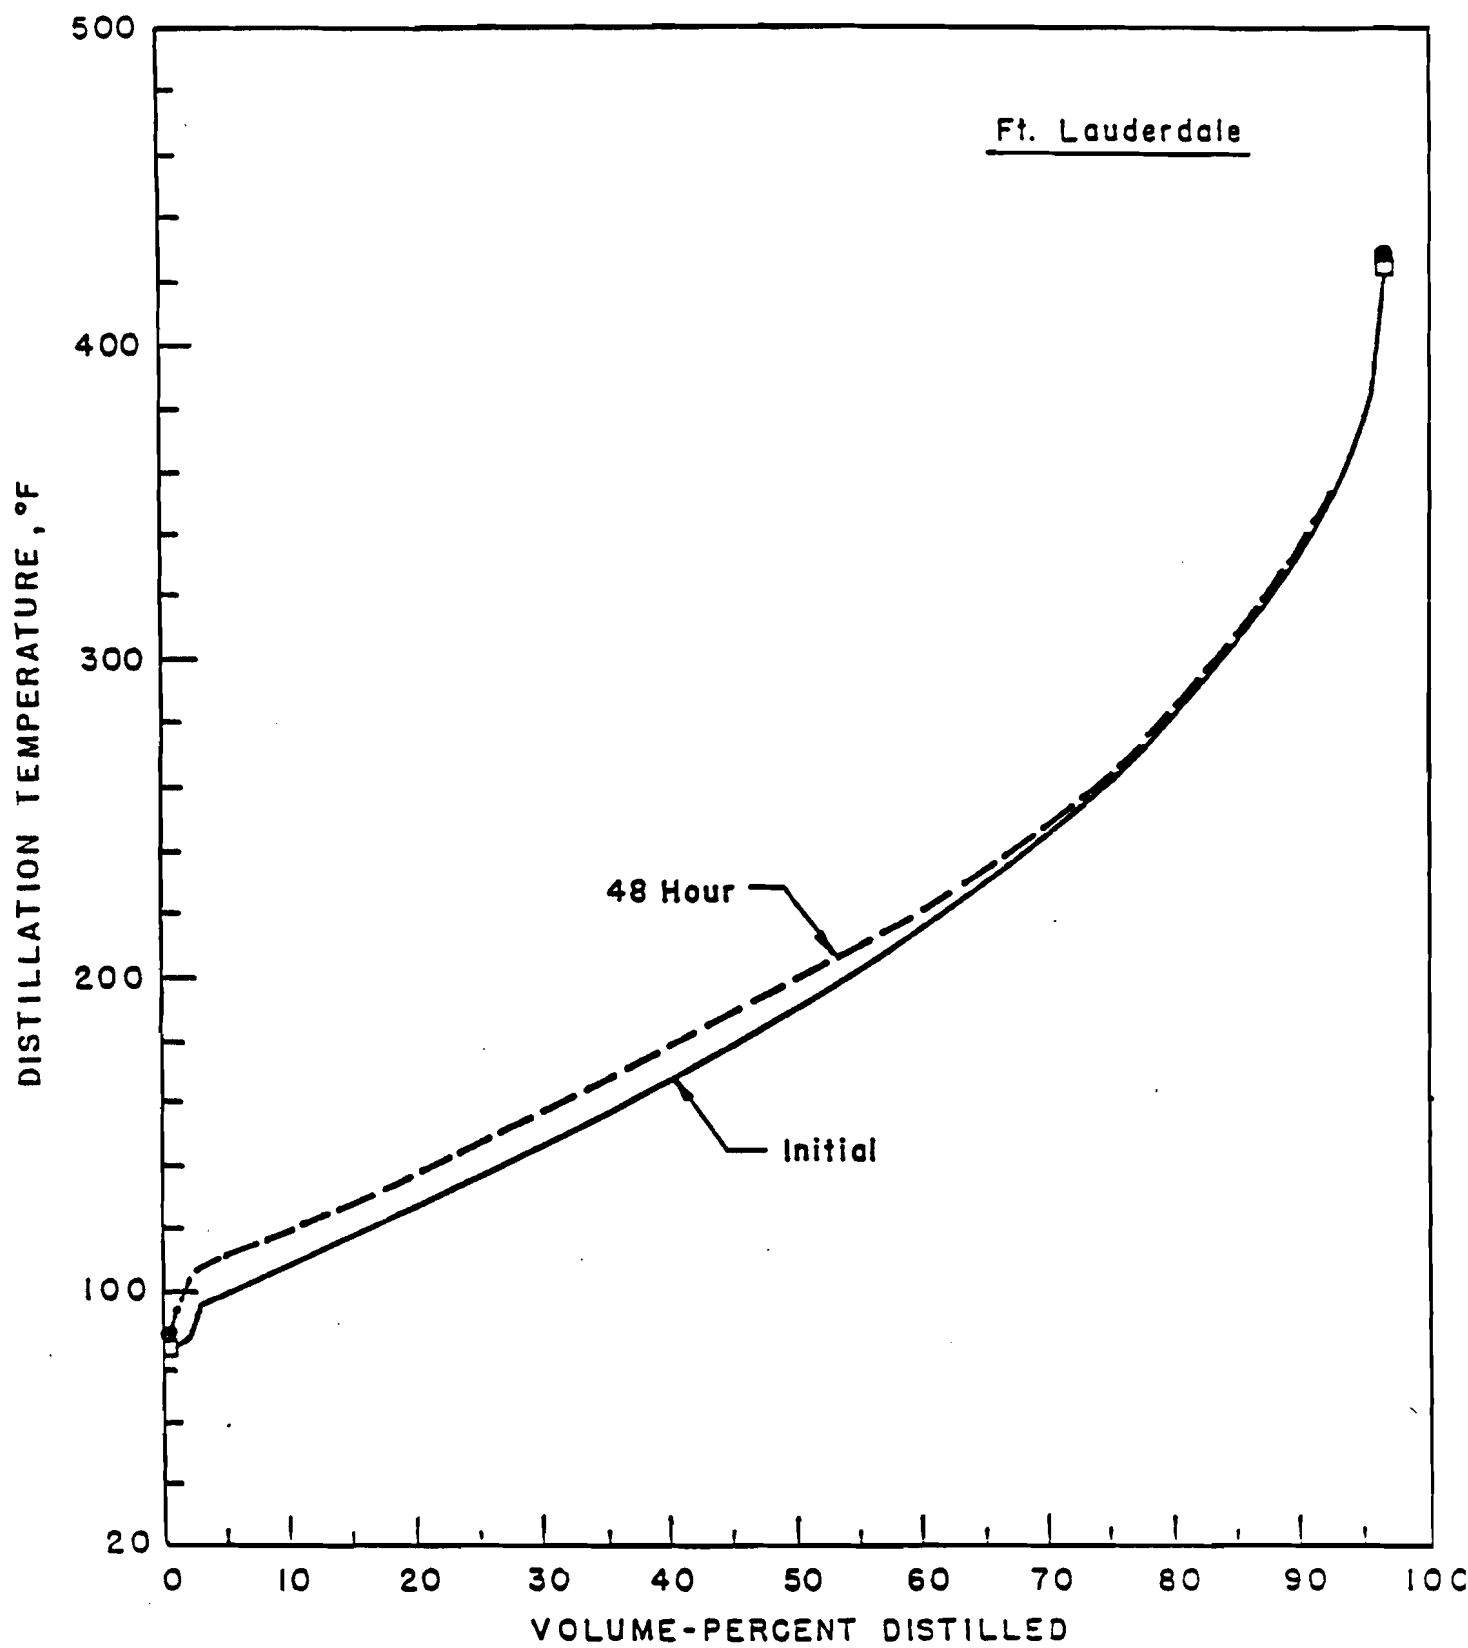


FIGURE 14. - Changes in distillation character due to weathering, winter fuels from Ft. Lauderdale.

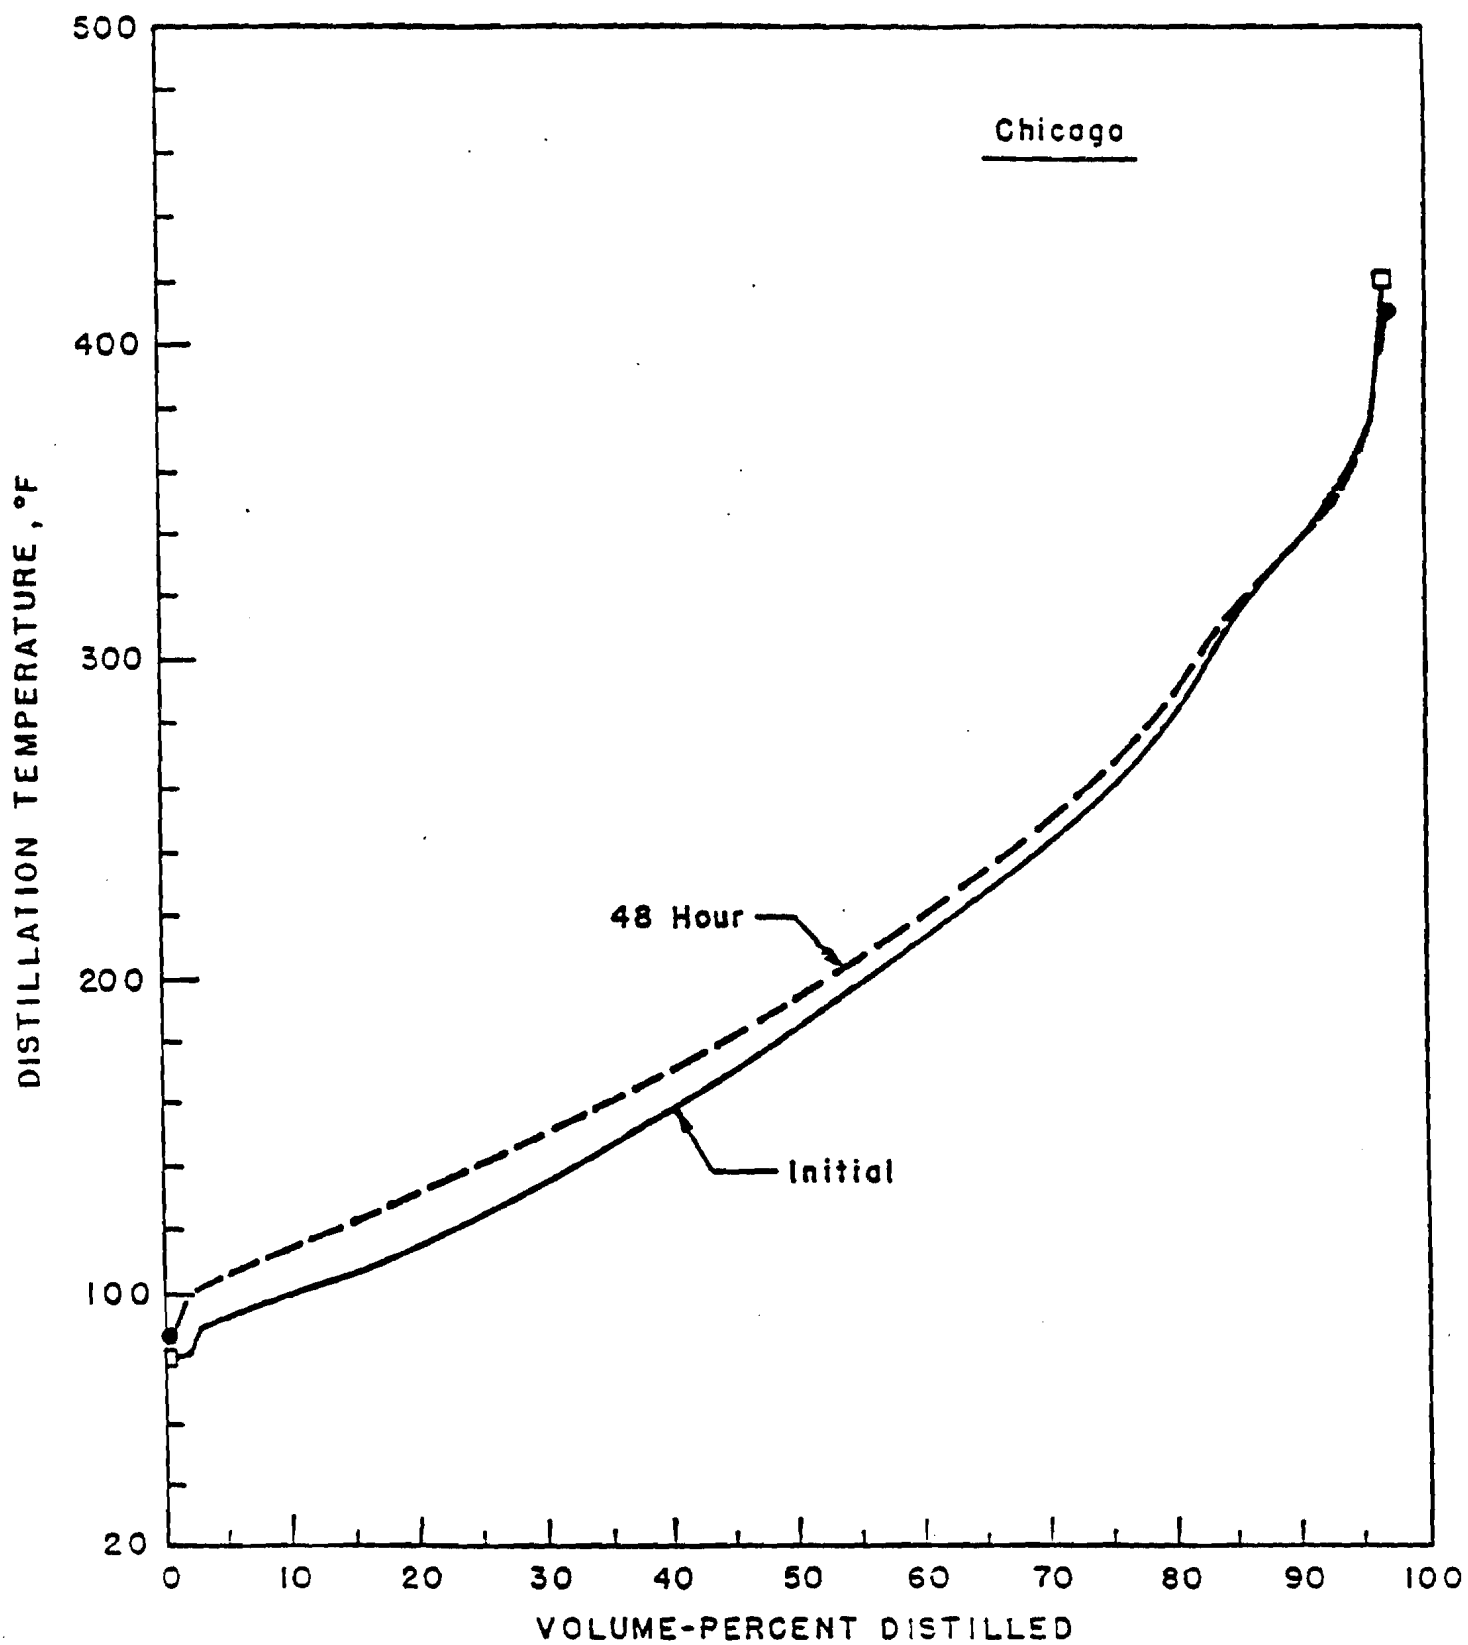


FIGURE 15. - Changes in distillation character due to weathering, winter fuels from Chicago.



TABLE 3. - Fuel composition summary - New Orleans - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.12           | 0.00                 | 0.00              | 0.02           | 0.00             | 0.13   |
| 4                                                            | 9.54           | 2.26                 | 0.00              | 0.88           | 0.00             | 12.69  |
| 5                                                            | 5.94           | 8.65                 | 0.12              | 4.52           | 0.00             | 19.23  |
| 6                                                            | 4.27           | 8.01                 | 1.42              | 1.51           | 1.03             | 16.24  |
| 7                                                            | 1.47           | 8.41                 | 2.10              | 2.68           | 3.68             | 18.33  |
| 8                                                            | 0.57           | 16.88                | 0.69              | 0.03           | 4.45             | 22.63  |
| 9                                                            | 0.12           | 2.83                 | 0.04              | 0.00           | 3.06             | 6.05   |
| 10                                                           | 0.05           | 2.20                 | 0.00              | 0.00           | 2.22             | 4.47   |
| 11                                                           | 0.05           | 0.02                 | 0.00              | 0.00           | 0.15             | 0.22   |
| 12                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 22.13          | 49.27                | 4.36              | 9.64           | 14.60            | 100.00 |

Average Molecular Weight = 88.64

Average Density - .702

Average Carbon Number = 6.29

H/C Ratio = 2.06

| <u>48 Hours</u> |               |                      |                   |                |                  |              |
|-----------------|---------------|----------------------|-------------------|----------------|------------------|--------------|
| Carbon No.      | <u>Normal</u> | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | <u>Total</u> |
| 1               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 2               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 3               | 0.05          | 0.00                 | 0.00              | 0.01           | 0.00             | 0.06         |
| 4               | 7.55          | 1.59                 | 0.00              | 0.70           | 0.00             | 9.85         |
| 5               | 5.65          | 8.00                 | 0.11              | 4.57           | 0.00             | 18.33        |
| 6               | 4.26          | 7.93                 | 1.43              | 1.53           | 1.11             | 16.25        |
| 7               | 1.50          | 8.45                 | 2.10              | 2.72           | 4.01             | 18.78        |
| 8               | 0.59          | 19.48                | 0.87              | 0.04           | 4.61             | 25.59        |
| 9               | 0.12          | 3.14                 | 0.00              | 0.00           | 3.19             | 6.45         |
| 10              | 0.05          | 2.28                 | 0.00              | 0.00           | 2.15             | 4.48         |
| 11              | 0.05          | 0.02                 | 0.00              | 0.00           | 0.14             | 0.21         |
| 12              | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| Total           | 19.82         | 50.87                | 4.51              | 9.57           | 15.21            | 100.00       |

Average Molecular Weight = 90.69

Average Density - .708

Average Carbon Number = 6.44

H/C Ratio = 2.04

TABLE 4. - Fuel composition summary - Chicago - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.17           | 0.00                 | 0.00              | 0.02           | 0.00             | 0.18   |
| 4                                                            | 11.68          | 1.57                 | 0.00              | 1.35           | 0.00             | 14.60  |
| 5                                                            | 6.23           | 10.56                | 0.19              | 4.29           | 0.00             | 21.28  |
| 6                                                            | 3.12           | 11.44                | 2.57              | 1.74           | 1.76             | 20.63  |
| 7                                                            | 1.73           | 4.56                 | 1.26              | 2.07           | 9.02             | 18.65  |
| 8                                                            | 0.58           | 5.75                 | 1.17              | 0.10           | 3.18             | 10.78  |
| 9                                                            | 0.14           | 1.04                 | 0.00              | 0.00           | 7.56             | 8.73   |
| 10                                                           | 0.10           | 0.20                 | 0.00              | 0.00           | 4.22             | 4.53   |
| 11                                                           | 0.10           | 0.03                 | 0.00              | 0.00           | 0.49             | 0.62   |
| 12                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 23.85          | 35.15                | 5.19              | 9.58           | 26.23            | 100.00 |

Average Molecular Weight = 85.92

Average Density - .715

Average Carbon Number = 6.16

H/C Ratio = 1.93

48 Hours

| Carbon No. | <u>48 Hours</u> |                      |                   |                |                  | Total  |
|------------|-----------------|----------------------|-------------------|----------------|------------------|--------|
|            | <u>Normal</u>   | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1          | 0.00            | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2          | 0.00            | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3          | 0.05            | 0.00                 | 0.00              | 0.00           | 0.00             | 0.05   |
| 4          | 7.98            | 0.88                 | 0.00              | 0.93           | 0.00             | 9.79   |
| 5          | 5.82            | 9.48                 | 0.19              | 4.01           | 0.00             | 19.49  |
| 6          | 4.19            | 11.73                | 2.78              | 2.49           | 1.87             | 23.06  |
| 7          | 1.88            | 4.96                 | 1.37              | 2.28           | 9.89             | 20.39  |
| 8          | 0.63            | 6.41                 | 0.77              | 0.11           | 3.55             | 11.48  |
| 9          | 0.15            | 1.23                 | 0.00              | 0.00           | 8.35             | 9.74   |
| 10         | 0.12            | 0.26                 | 0.00              | 0.00           | 4.75             | 5.12   |
| 11         | 0.11            | 0.03                 | 0.00              | 0.00           | 0.73             | 0.87   |
| 12         | 0.00            | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total      | 20.93           | 34.98                | 5.11              | 9.82           | 29.14            | 100.00 |

Average Molecular Weight = 88.87

Average Density - .727

Average Carbon Number = 6.39

H/C Ratio = 1.88

TABLE 5. - Fuel composition summary - Ft. Lauderdale - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.14           | 0.00                 | 0.00              | 0.05           | 0.00             | 0.19   |
| 4                                                            | 8.12           | 1.59                 | 0.00              | 1.20           | 0.00             | 10.92  |
| 5                                                            | 5.78           | 10.71                | 0.17              | 4.19           | 0.00             | 20.85  |
| 6                                                            | 3.40           | 10.87                | 2.64              | 3.04           | 2.29             | 22.25  |
| 7                                                            | 1.66           | 5.75                 | 1.52              | 2.59           | 8.31             | 19.83  |
| 8                                                            | 0.45           | 5.92                 | 0.77              | 0.06           | 6.45             | 13.65  |
| 9                                                            | 0.12           | 1.63                 | 0.02              | 0.00           | 6.09             | 7.86   |
| 10                                                           | 0.08           | 0.25                 | 0.00              | 0.00           | 3.67             | 4.00   |
| 11                                                           | 0.07           | 0.00                 | 0.00              | 0.00           | 0.40             | 0.46   |
| 12                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 19.81          | 36.73                | 5.12              | 11.13          | 27.21            | 100.00 |

Average Molecular Weight = 87.39

Average Density - .720

Average Carbon Number = 6.27

H/C Ratio = 1.90

| <u>48 Hours</u> |               |                      |                   |                |                  |              |
|-----------------|---------------|----------------------|-------------------|----------------|------------------|--------------|
| Carbon No.      | <u>Normal</u> | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | <u>Total</u> |
| 1               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 2               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 3               | 0.06          | 0.00                 | 0.00              | 0.02           | 0.00             | 0.08         |
| 4               | 5.41          | 1.10                 | 0.00              | 0.92           | 0.00             | 7.43         |
| 5               | 5.42          | 10.00                | 0.17              | 4.03           | 0.00             | 19.61        |
| 6               | 3.37          | 10.79                | 2.72              | 3.25           | 2.56             | 22.68        |
| 7               | 1.71          | 6.44                 | 1.75              | 2.88           | 8.46             | 21.24        |
| 8               | 0.42          | 6.32                 | 0.89              | 0.08           | 8.12             | 15.83        |
| 9               | 0.12          | 2.10                 | 0.06              | 0.00           | 5.86             | 8.14         |
| 10              | 0.07          | 0.37                 | 0.00              | 0.00           | 3.59             | 4.03         |
| 11              | 0.05          | 0.13                 | 0.00              | 0.00           | 0.72             | 0.90         |
| 12              | 0.00          | 0.00                 | 0.00              | 0.00           | 0.05             | 0.05         |
| Total           | 16.61         | 37.25                | 5.59              | 11.19          | 29.36            | 100.00       |

Average Molecular Weight = 89.78

Average Density - .730

Average Carbon Number = 6.46

H/C Ratio = 1.87

TABLE 6. - Fuel composition summary - Philadelphia - winter

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                         |                   |                |                  | <u>Total</u> |
|---------------|----------------|-------------------------|-------------------|----------------|------------------|--------------|
|               | <u>Normal</u>  | Paraffins<br><u>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1             | 0.00           | 0.00                    | 0.00              | 0.00           | 0.00             | 0.00         |
| 2             | 0.00           | 0.00                    | 0.00              | 0.00           | 0.00             | 0.00         |
| 3             | 0.06           | 0.00                    | 0.00              | 0.01           | 0.00             | 0.07         |
| 4             | 9.23           | 3.19                    | 0.00              | 5.09           | 0.00             | 17.51        |
| 5             | 9.55           | 12.86                   | 0.24              | 6.77           | 0.00             | 29.43        |
| 6             | 1.70           | 6.46                    | 1.61              | 5.27           | 0.44             | 15.49        |
| 7             | 0.85           | 2.90                    | 1.42              | 3.62           | 3.50             | 12.29        |
| 8             | 0.37           | 3.34                    | 1.65              | 0.16           | 5.21             | 10.74        |
| 9             | 0.14           | 2.89                    | 0.09              | 0.00           | 4.96             | 8.08         |
| 10            | 0.11           | 0.70                    | 0.00              | 0.00           | 3.97             | 4.78         |
| 11            | 0.15           | 0.08                    | 0.00              | 0.00           | 0.89             | 1.13         |
| 12            | 0.15           | 0.16                    | 0.00              | 0.00           | 0.18             | 0.48         |
| Total         | 22.31          | 32.59                   | 5.02              | 20.93          | 19.15            | 100.00       |

Average Molecular Weight = 83.51

Average Density - .699

Average Carbon Number = 5.96

H/C Ratio = 1.99

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                         |                   |                |                  | <u>Total</u> |
|---------------|-----------------|-------------------------|-------------------|----------------|------------------|--------------|
|               | <u>Normal</u>   | Paraffins<br><u>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1             | 0.00            | 0.00                    | 0.00              | 0.00           | 0.00             | 0.00         |
| 2             | 0.00            | 0.00                    | 0.00              | 0.00           | 0.00             | 0.00         |
| 3             | 0.01            | 0.00                    | 0.00              | 0.00           | 0.00             | 0.01         |
| 4             | 4.77            | 1.13                    | 0.00              | 2.60           | 0.00             | 8.50         |
| 5             | 8.95            | 11.01                   | 0.25              | 6.31           | 0.00             | 26.53        |
| 6             | 1.93            | 7.08                    | 1.86              | 5.95           | 0.51             | 17.33        |
| 7             | 1.04            | 3.46                    | 1.75              | 4.34           | 4.40             | 14.98        |
| 8             | 0.39            | 4.21                    | 2.16              | 0.26           | 6.47             | 13.48        |
| 9             | 0.17            | 3.61                    | 0.12              | 0.00           | 6.33             | 10.23        |
| 10            | 0.14            | 0.96                    | 0.00              | 0.00           | 4.99             | 6.08         |
| 11            | 0.20            | 0.08                    | 0.00              | 0.00           | 1.69             | 1.97         |
| 12            | 0.19            | 0.00                    | 0.00              | 0.00           | 0.70             | 0.90         |
| Total         | 17.78           | 31.54                   | 6.13              | 19.46          | 25.09            | 100.00       |

Average Molecular Weight = 89.77

Average Density - .723

Average Carbon Number = 6.44

H/C Ratio = 1.91

TABLE 7. - Fuel composition summary - San Diego - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.12           | 0.00                 | 0.00              | 0.03           | 0.00             | 0.15   |
| 4                                                            | 7.41           | 3.97                 | 0.00              | 0.74           | 0.00             | 12.12  |
| 5                                                            | 4.64           | 10.29                | 0.19              | 4.84           | 0.00             | 19.96  |
| 6                                                            | 2.57           | 7.20                 | 2.33              | 3.22           | 1.25             | 16.57  |
| 7                                                            | 1.37           | 4.68                 | 3.17              | 0.54           | 6.28             | 16.05  |
| 8                                                            | 0.78           | 6.61                 | 1.22              | 0.01           | 9.12             | 17.75  |
| 9                                                            | 0.38           | 3.14                 | 0.11              | 0.00           | 7.19             | 10.82  |
| 10                                                           | 0.25           | 1.02                 | 0.00              | 0.00           | 4.46             | 5.72   |
| 11                                                           | 0.14           | 0.03                 | 0.00              | 0.00           | 0.48             | 0.64   |
| 12                                                           | 0.00           | 0.06                 | 0.00              | 0.00           | 0.15             | 0.22   |
| Total                                                        | 17.65          | 37.00                | 7.03              | 9.39           | 28.93            | 100.00 |

Average Molecular Weight = 89.52

Average Density - .726

Average Carbon Number = 6.43

H/C Ratio = 1.89

| <u>48 Hours</u> |               |                      |                   |                |                  |        |
|-----------------|---------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.      |               |                      |                   |                |                  | Total  |
|                 | <u>Normal</u> | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3               | 0.05          | 0.00                 | 0.00              | 0.01           | 0.00             | 0.06   |
| 4               | 6.00          | 2.85                 | 0.00              | 0.60           | 0.00             | 9.45   |
| 5               | 4.52          | 9.69                 | 0.20              | 4.69           | 0.00             | 19.10  |
| 6               | 2.64          | 7.32                 | 2.35              | 3.28           | 1.30             | 16.90  |
| 7               | 1.45          | 4.88                 | 3.31              | 0.58           | 6.58             | 16.79  |
| 8               | 0.82          | 6.94                 | 1.00              | 0.01           | 9.60             | 18.37  |
| 9               | 0.40          | 3.21                 | 0.16              | 0.00           | 7.61             | 11.37  |
| 10              | 0.26          | 1.43                 | 0.00              | 0.00           | 4.90             | 6.59   |
| 11              | 0.15          | 0.17                 | 0.00              | 0.00           | 0.63             | 0.95   |
| 12              | 0.00          | 0.11                 | 0.00              | 0.00           | 0.30             | 0.41   |
| Total           | 16.29         | 36.61                | 7.01              | 9.18           | 30.91            | 100.00 |

Average Molecular Weight = 91.61

Average Density - .734

Average Carbon Number = 6.60

H/C Ratio = 1.86

TABLE 8. - Fuel composition summary - Rockville - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                          |                   |                |                  |        |
|--------------------------------------------------------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
| Carbon<br>No.                                                | <u>Initial</u> |                          |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.19           | 0.00                     | 0.00              | 0.03           | 0.00             | 0.22   |
| 4                                                            | 7.41           | 1.77                     | 0.00              | 2.54           | 0.00             | 11.72  |
| 5                                                            | 7.00           | 10.49                    | 0.18              | 4.80           | 0.00             | 22.48  |
| 6                                                            | 2.47           | 8.54                     | 1.66              | 3.64           | 1.21             | 17.52  |
| 7                                                            | 1.22           | 5.72                     | 2.07              | 1.40           | 5.70             | 16.11  |
| 8                                                            | 0.52           | 7.65                     | 1.59              | 0.07           | 7.04             | 16.87  |
| 9                                                            | 0.35           | 3.01                     | 0.08              | 0.00           | 6.41             | 9.87   |
| 10                                                           | 0.25           | 0.83                     | 0.00              | 0.00           | 3.69             | 4.77   |
| 11                                                           | 0.11           | 0.03                     | 0.00              | 0.00           | 0.29             | 0.43   |
| 12                                                           | 0.00           | 0.01                     | 0.00              | 0.00           | 0.03             | 0.03   |
| Total                                                        | 19.52          | 38.05                    | 5.58              | 12.48          | 24.37            | 100.00 |

Average Molecular Weight = 88.15

Average Density - .716

Average Carbon Number = 6.31

H/C Ratio = 1.94

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | Total |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|-------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |       |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00  |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00  |
| 3             | 0.06            | 0.00                     | 0.00              | 0.01           | 0.00             | 0.07  |
| 4             | 5.46            | 1.09                     | 0.00              | 1.86           | 0.00             | 8.41  |
| 5             | 6.83            | 9.78                     | 0.18              | 4.71           | 0.00             | 21.51 |
| 6             | 2.63            | 8.94                     | 1.78              | 3.86           | 1.31             | 18.53 |
| 7             | 1.32            | 6.24                     | 2.36              | 1.45           | 6.20             | 17.58 |
| 8             | 0.59            | 9.12                     | 0.98              | 0.06           | 7.52             | 18.27 |
| 9             | 0.38            | 2.73                     | 0.09              | 0.00           | 6.72             | 9.92  |
| 10            | 0.24            | 1.01                     | 0.00              | 0.00           | 4.00             | 5.25  |
| 11            | 0.11            | 0.03                     | 0.00              | 0.00           | 0.32             | 0.47  |
| 12            | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00  |
| Total         | 17.62           | 38.94                    | 5.39              | 11.95          | 26.07            | 99.97 |

Average Molecular Weight = 90.25

Average Density - .724

Average Carbon Number = 6.47

H/C Ratio = 1.91

TABLE 9. - Fuel composition summary - Sacramento - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.24           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.24   |
| 4                                                            | 5.93           | 2.87                 | 0.00              | 0.97           | 0.00             | 9.77   |
| 5                                                            | 5.75           | 13.15                | 0.22              | 3.34           | 0.00             | 22.46  |
| 6                                                            | 2.75           | 10.84                | 3.81              | 3.37           | 1.64             | 22.42  |
| 7                                                            | 1.12           | 5.51                 | 3.10              | 1.28           | 6.00             | 17.00  |
| 8                                                            | 0.38           | 7.09                 | 1.90              | 0.06           | 7.80             | 17.22  |
| 9                                                            | 0.21           | 3.01                 | 0.07              | 0.00           | 4.95             | 8.23   |
| 10                                                           | 0.09           | 0.36                 | 0.00              | 0.00           | 2.06             | 2.50   |
| 11                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.15             | 0.15   |
| 12                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 16.46          | 42.84                | 9.10              | 9.01           | 22.59            | 100.00 |

Average Molecular Weight = 87.54

Average Density - .714

Average Carbon Number = 6.26

H/C Ratio = 1.96

| <u>48 Hours</u> |               |                      |                   |                |                  |        |
|-----------------|---------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.      | <u>Normal</u> | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | Total  |
| 1               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3               | 0.12          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.12   |
| 4               | 5.00          | 2.17                 | 0.00              | 0.82           | 0.00             | 7.99   |
| 5               | 5.71          | 12.67                | 0.23              | 3.32           | 0.00             | 21.92  |
| 6               | 2.87          | 11.15                | 3.96              | 3.24           | 1.70             | 22.92  |
| 7               | 1.18          | 5.67                 | 1.61              | 2.82           | 6.25             | 17.53  |
| 8               | 0.35          | 8.55                 | 1.26              | 0.03           | 8.12             | 18.31  |
| 9               | 0.11          | 3.02                 | 0.07              | 0.00           | 5.22             | 8.42   |
| 10              | 0.00          | 0.41                 | 0.00              | 0.00           | 2.23             | 2.65   |
| 11              | 0.00          | 0.00                 | 0.00              | 0.00           | 0.14             | 0.14   |
| 12              | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total           | 15.33         | 43.65                | 7.13              | 10.24          | 23.65            | 100.00 |

Average Molecular Weight = 88.71

Average Density - .718

Average Carbon Number = 6.35

H/C Ratio = 1.94

TABLE 10. - Fuel composition summary - Houston - winter

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                          |                   |                |                  | <u>Total</u> |
|---------------|----------------|--------------------------|-------------------|----------------|------------------|--------------|
|               | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 2             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 3             | 0.09           | 0.00                     | 0.00              | 0.03           | 0.00             | 0.12         |
| 4             | 8.11           | 1.43                     | 0.00              | 1.86           | 0.00             | 11.40        |
| 5             | 6.98           | 11.01                    | 0.18              | 4.13           | 0.00             | 22.31        |
| 6             | 2.02           | 8.10                     | 1.88              | 2.79           | 0.88             | 15.67        |
| 7             | 1.08           | 5.13                     | 2.30              | 0.87           | 4.96             | 14.34        |
| 8             | 0.59           | 4.17                     | 0.95              | 0.03           | 9.73             | 15.47        |
| 9             | 0.46           | 2.71                     | 0.07              | 0.00           | 9.26             | 12.50        |
| 10            | 0.27           | 0.49                     | 0.00              | 0.00           | 6.04             | 6.79         |
| 11            | 0.17           | 0.01                     | 0.00              | 0.00           | 1.01             | 1.20         |
| 12            | 0.10           | 0.02                     | 0.00              | 0.00           | 0.09             | 0.21         |
| Total         | 19.87          | 33.07                    | 5.38              | 9.71           | 31.97            | 100.00       |

Average Molecular Weight = 89.96

Average Density - .730

Average Carbon Number = 6.48

H/C Ratio = 1.87

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | <u>Total</u> |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|--------------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 3             | 0.04            | 0.00                     | 0.00              | 0.01           | 0.00             | 0.05         |
| 4             | 6.63            | 1.03                     | 0.00              | 1.50           | 0.00             | 9.17         |
| 5             | 6.85            | 10.53                    | 0.18              | 4.01           | 0.00             | 21.58        |
| 6             | 2.10            | 8.32                     | 1.96              | 2.78           | 0.90             | 16.06        |
| 7             | 1.15            | 5.23                     | 1.25              | 1.98           | 5.23             | 14.85        |
| 8             | 0.62            | 4.94                     | 1.18              | 0.02           | 10.27            | 17.03        |
| 9             | 0.24            | 2.44                     | 0.09              | 0.00           | 9.90             | 12.67        |
| 10            | 0.14            | 0.65                     | 0.00              | 0.00           | 6.31             | 7.11         |
| 11            | 0.19            | 0.00                     | 0.00              | 0.00           | 1.09             | 1.28         |
| 12            | 0.13            | 0.00                     | 0.00              | 0.00           | 0.07             | 0.20         |
| Total         | 18.10           | 33.16                    | 4.66              | 10.30          | 33.78            | 100.00       |

Average Molecular Weight = 91.54

Average Density - .736

Average Carbon Number = 6.60

H/C Ratio = 1.84



TABLE 11. - Fuel composition summary - Wichita - winter

| Volume-percent Summation by Carbon Number and Compound Class |                |                          |                   |                |                  |        |
|--------------------------------------------------------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
| Carbon<br>No.                                                | <u>Initial</u> |                          |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.12           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.12   |
| 4                                                            | 11.92          | 1.45                     | 0.00              | 2.73           | 0.00             | 16.11  |
| 5                                                            | 6.22           | 7.29                     | 0.16              | 3.92           | 0.00             | 17.59  |
| 6                                                            | 3.56           | 7.03                     | 2.06              | 3.34           | 1.21             | 17.20  |
| 7                                                            | 1.56           | 8.90                     | 1.49              | 1.28           | 5.44             | 18.66  |
| 8                                                            | 0.56           | 9.20                     | 1.10              | 0.08           | 7.29             | 18.22  |
| 9                                                            | 0.29           | 2.45                     | 0.00              | 0.00           | 5.33             | 8.07   |
| 10                                                           | 0.15           | 0.86                     | 0.00              | 0.00           | 2.76             | 3.77   |
| 11                                                           | 0.04           | 0.00                     | 0.00              | 0.00           | 0.22             | 0.26   |
| 12                                                           | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 24.42          | 37.18                    | 4.80              | 11.35          | 22.26            | 100.00 |

Average Molecular Weight = 87.02

Average Density - .710

Average Carbon Number = 6.22

H/C Ratio = 1.97

| <u>48 Hours</u> |               |                          |                   |                |                  |        |
|-----------------|---------------|--------------------------|-------------------|----------------|------------------|--------|
| Carbon<br>No.   | <u>Normal</u> | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | Total  |
| 1               | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2               | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3               | 0.04          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.04   |
| 4               | 9.04          | 0.94                     | 0.00              | 2.06           | 0.00             | 12.04  |
| 5               | 6.04          | 6.79                     | 0.17              | 3.80           | 0.00             | 16.81  |
| 6               | 3.73          | 7.29                     | 2.16              | 3.50           | 1.25             | 17.93  |
| 7               | 1.67          | 9.58                     | 1.58              | 1.35           | 5.87             | 20.06  |
| 8               | 0.60          | 10.00                    | 1.21              | 0.10           | 7.82             | 19.72  |
| 9               | 0.33          | 2.81                     | 0.01              | 0.00           | 5.81             | 8.94   |
| 10              | 0.15          | 0.73                     | 0.00              | 0.00           | 3.18             | 4.06   |
| 11              | 0.05          | 0.00                     | 0.00              | 0.00           | 0.35             | 0.41   |
| 12              | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| Total           | 21.65         | 38.13                    | 5.12              | 10.81          | 24.28            | 100.00 |

Average Molecular Weight = 89.57

Average Density - .719

Average Carbon Number = 6.41

H/C Ratio = 1.94

TABLE 12. - Fuel composition summary - Denver - winter

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                          |                   |                |                  | Total  |
|---------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.26           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.26   |
| 4             | 5.23           | 5.73                     | 0.00              | 2.54           | 0.00             | 13.50  |
| 5             | 6.84           | 8.49                     | 0.19              | 3.53           | 0.00             | 19.05  |
| 6             | 5.48           | 9.02                     | 3.84              | 2.55           | 1.28             | 22.16  |
| 7             | 2.25           | 5.97                     | 3.08              | 1.69           | 6.32             | 19.30  |
| 8             | 0.67           | 3.91                     | 0.71              | 0.07           | 7.64             | 13.00  |
| 9             | 0.37           | 2.27                     | 0.02              | 0.00           | 5.73             | 8.40   |
| 10            | 0.19           | 0.39                     | 0.00              | 0.00           | 3.23             | 3.81   |
| 11            | 0.14           | 0.00                     | 0.00              | 0.00           | 0.38             | 0.52   |
| 12            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| Total         | 21.43          | 35.78                    | 7.84              | 10.38          | 24.58            | 100.00 |

Average Molecular Weight = 86.83

Average Density - .715

Average Carbon Number = 6.22

H/C Ratio = 1.94

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | Total  |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.07            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.07   |
| 4             | 3.87            | 3.48                     | 0.00              | 1.85           | 0.00             | 9.20   |
| 5             | 6.63            | 7.88                     | 0.19              | 3.39           | 0.00             | 18.10  |
| 6             | 5.79            | 9.33                     | 4.05              | 2.65           | 1.35             | 23.18  |
| 7             | 2.44            | 6.90                     | 2.91              | 1.80           | 6.85             | 20.89  |
| 8             | 0.76            | 4.24                     | 0.82              | 0.10           | 8.37             | 14.29  |
| 9             | 0.41            | 2.52                     | 0.01              | 0.00           | 6.24             | 9.17   |
| 10            | 0.21            | 0.47                     | 0.00              | 0.00           | 3.66             | 4.33   |
| 11            | 0.13            | 0.00                     | 0.00              | 0.00           | 0.62             | 0.75   |
| 12            | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| Total         | 20.31           | 34.82                    | 7.98              | 9.80           | 27.09            | 100.00 |

Average Molecular Weight = 89.57

Average Density - .726

Average Carbon Number = 6.43

H/C Ratio = 1.90

TABLE 13. - Vapor pressure versus time - summer fuels

| Fuel               | Original | Equivalent Reid Vapor Pressure (psi) |     |     |     |
|--------------------|----------|--------------------------------------|-----|-----|-----|
|                    |          | Time                                 |     |     |     |
|                    |          | 0                                    | 12  | 24  | 48  |
| New Orleans, LA    | 11.2     | 9.5                                  | 9.3 | 9.2 | 9.2 |
| Houston, TX        | 8.8      | 8.2                                  | 7.6 | 7.7 | 7.4 |
| Washington, DC     | 9.9      | 9.7                                  | 8.5 | 8.4 | 8.2 |
| Denver, CO         | 9.2      | 8.9                                  | 8.4 | 8.5 | 8.3 |
| Ft. Lauderdale, FL | 10.6     | 9.8                                  | 9.5 | 9.3 | 9.3 |
| Chicago, IL        | 10.2     | 9.6                                  | 9.5 | 9.3 | 9.3 |
| Sacramento, CA     | 8.7      | 8.4                                  | 8.3 | 8.2 | 8.0 |
| San Diego, CA      | 8.9      | 8.4                                  | 8.2 | 8.2 | 8.1 |
| Wichita, KS        | 8.9      | 8.8                                  | 8.6 | 8.4 | 8.4 |
| Duluth, MN         | 10.6     | 9.3                                  | 8.3 | 7.9 | 8.1 |

TABLE 14. - Octane ratings - summer fuels

| Fuel               | RON     |       |       | MON     |       |       |
|--------------------|---------|-------|-------|---------|-------|-------|
|                    | Initial | Final | Diff. | Initial | Final | Diff. |
| New Orleans, LA    | 95.2    | 95.1  | 0.1   | 83.7    | 83.7  | 0.0   |
| Houston, TX        | 97.5    | 97.5  | 0.0   | 86.5    | 86.5  | 0.0   |
| Washington, DC     | 91.7    | 91.4  | 0.3   | 81.6    | 81.6  | 0.0   |
| Denver, CO         | 89.4    | 89.4  | 0.0   | 80.1    | 80.0  | 0.0   |
| Ft. Lauderdale, FL | 97.5    | 97.5  | 0.0   | 86.8    | 86.8  | 0.0   |
| Chicago, IL        | 93.1    | 93.0  | 0.1   | 83.7    | 83.7  | 0.0   |
| Sacramento, CA     | 98.1    | 97.5  | 0.6   | 85.8    | 85.0  | 0.8   |
| San Diego, CA      | 92.7    | 92.6  | 0.1   | 82.2    | 82.2  | 0.0   |
| Wichita, KS        | 94.1    | 94.0  | 0.1   | 85.0    | 84.8  | 0.2   |
| Duluth, MN         | 94.9    | 94.0  | 0.0   | 86.4    | 86.1  | 0.3   |

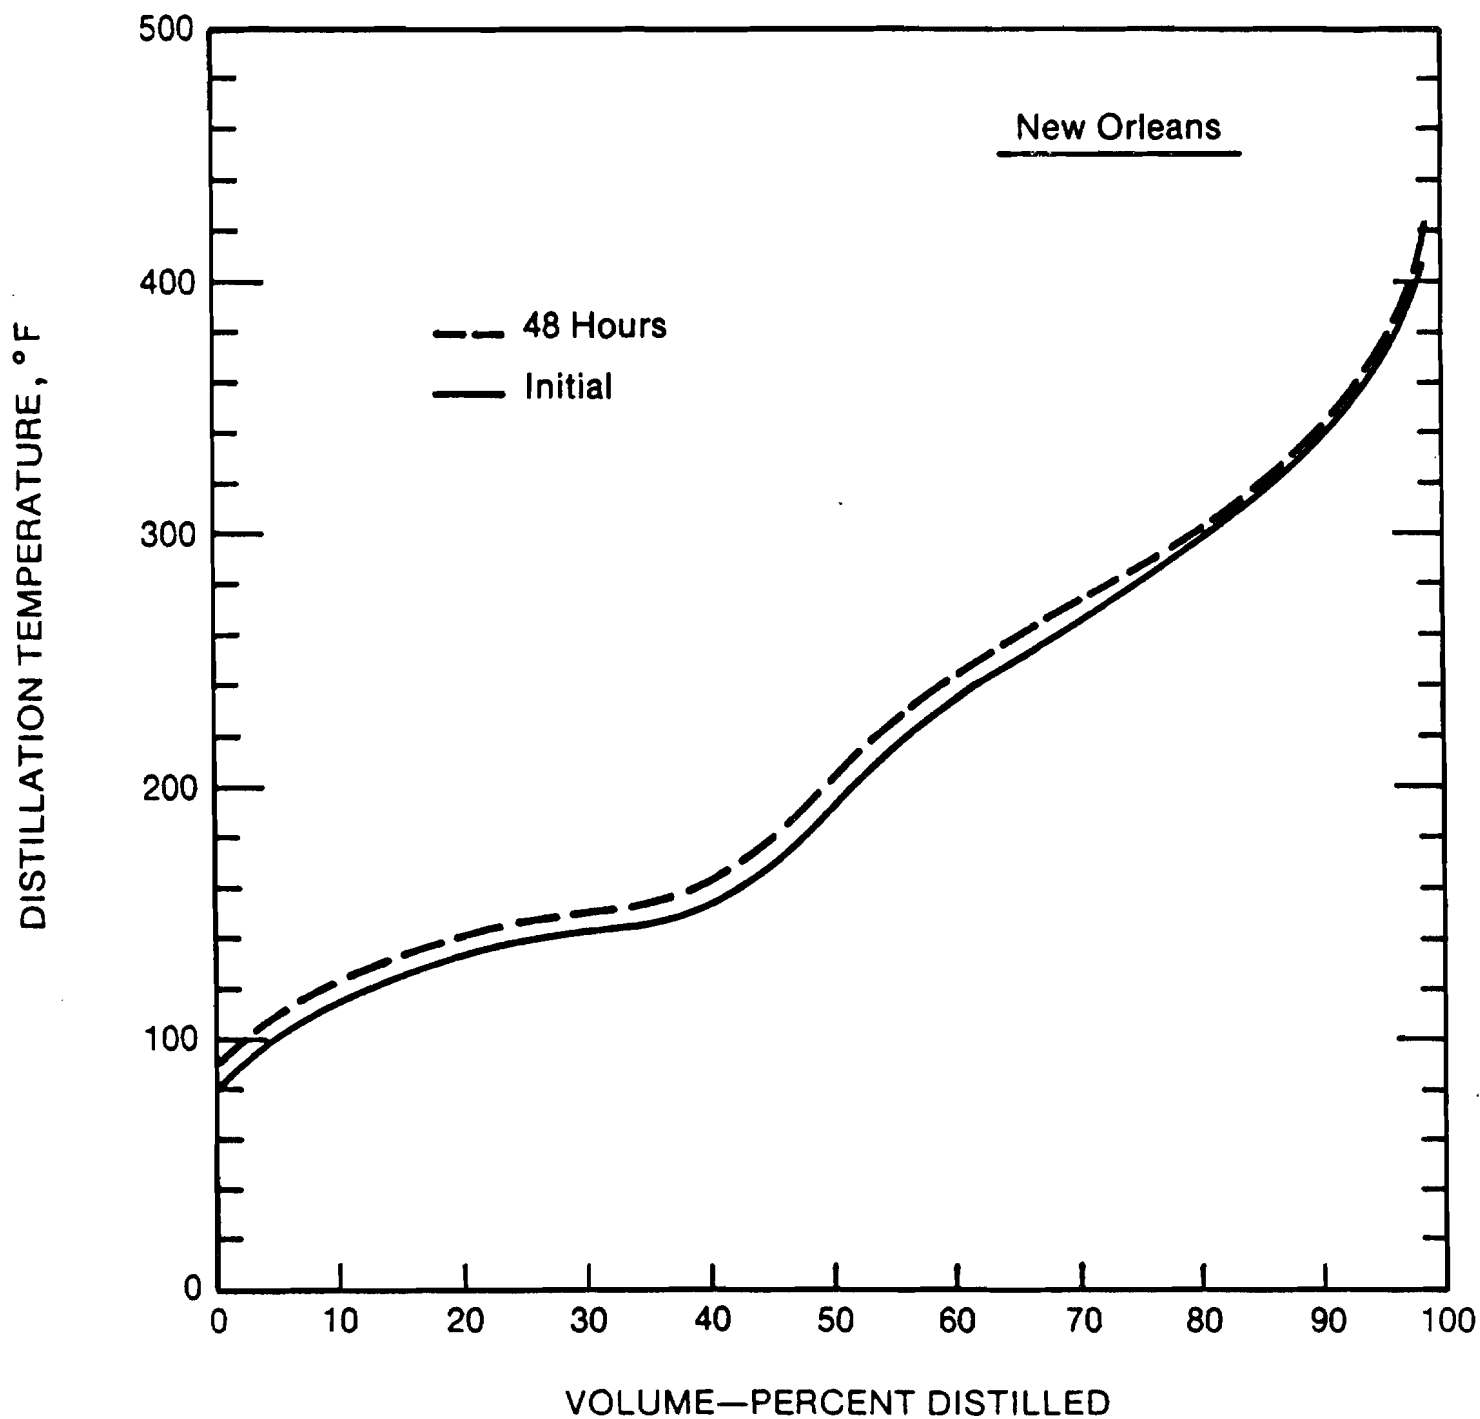


FIGURE 16. - Changes in distillation character due to weathering, summer fuel from New Orleans

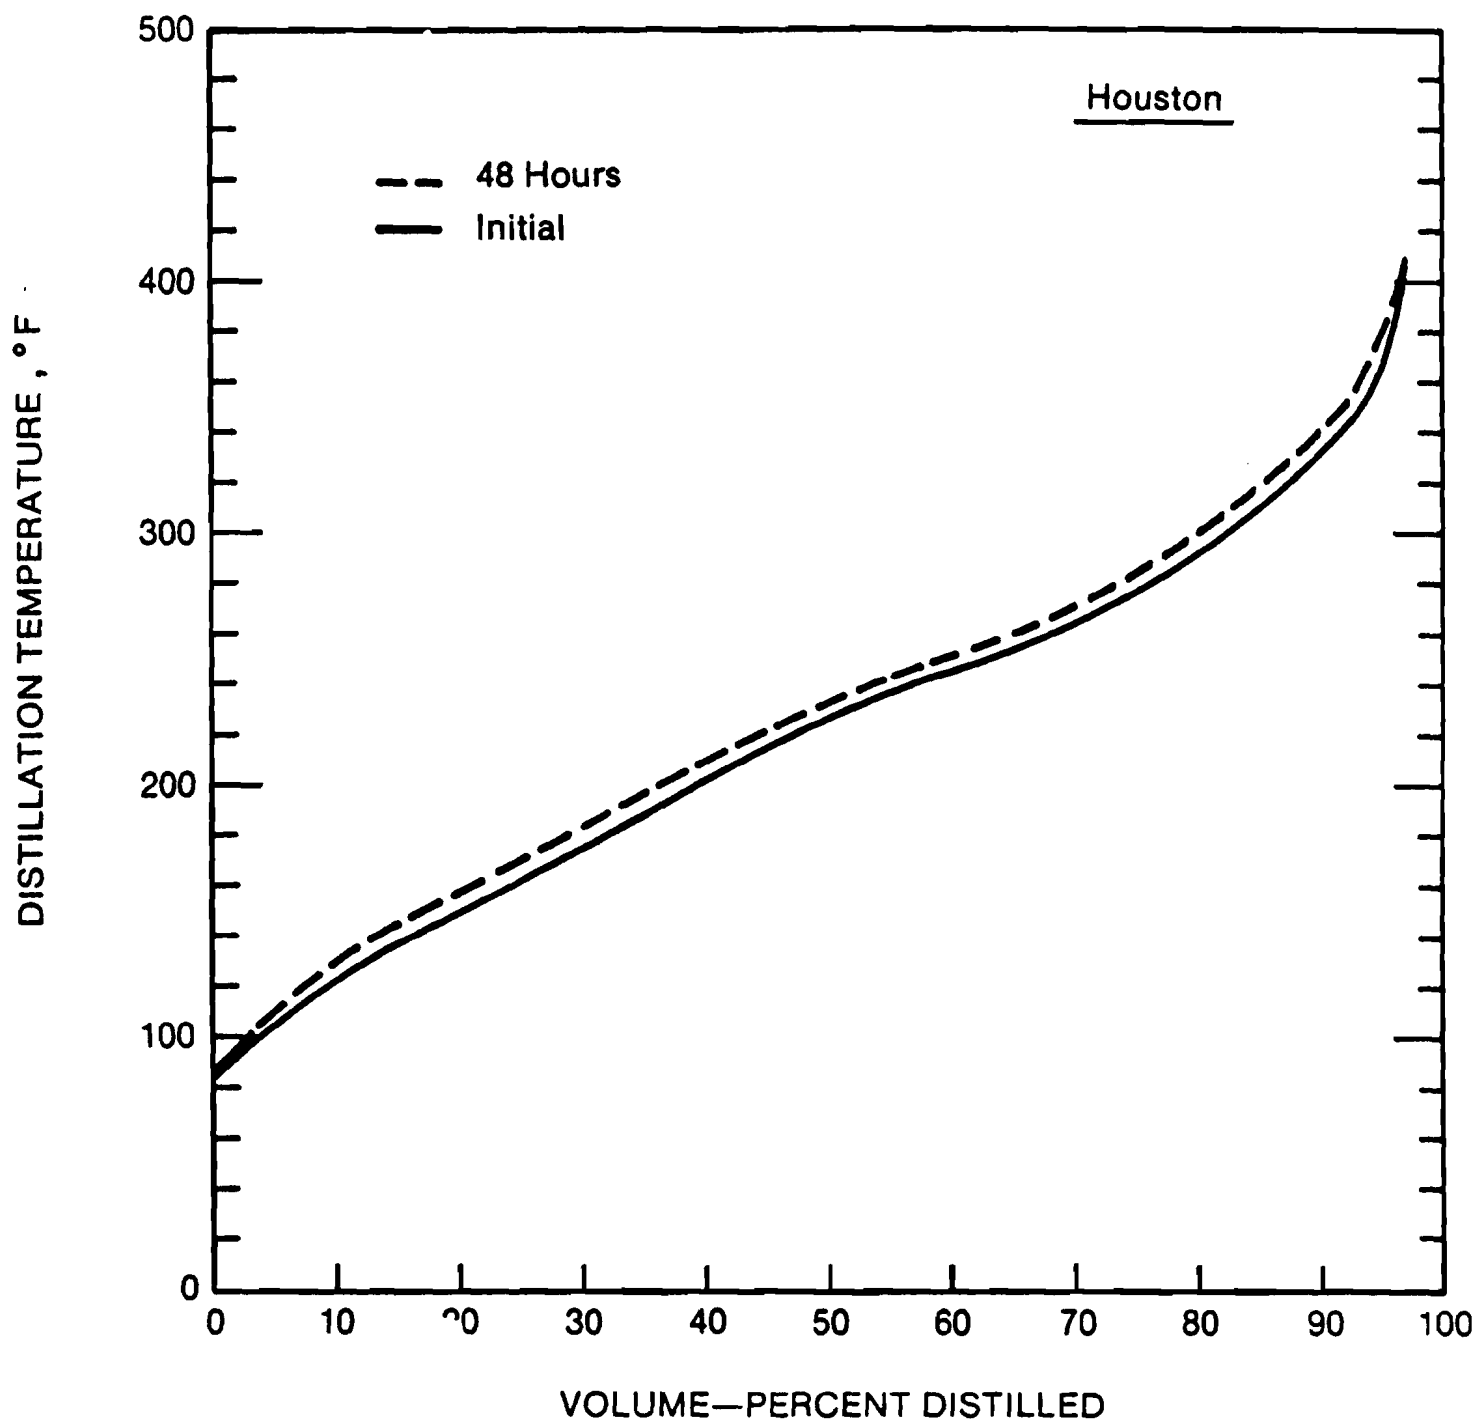


FIGURE 17. - Changes in distillation character due to weathering, summer fuels from Houston.

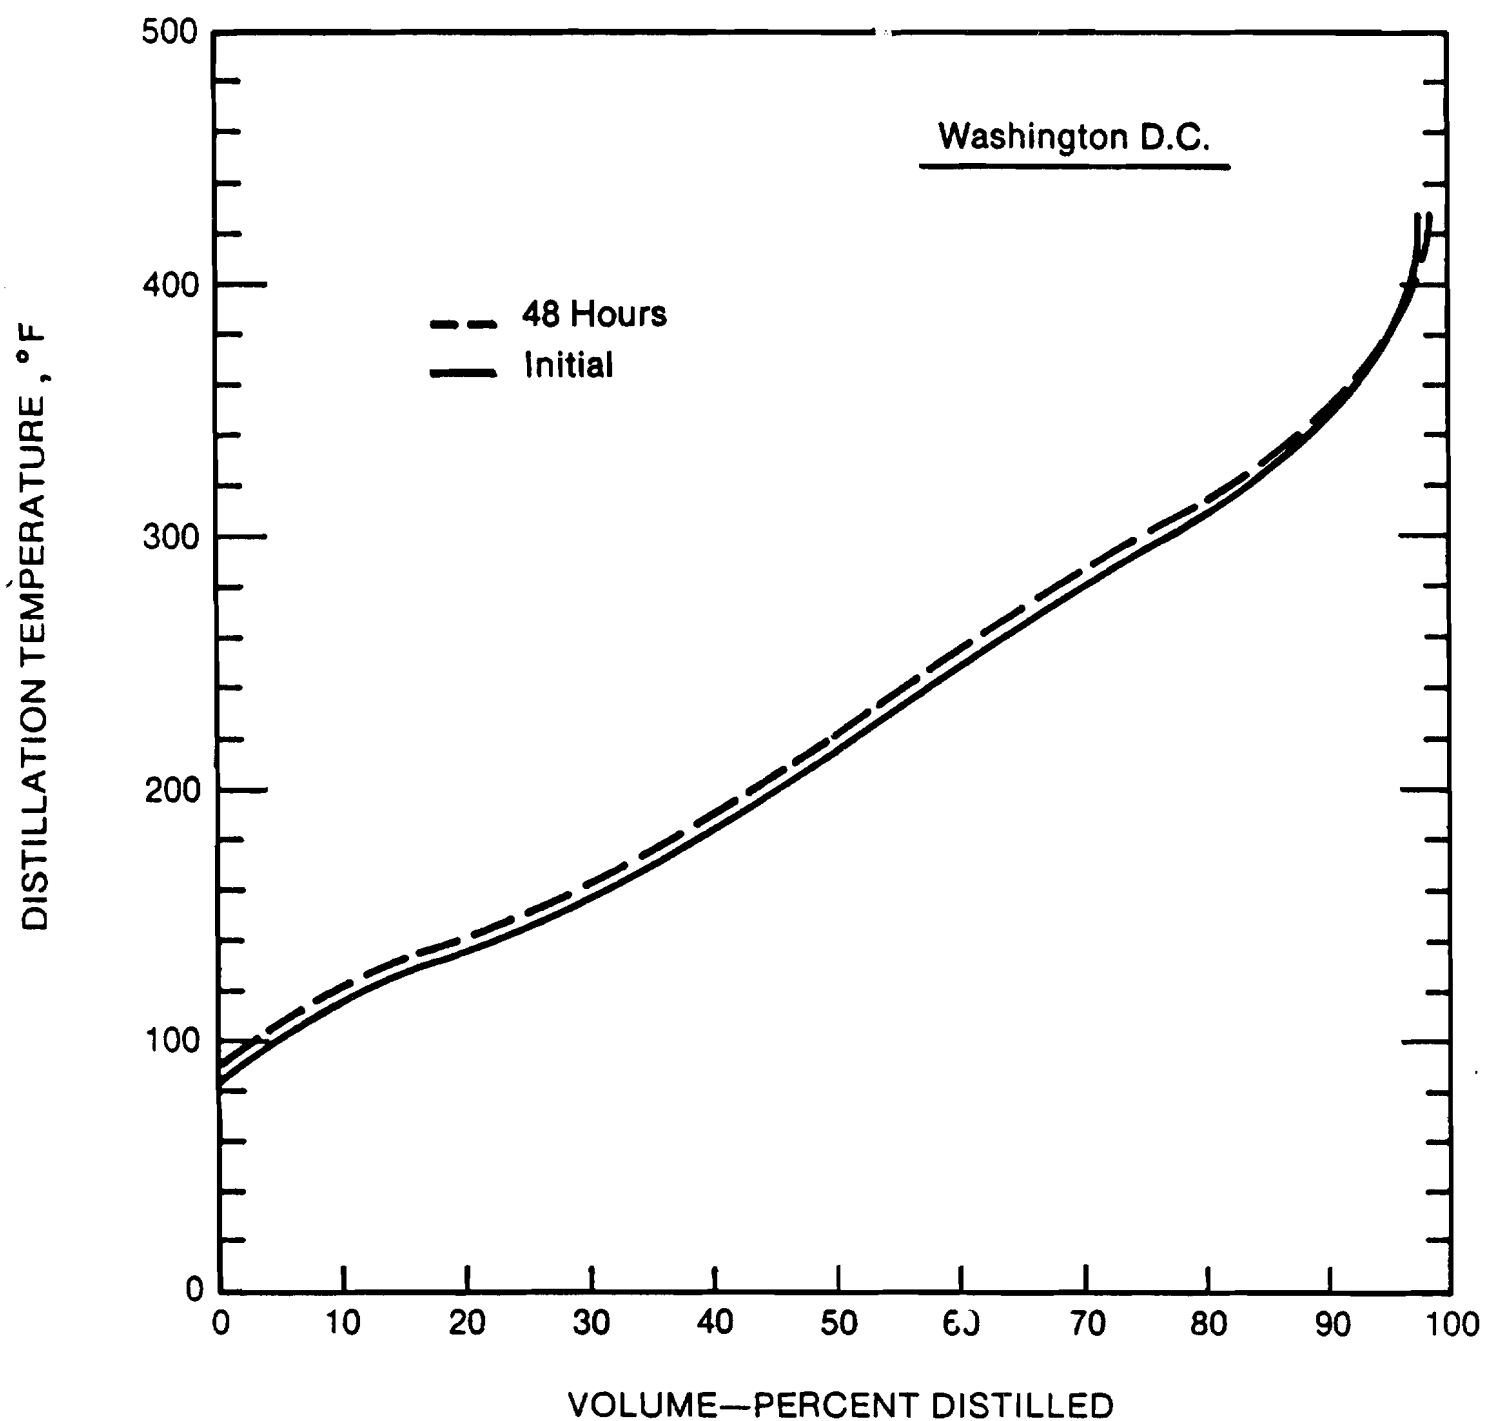


FIGURE 18. - Changes in distillation character due to weathering, summer fuels from Washington, DC

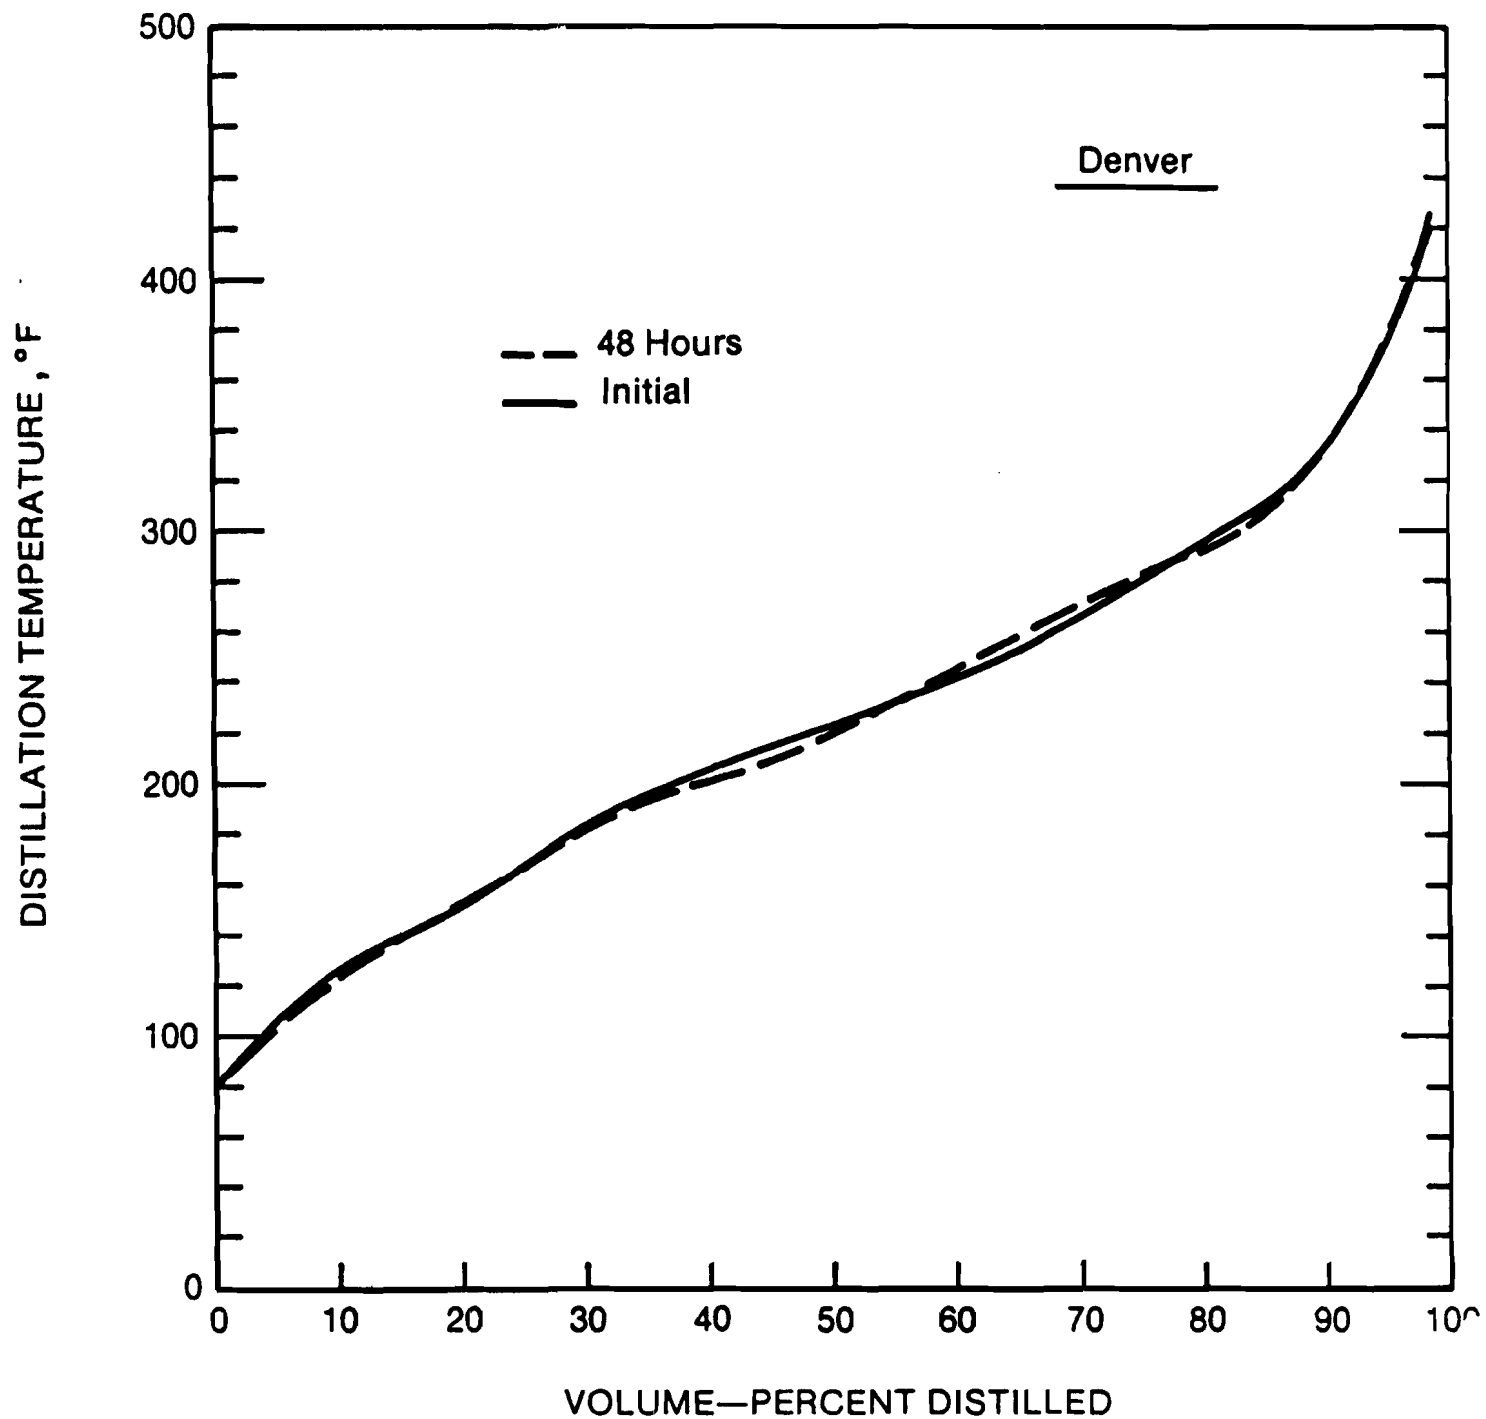


FIGURE 19. - Changes in distillation character due to weathering, summer fuel from Denver.

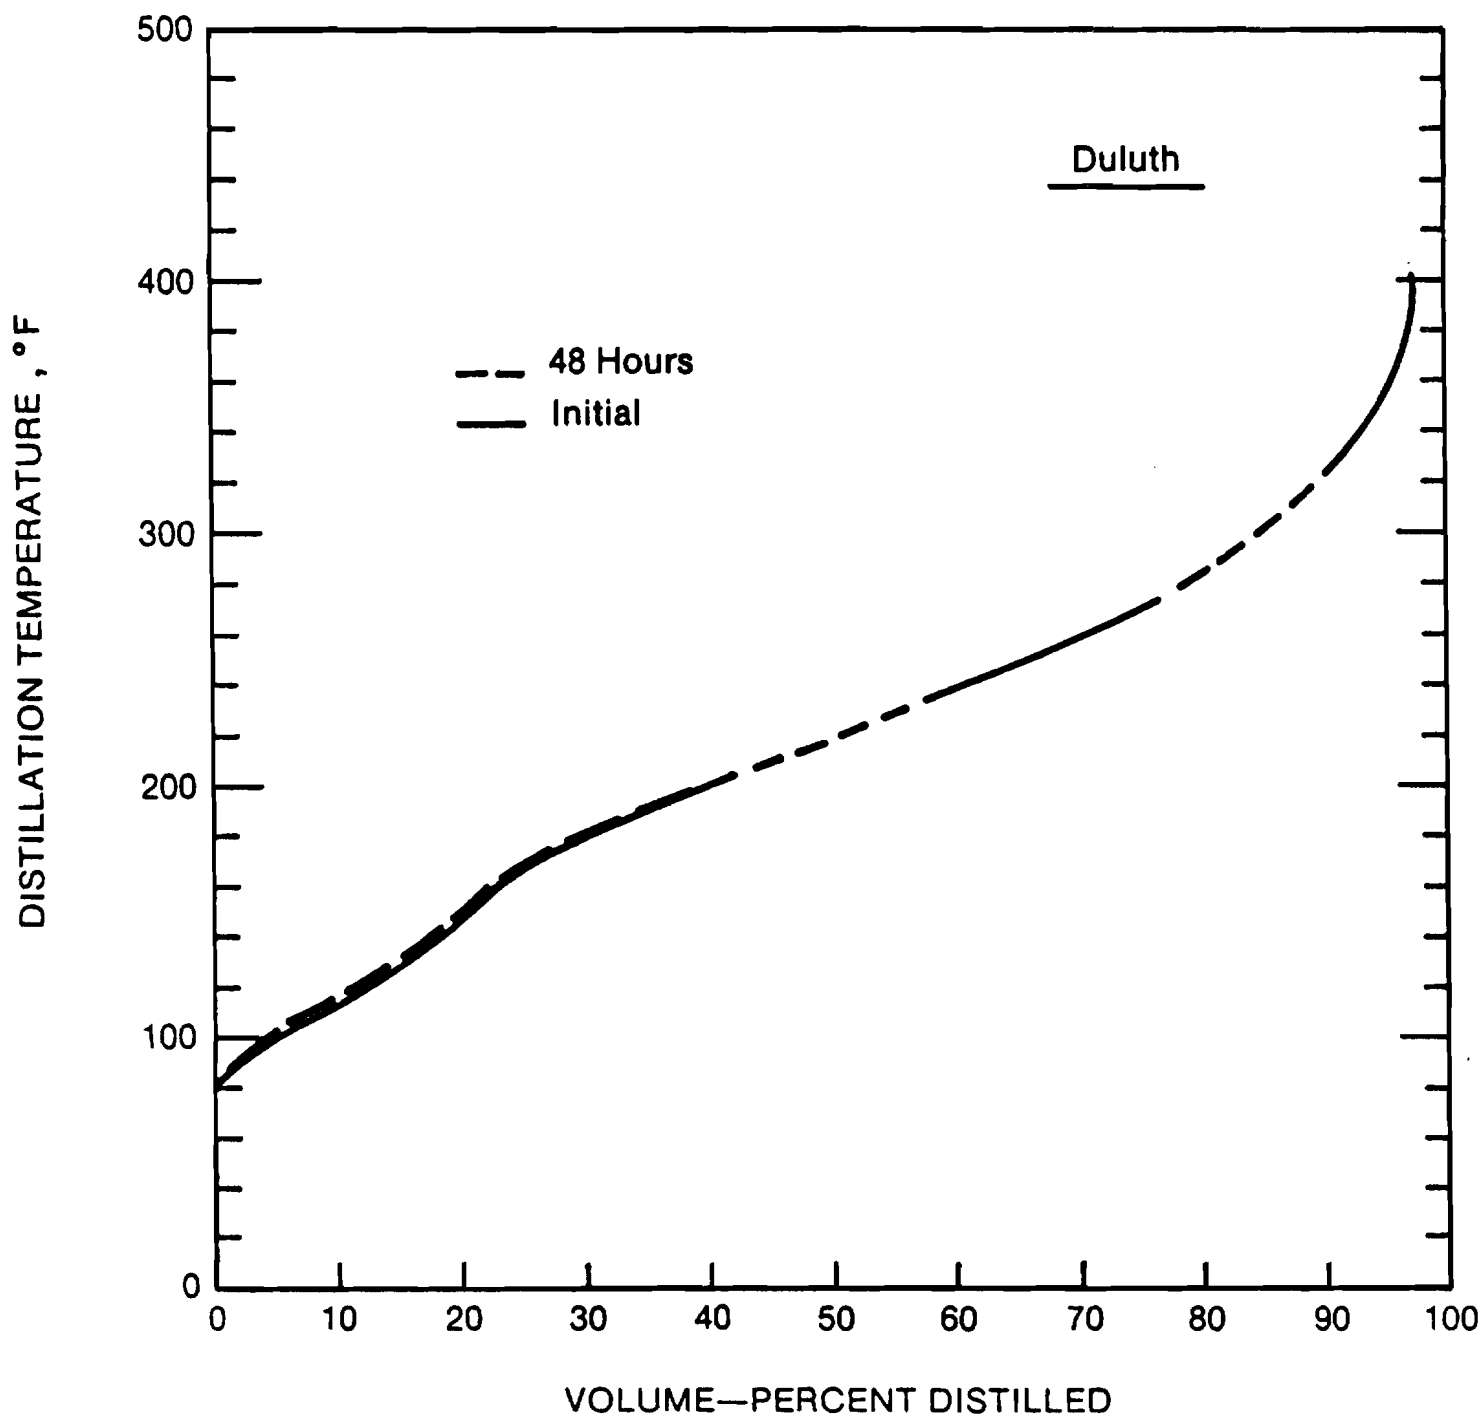


FIGURE 20. - Changes in distillation character due to weathering, summer fuel from Duluth.



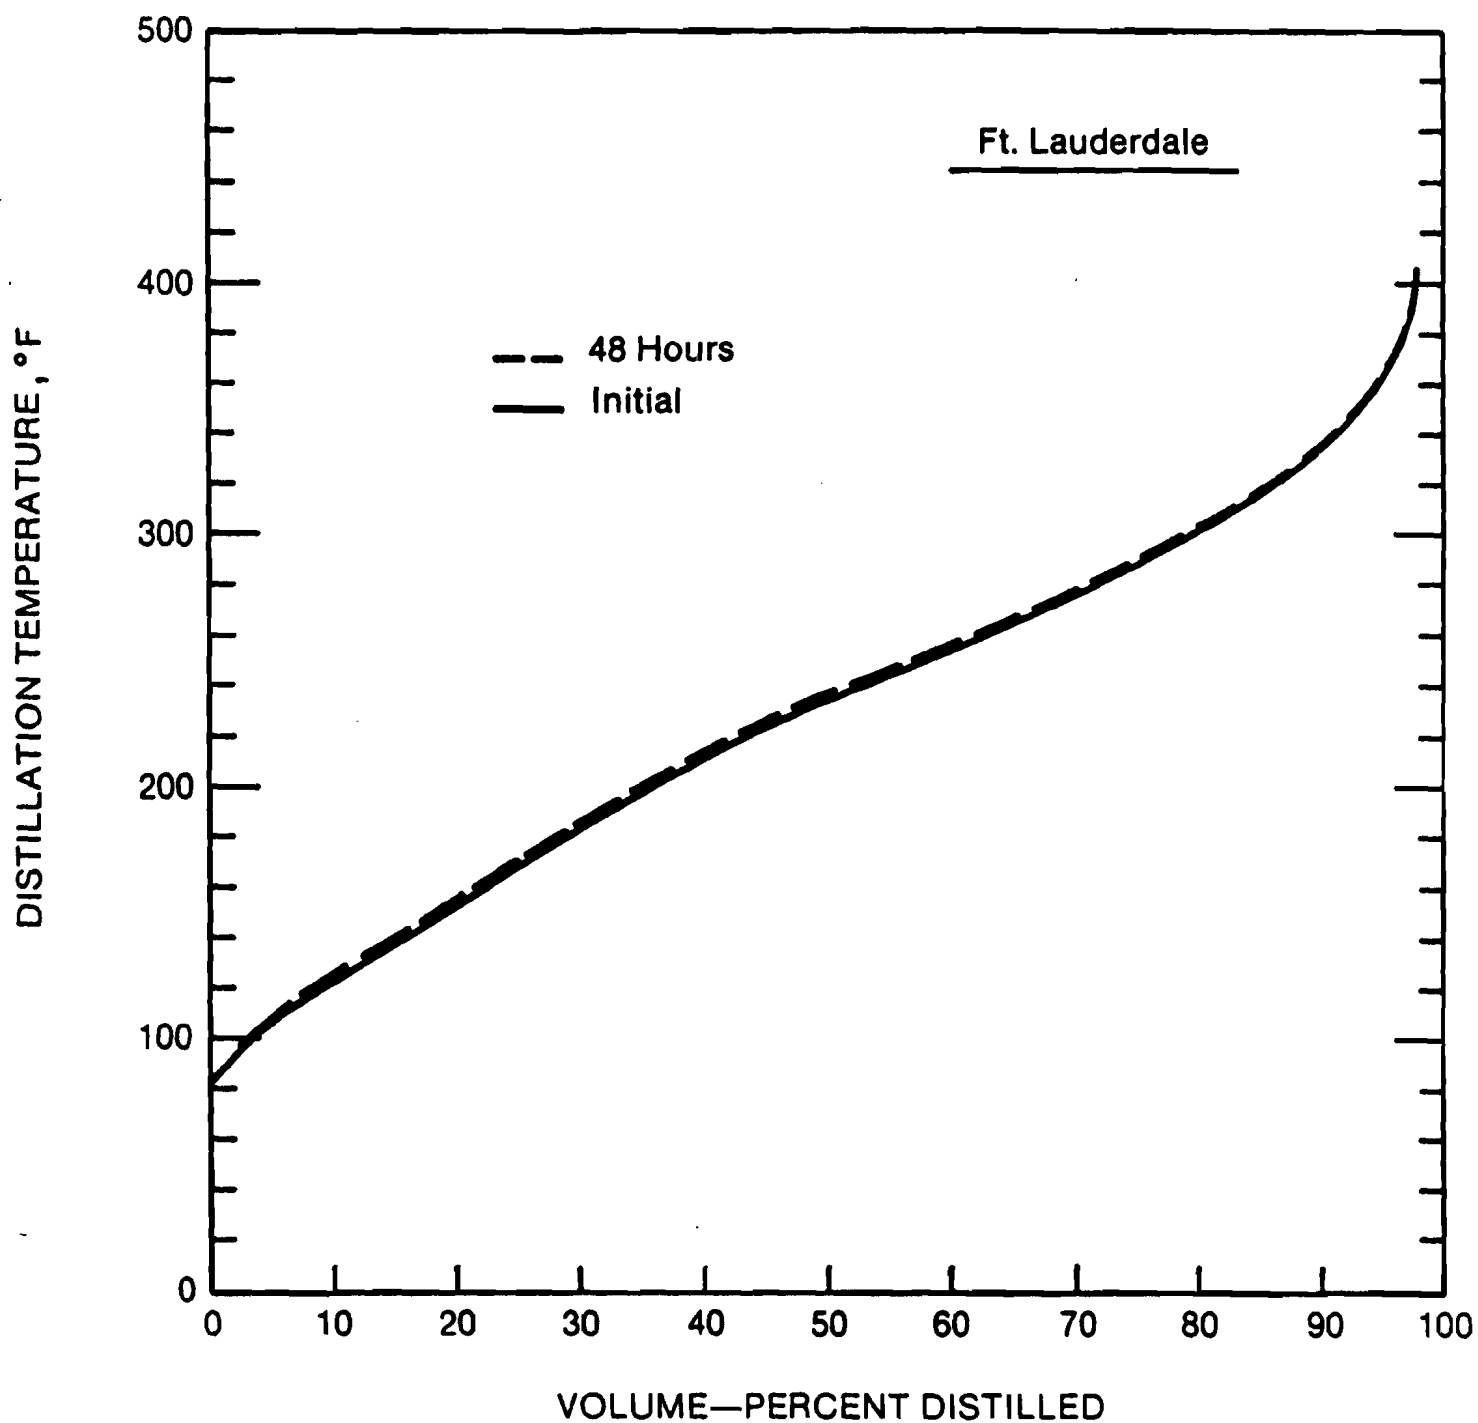


FIGURE 21. - Changes in distillation character due to weathering, summer fuel from Ft. Lauderdale.

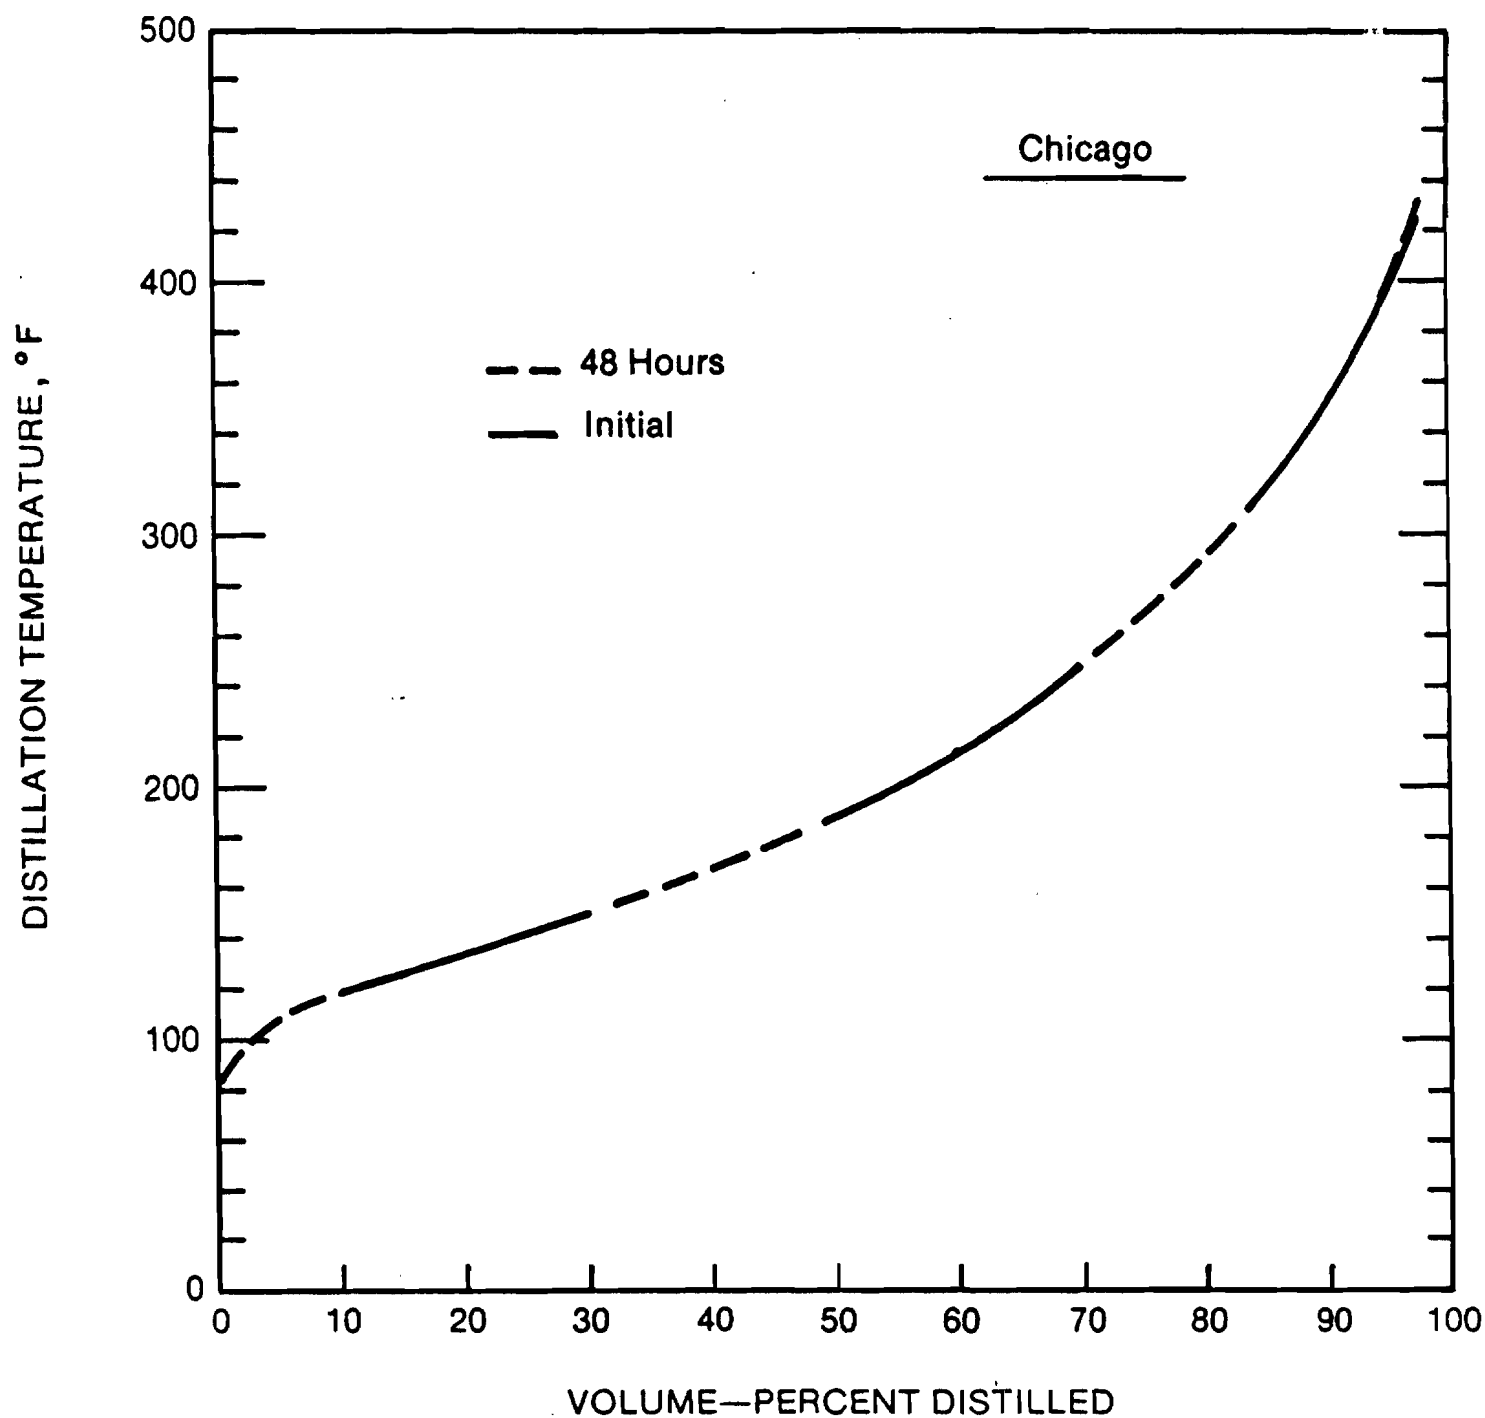


FIGURE 22. - Changes in distillation character due to weathering, summer fuel from Chicago.

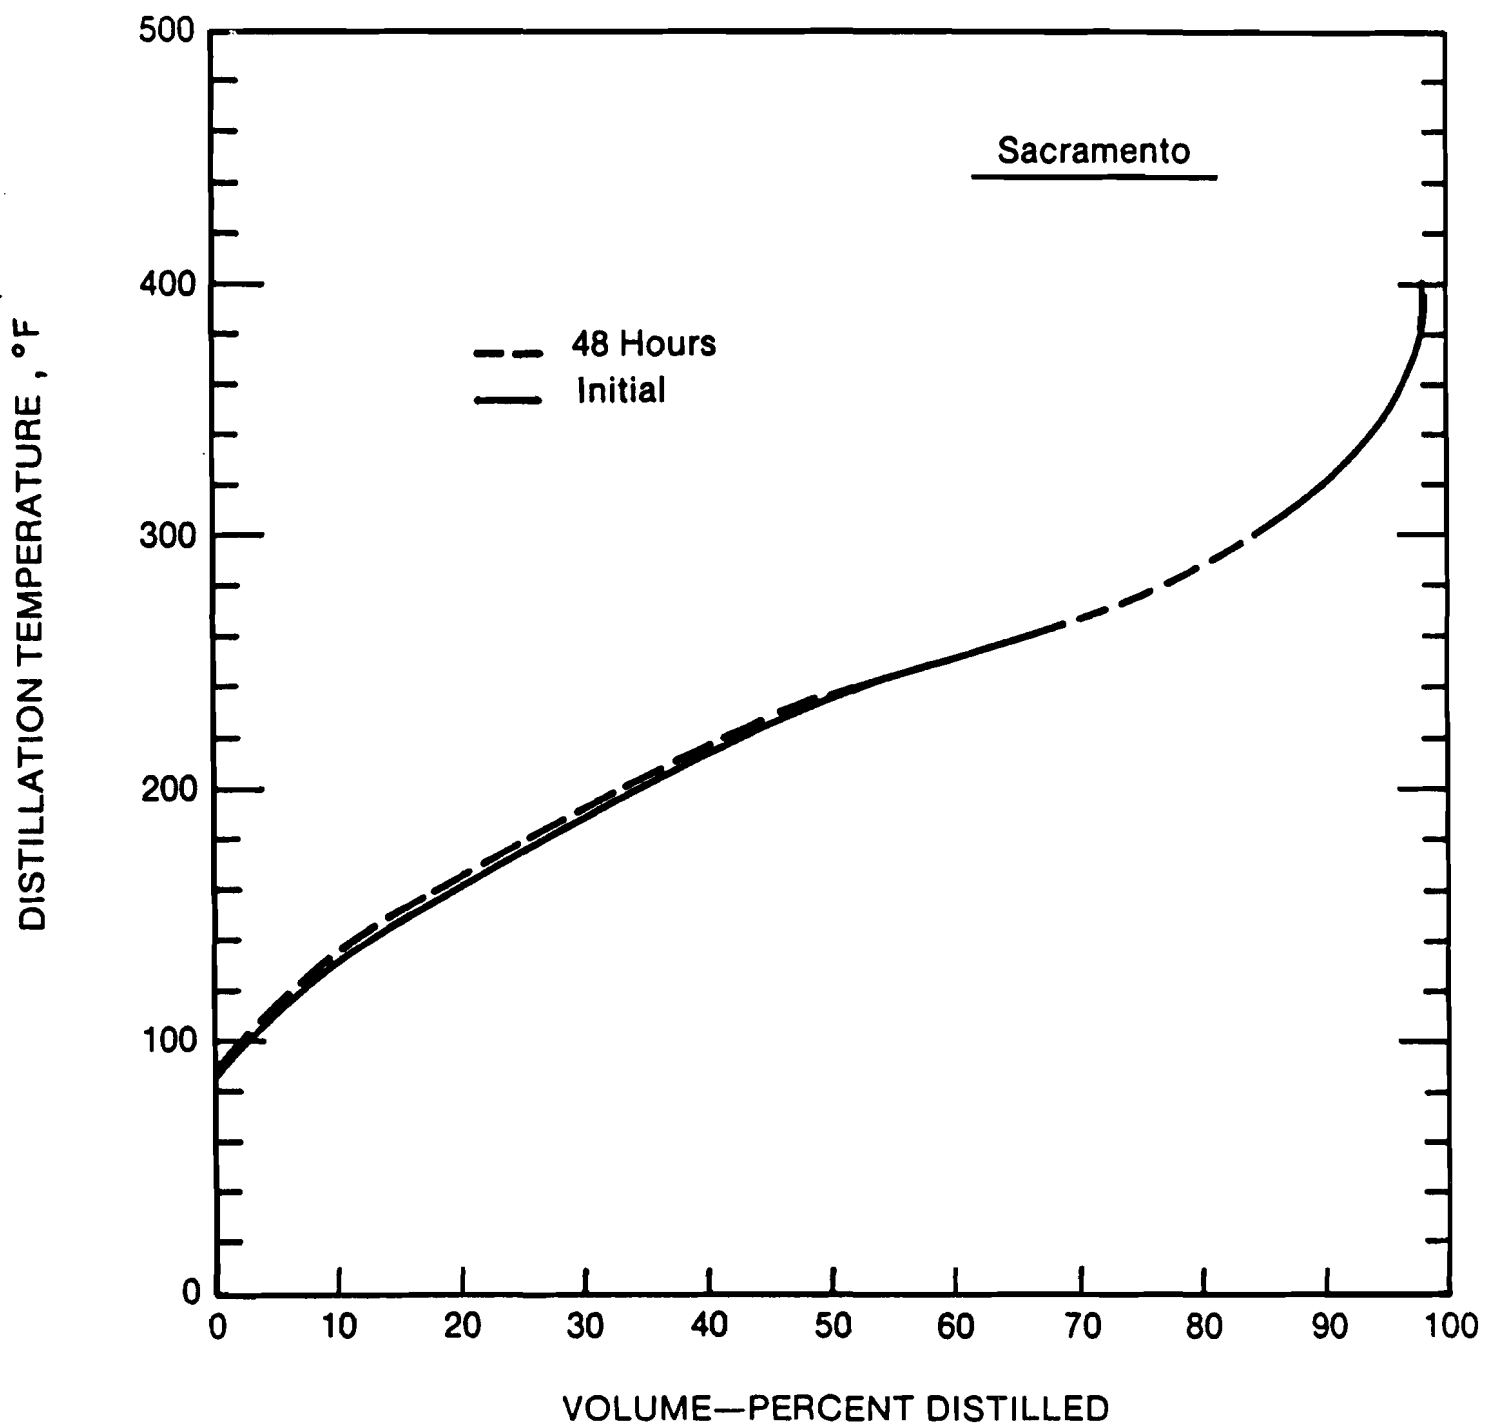


FIGURE 23. - Changes in distillation character due to weathering, summer fuel from Sacramento

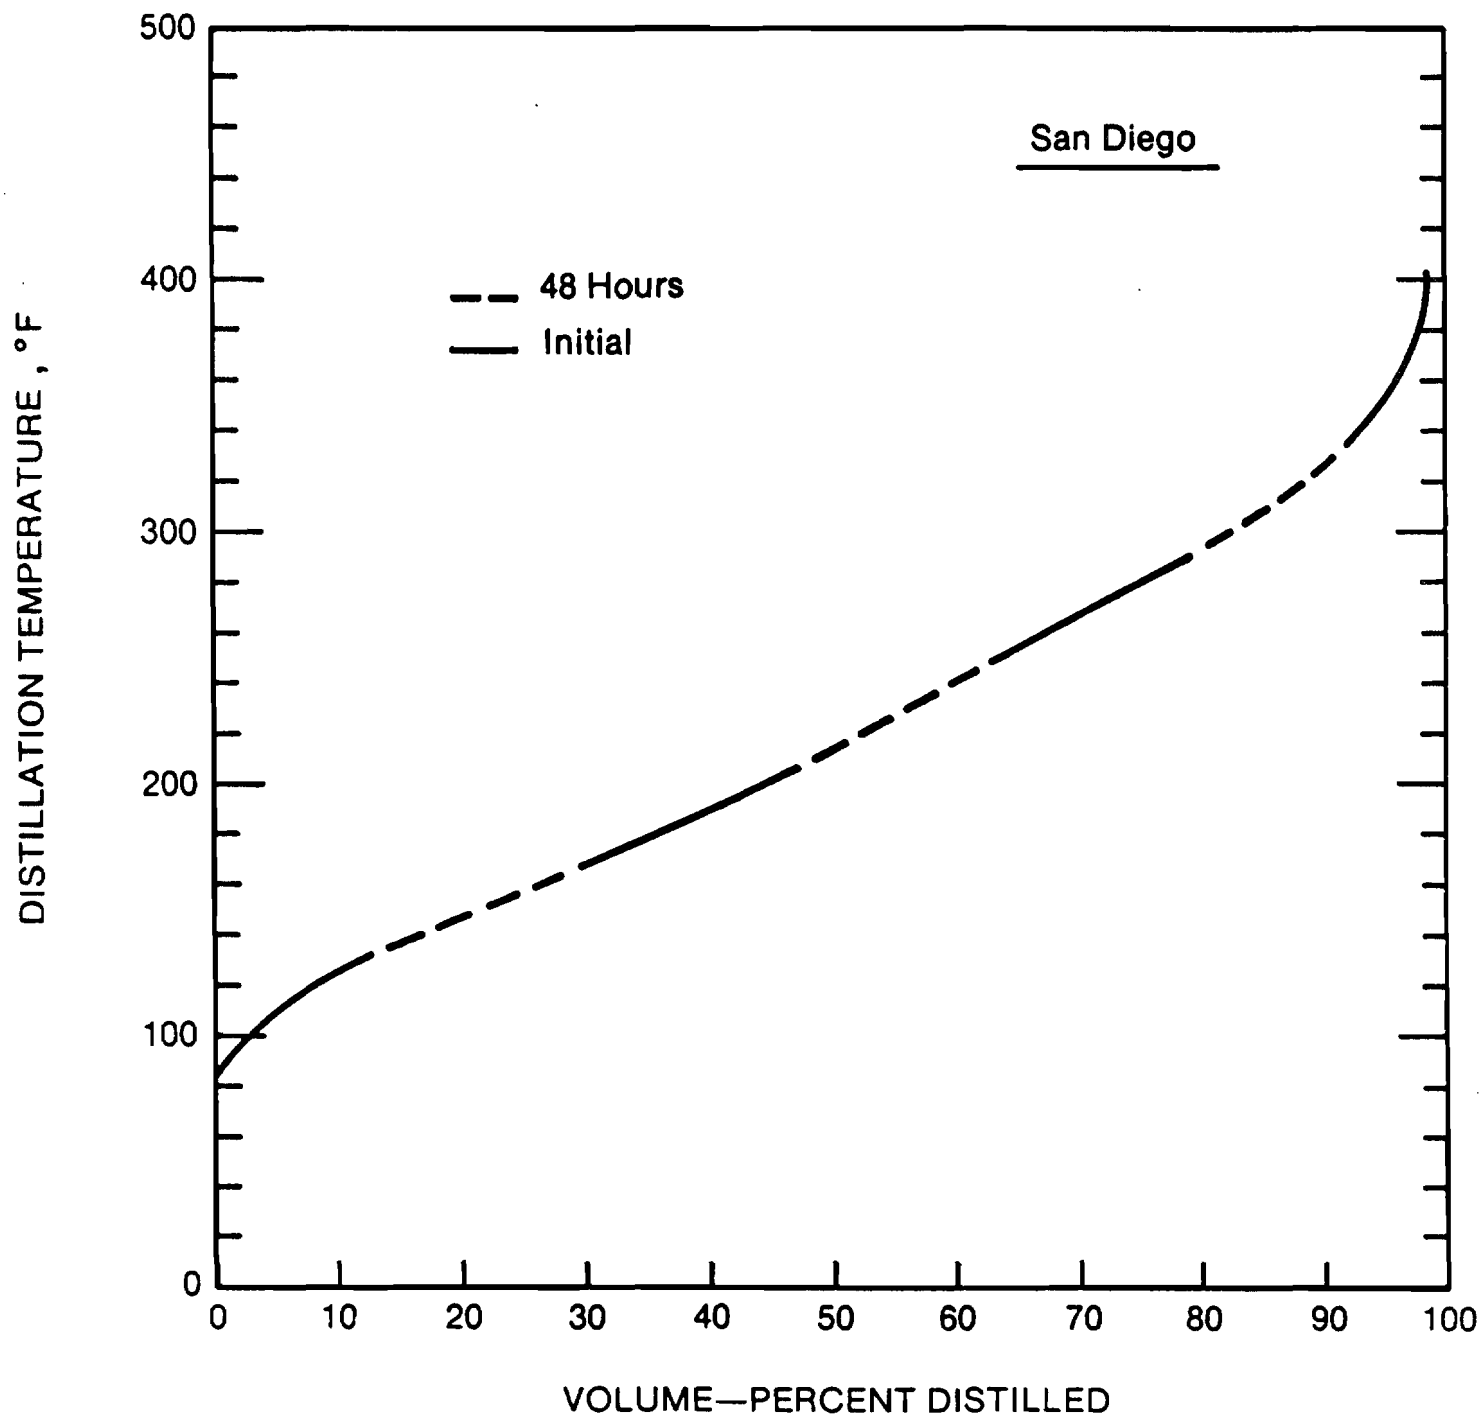


FIGURE 24. - Changes in distillation character due to weathering, summer fuel from San Diego.

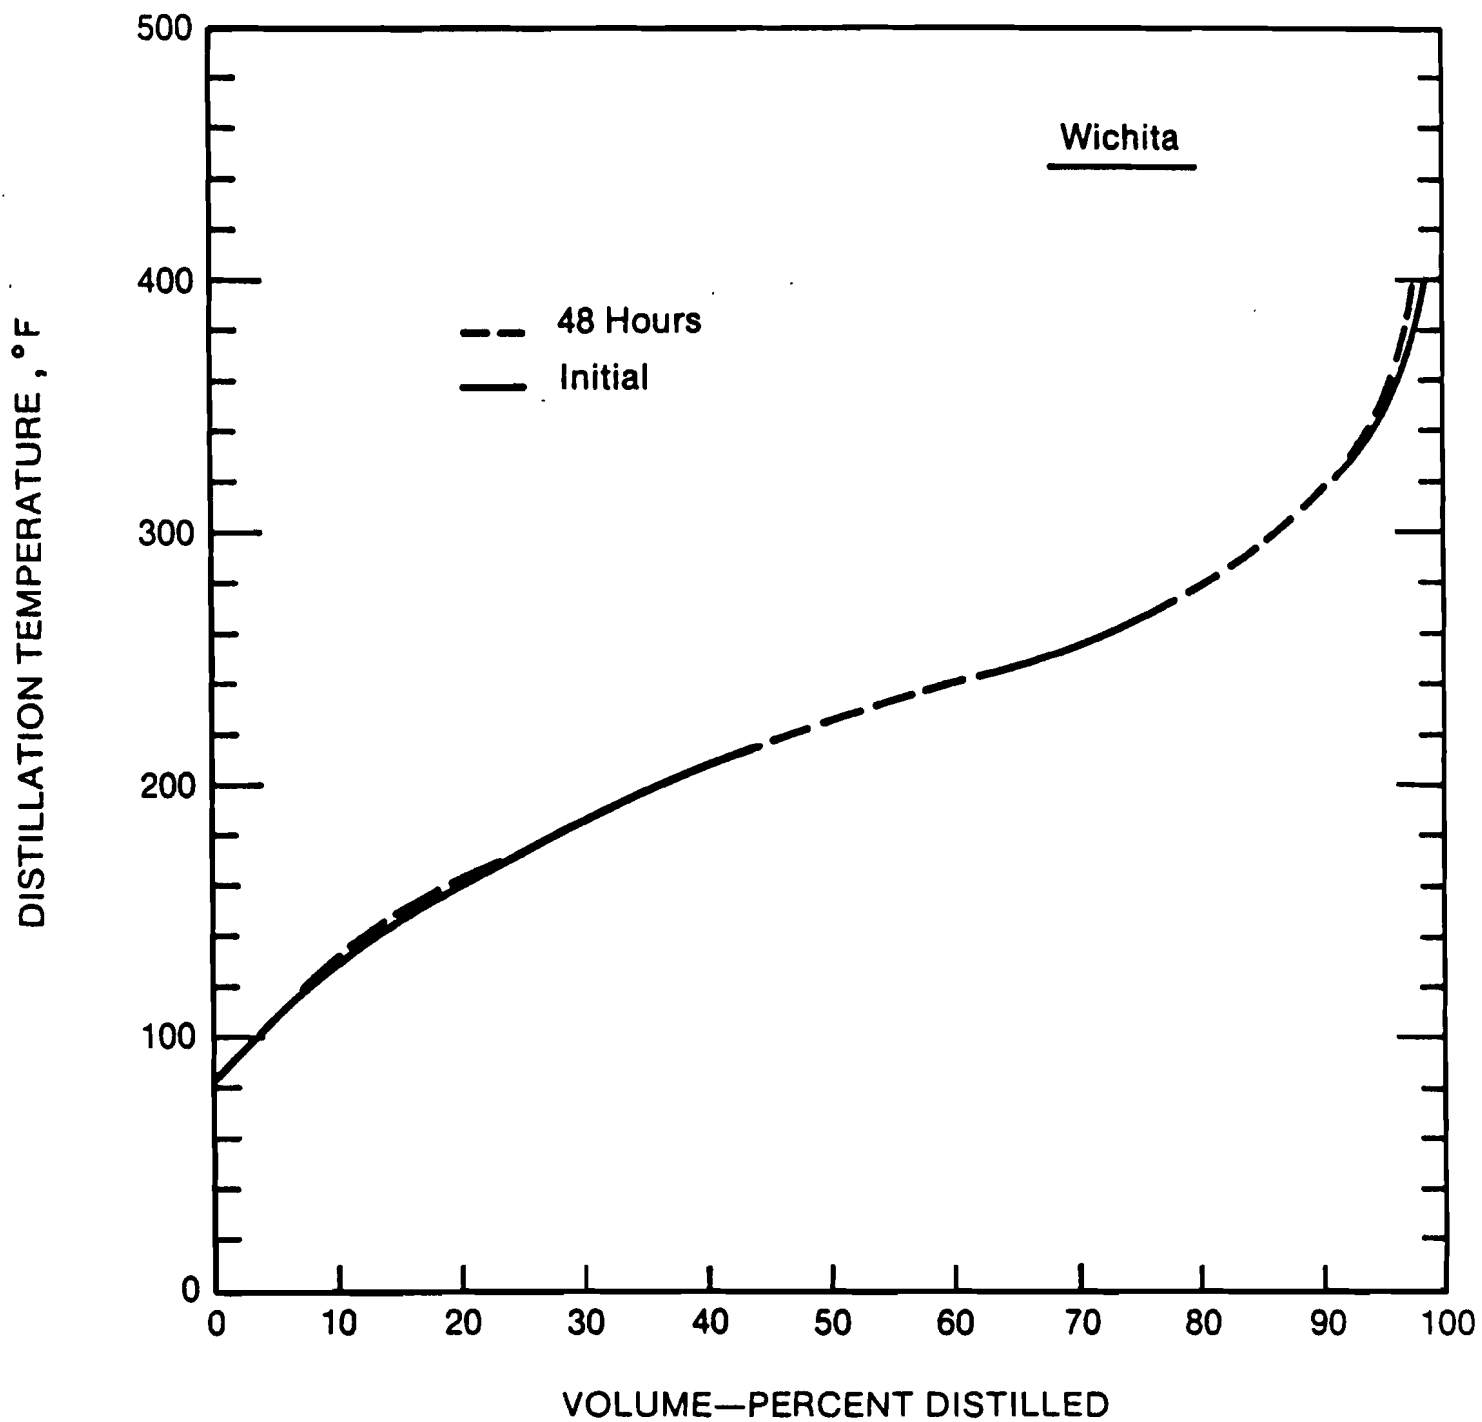


FIGURE 25. - Changes in distillation character due to weathering, summer fuel from Wichita.

TABLE 15. - Fuel composition summary - Denver - summer

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                          |                   |                |                  | <u>Total</u> |
|---------------|----------------|--------------------------|-------------------|----------------|------------------|--------------|
|               | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 2             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 3             | 0.46           | 0.00                     | 0.00              | 0.02           | 0.00             | 0.48         |
| 4             | 2.77           | 1.54                     | 0.00              | 1.58           | 0.00             | 5.89         |
| 5             | 6.20           | 7.89                     | 0.17              | 3.25           | 0.00             | 17.52        |
| 6             | 4.68           | 7.18                     | 3.13              | 4.01           | 1.48             | 20.48        |
| 7             | 2.40           | 6.29                     | 1.64              | 3.22           | 7.78             | 21.33        |
| 8             | 0.92           | 5.48                     | 1.06              | 0.46           | 9.14             | 17.07        |
| 9             | 0.24           | 3.08                     | 0.09              | 0.00           | 7.30             | 10.72        |
| 10            | 0.13           | 0.87                     | 0.00              | 0.00           | 4.46             | 5.47         |
| 11            | 0.08           | 0.20                     | 0.00              | 0.00           | 0.63             | 0.91         |
| 12            | 0.00           | 0.13                     | 0.00              | 0.00           | 0.00             | 0.13         |
| Total         | 17.89          | 32.67                    | 6.10              | 12.54          | 30.80            | 100.00       |

Average Molecular Weight = 92.23

Average Density = .736

Average Carbon Number = 6.64

H/C Ratio = 1.85

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | <u>Total</u> |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|--------------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 3             | 0.24            | 0.00                     | 0.00              | 0.11           | 0.00             | 0.35         |
| 4             | 8.91            | 1.94                     | 0.00              | 1.11           | 0.00             | 11.96        |
| 5             | 3.90            | 5.09                     | 0.12              | 2.04           | 0.00             | 11.15        |
| 6             | 3.91            | 5.89                     | 2.73              | 3.26           | 1.19             | 16.97        |
| 7             | 2.34            | 6.03                     | 1.62              | 3.39           | 7.92             | 21.30        |
| 8             | 1.00            | 5.53                     | 1.25              | 0.38           | 10.35            | 18.52        |
| 9             | 0.27            | 3.45                     | 0.09              | 0.00           | 8.57             | 12.38        |
| 10            | 0.14            | 0.93                     | 0.00              | 0.00           | 5.15             | 6.23         |
| 11            | 0.09            | 0.21                     | 0.00              | 0.00           | 0.71             | 1.02         |
| 12            | 0.00            | 0.13                     | 0.00              | 0.00           | 0.00             | 0.13         |
| Total         | 20.80           | 29.19                    | 5.82              | 10.29          | 33.89            | 100.00       |

Average Molecular Weight = 92.41

Average Density = .740

Average Carbon Number = 6.19

H/C Ratio = 1.83

TABLE 16. - Fuel composition summary - Wichita - summer

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |              |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | <u>Total</u> |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |              |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 3                                                            | 0.11           | 0.00                 | 0.00              | 0.07           | 0.00             | 0.17         |
| 4                                                            | 6.48           | 1.05                 | 0.00              | 1.79           | 0.00             | 9.33         |
| 5                                                            | 2.72           | 5.94                 | 0.08              | 2.57           | 0.00             | 11.32        |
| 6                                                            | 2.27           | 5.41                 | 0.87              | 3.19           | 1.41             | 13.15        |
| 7                                                            | 1.49           | 7.27                 | 1.72              | 2.56           | 6.85             | 19.90        |
| 8                                                            | 0.49           | 19.98                | 0.91              | 0.38           | 9.33             | 31.08        |
| 9                                                            | 0.12           | 4.23                 | 0.20              | 0.00           | 5.81             | 10.35        |
| 10                                                           | 0.04           | 1.56                 | 0.00              | 0.00           | 2.88             | 4.48         |
| 11                                                           | 0.02           | 0.01                 | 0.00              | 0.00           | 0.20             | 0.23         |
| 12                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| Total                                                        | 13.75          | 45.44                | 3.77              | 10.57          | 26.48            | 100.00       |

Average Molecular Weight = 94.48

Average Density = .730

Average Carbon Number = 6.78

H/C Ratio = 1.91

| <u>48 Hours</u> |               |                      |                   |                |                  |              |
|-----------------|---------------|----------------------|-------------------|----------------|------------------|--------------|
| Carbon No.      | <u>Normal</u> | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | <u>Total</u> |
| 1               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 2               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 3               | 0.08          | 0.00                 | 0.00              | 0.04           | 0.00             | 0.13         |
| 4               | 7.55          | 1.21                 | 0.00              | 1.57           | 0.00             | 10.33        |
| 5               | 1.41          | 3.22                 | 0.05              | 1.28           | 0.00             | 5.96         |
| 6               | 2.20          | 4.15                 | 0.73              | 1.99           | 1.04             | 10.12        |
| 7               | 1.49          | 6.78                 | 1.53              | 2.33           | 6.92             | 19.04        |
| 8               | 0.59          | 21.42                | 1.10              | 0.34           | 11.37            | 34.83        |
| 9               | 0.16          | 5.10                 | 0.25              | 0.00           | 7.81             | 13.31        |
| 10              | 0.05          | 2.24                 | 0.00              | 0.00           | 3.68             | 5.97         |
| 11              | 0.03          | 0.02                 | 0.00              | 0.00           | 0.27             | 0.32         |
| 12              | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| Total           | 13.56         | 44.14                | 3.66              | 7.56           | 31.08            | 100.00       |

Average Molecular Weight = 97.65

Average Density = .741

Average Carbon Number = 6.62

H/C Ratio = 1.87

TABLE 17. - Fuel composition summary - Washington, DC - summer

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                          |                   |                |                  | Total  |
|---------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.61           | 0.00                     | 0.00              | 0.08           | 0.00             | 0.68   |
| 4             | 7.72           | 2.47                     | 0.00              | 2.06           | 0.00             | 12.26  |
| 5             | 4.69           | 8.99                     | 0.16              | 4.42           | 0.00             | 18.26  |
| 6             | 2.83           | 7.15                     | 1.78              | 4.22           | 1.43             | 17.41  |
| 7             | 1.45           | 4.96                     | 1.68              | 2.51           | 5.82             | 16.40  |
| 8             | 0.54           | 8.83                     | 0.85              | 0.20           | 8.06             | 18.49  |
| 9             | 0.18           | 2.74                     | 0.07              | 0.00           | 7.07             | 10.06  |
| 10            | 0.12           | 0.83                     | 0.00              | 0.00           | 4.47             | 5.42   |
| 11            | 0.12           | 0.18                     | 0.00              | 0.00           | 0.58             | 0.88   |
| 12            | 0.06           | 0.08                     | 0.00              | 0.00           | 0.00             | 0.14   |
| Total         | 18.32          | 36.23                    | 4.54              | 13.49          | 27.41            | 100.00 |

Average Molecular Weight = 89.26

Average Density = .722

Average Carbon Number = 6.15

H/C Ratio = 1.90

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | Total  |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.57            | 0.00                     | 0.00              | 0.05           | 0.00             | 0.61   |
| 4             | 7.36            | 2.34                     | 0.00              | 1.89           | 0.00             | 11.59  |
| 5             | 4.64            | 8.87                     | 0.16              | 4.37           | 0.00             | 18.04  |
| 6             | 2.87            | 7.19                     | 1.78              | 4.27           | 1.43             | 17.53  |
| 7             | 1.47            | 5.01                     | 1.69              | 2.52           | 5.90             | 16.60  |
| 8             | 0.58            | 8.95                     | 0.90              | 0.21           | 8.24             | 18.88  |
| 9             | 0.18            | 2.81                     | 0.08              | 0.00           | 7.24             | 10.32  |
| 10            | 0.12            | 0.90                     | 0.00              | 0.00           | 4.40             | 5.41   |
| 11            | 0.13            | 0.18                     | 0.00              | 0.00           | 0.55             | 0.86   |
| 12            | 0.07            | 0.08                     | 0.00              | 0.00           | 0.00             | 0.15   |
| Total         | 18.00           | 36.34                    | 4.61              | 13.30          | 27.75            | 100.00 |

Average Molecular Weight = 89.76

Average Density = .724

Average Carbon Number = 6.20

H/C Ratio = 1.89



TABLE 18. - Fuel composition summary - San Diego - summer

| Volume-percent Summation by Carbon Number and Compound Class |                |                          |                   |                |                  |        |
|--------------------------------------------------------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
| Carbon<br>No.                                                | <u>Initial</u> |                          |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.28           | 0.00                     | 0.00              | 0.08           | 0.00             | 0.36   |
| 4                                                            | 15.37          | 2.61                     | 0.00              | 3.61           | 0.00             | 21.59  |
| 5                                                            | 3.67           | 10.72                    | 0.13              | 3.34           | 0.00             | 17.85  |
| 6                                                            | 2.37           | 7.80                     | 2.98              | 3.81           | 1.28             | 18.25  |
| 7                                                            | 1.15           | 4.79                     | 1.87              | 2.45           | 5.67             | 15.93  |
| 8                                                            | 0.43           | 3.71                     | 0.99              | 0.09           | 8.06             | 13.28  |
| 9                                                            | 0.12           | 2.02                     | 0.05              | 0.00           | 6.36             | 8.55   |
| 10                                                           | 0.06           | 0.19                     | 0.00              | 0.00           | 3.28             | 3.53   |
| 11                                                           | 0.00           | 0.02                     | 0.00              | 0.00           | 0.18             | 0.20   |
| 12                                                           | 0.00           | 0.48                     | 0.00              | 0.00           | 0.00             | 0.48   |
| Total                                                        | 23.47          | 32.32                    | 6.02              | 13.37          | 24.82            | 100.00 |

Average Molecular Weight = 83.84

Average Density = .707

Average Carbon Number = 5.13

H/C Ratio = 1.94

| <u>48 Hours</u> |               |                          |                   |                |                  |              |
|-----------------|---------------|--------------------------|-------------------|----------------|------------------|--------------|
| Carbon<br>No.   | <u>Normal</u> | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | <u>Total</u> |
| 1               | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 2               | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 3               | 0.15          | 0.00                     | 0.00              | 0.05           | 0.00             | 0.20         |
| 4               | 7.15          | 1.30                     | 0.00              | 2.09           | 0.00             | 10.54        |
| 5               | 2.97          | 11.39                    | 0.15              | 4.62           | 0.00             | 19.13        |
| 6               | 2.32          | 8.63                     | 3.36              | 4.53           | 1.48             | 20.32        |
| 7               | 1.30          | 5.55                     | 2.13              | 2.79           | 6.43             | 18.20        |
| 8               | 0.53          | 4.33                     | 1.38              | 0.21           | 9.23             | 15.67        |
| 9               | 0.14          | 2.35                     | 0.08              | 0.00           | 7.44             | 10.02        |
| 10              | 0.08          | 0.50                     | 0.00              | 0.00           | 4.20             | 4.78         |
| 11              | 0.06          | 0.16                     | 0.00              | 0.00           | 0.65             | 0.87         |
| 12              | 0.00          | 0.23                     | 0.00              | 0.00           | 0.05             | 0.28         |
| Total           | 14.71         | 34.43                    | 7.09              | 14.28          | 29.49            | 100.00       |

Average Molecular Weight = 89.32

Average Density = .729

Average Carbon Number = 6.08

H/C Ratio = 1.87

TABLE 19. - Fuel composition summary - Houston - summer

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                          |                   |                |                  | Total  |
|---------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.07           | 0.00                     | 0.00              | 0.03           | 0.00             | 0.10   |
| 4             | 5.67           | 0.88                     | 0.00              | 2.36           | 0.00             | 8.91   |
| 5             | 3.01           | 7.93                     | 0.11              | 4.64           | 0.00             | 15.69  |
| 6             | 1.89           | 5.61                     | 1.31              | 2.85           | 1.20             | 12.85  |
| 7             | 1.09           | 4.29                     | 0.91              | 1.47           | 9.52             | 17.27  |
| 8             | 0.35           | 15.41                    | 0.44              | 0.10           | 12.24            | 28.53  |
| 9             | 0.22           | 1.95                     | 0.00              | 0.00           | 8.96             | 11.12  |
| 10            | 0.08           | 0.22                     | 0.00              | 0.00           | 4.29             | 4.59   |
| 11            | 0.02           | 0.00                     | 0.00              | 0.00           | 0.61             | 0.63   |
| 12            | 0.00           | 0.31                     | 0.00              | 0.00           | 0.00             | 0.31   |
| Total         | 12.39          | 36.59                    | 2.75              | 11.45          | 36.81            | 100.00 |

Average Molecular Weight = 93.15

Average Density = .747

Average Carbon Number = 6.74

H/C Ratio = 1.79

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | Total  |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.53            | 0.00                     | 0.00              | 0.04           | 0.00             | 0.57   |
| 4             | 7.95            | 2.36                     | 0.00              | 2.19           | 0.00             | 12.50  |
| 5             | 2.81            | 7.33                     | 0.10              | 4.49           | 0.00             | 14.73  |
| 6             | 1.78            | 5.30                     | 1.43              | 2.77           | 1.14             | 12.42  |
| 7             | 1.06            | 4.14                     | 1.05              | 1.17           | 9.27             | 16.68  |
| 8             | 0.34            | 14.63                    | 0.45              | 0.02           | 11.99            | 27.44  |
| 9             | 0.20            | 1.88                     | 0.00              | 0.00           | 8.54             | 10.62  |
| 10            | 0.08            | 0.14                     | 0.00              | 0.00           | 4.04             | 4.26   |
| 11            | 0.00            | 0.00                     | 0.00              | 0.00           | 0.45             | 0.45   |
| 12            | 0.00            | 0.33                     | 0.00              | 0.00           | 0.00             | 0.33   |
| Total         | 14.75           | 36.12                    | 3.03              | 10.68          | 35.43            | 100.00 |

Average Molecular Weight = 91.07

Average Density = .740

Average Carbon Number = 6.32

H/C Ratio = 1.81

TABLE 20. - Fuel composition summary - Sacramento - summer

| Volume-percent Summation by Carbon Number and Compound Class |                |                          |                   |                |                  |        |
|--------------------------------------------------------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
| Carbon<br>No.                                                | <u>Initial</u> |                          |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.27           | 0.00                     | 0.00              | 0.08           | 0.00             | 0.35   |
| 4                                                            | 8.72           | 1.88                     | 0.00              | 1.08           | 0.00             | 11.68  |
| 5                                                            | 1.70           | 4.80                     | 0.09              | 2.04           | 0.00             | 8.63   |
| 6                                                            | 2.20           | 5.63                     | 1.21              | 2.97           | 2.84             | 14.85  |
| 7                                                            | 1.57           | 5.02                     | 0.92              | 1.87           | 12.68            | 22.06  |
| 8                                                            | 0.57           | 5.43                     | 0.38              | 0.11           | 17.06            | 23.54  |
| 9                                                            | 0.23           | 1.44                     | 0.00              | 0.00           | 11.73            | 13.40  |
| 10                                                           | 0.09           | 0.18                     | 0.00              | 0.00           | 4.66             | 4.92   |
| 11                                                           | 0.00           | 0.00                     | 0.00              | 0.00           | 0.55             | 0.55   |
| 12                                                           | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 15.35          | 24.37                    | 2.60              | 8.16           | 49.52            | 100.00 |

Average Molecular Weight = 93.00

Average Density = .766

Average Carbon Number = 6.34

H/C Ratio = 1.67

| <u>48 Hours</u> |               |                          |                   |                |                  |              |
|-----------------|---------------|--------------------------|-------------------|----------------|------------------|--------------|
| Carbon<br>No.   | <u>Normal</u> | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | <u>Total</u> |
| 1               | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 2               | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| 3               | 0.24          | 0.00                     | 0.00              | 0.10           | 0.00             | 0.33         |
| 4               | 8.68          | 1.82                     | 0.00              | 1.06           | 0.00             | 11.56        |
| 5               | 1.71          | 4.71                     | 0.09              | 2.07           | 0.00             | 8.57         |
| 6               | 2.16          | 5.65                     | 1.23              | 3.05           | 2.92             | 15.02        |
| 7               | 1.57          | 5.04                     | 0.93              | 1.88           | 12.80            | 22.22        |
| 8               | 0.57          | 5.45                     | 0.38              | 0.11           | 16.94            | 23.45        |
| 9               | 0.23          | 1.35                     | 0.00              | 0.00           | 11.72            | 13.30        |
| 10              | 0.09          | 0.13                     | 0.00              | 0.00           | 4.71             | 4.93         |
| 11              | 0.00          | 0.05                     | 0.00              | 0.00           | 0.56             | 0.62         |
| 12              | 0.00          | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00         |
| Total           | 15.24         | 24.21                    | 2.63              | 8.27           | 49.65            | 100.00       |

Average Molecular Weight = 93.04

Average Density = .766

Average Carbon Number = 6.34

H/C Ratio = 1.66

TABLE 21. - Fuel composition summary - Fort Lauderdale - summer

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.50           | 0.00                 | 0.00              | 0.07           | 0.00             | 0.57   |
| 4                                                            | 7.85           | 2.58                 | 0.00              | 1.67           | 0.00             | 12.10  |
| 5                                                            | 5.38           | 7.40                 | 0.16              | 3.28           | 0.00             | 16.22  |
| 6                                                            | 1.26           | 4.03                 | 0.63              | 1.82           | 0.93             | 8.67   |
| 7                                                            | 1.12           | 3.77                 | 0.88              | 0.99           | 11.09            | 17.85  |
| 8                                                            | 0.55           | 14.80                | 0.24              | 0.10           | 11.52            | 27.22  |
| 9                                                            | 0.18           | 1.41                 | 0.00              | 0.00           | 8.90             | 10.49  |
| 10                                                           | 0.08           | 0.47                 | 0.00              | 0.00           | 5.04             | 5.59   |
| 11                                                           | 0.00           | 0.46                 | 0.00              | 0.00           | 0.62             | 1.08   |
| 12                                                           | 0.00           | 0.22                 | 0.00              | 0.00           | 0.00             | 0.22   |
| Total                                                        | 16.93          | 35.12                | 1.92              | 7.94           | 38.10            | 100.00 |

Average Molecular Weight = 91.95

Average Density = .743

Average Carbon Number = 6.42

H/C Ratio = 1.79

48 Hours

| Carbon No. | <u>48 Hours</u> |                      |                   |                |                  | Total  |
|------------|-----------------|----------------------|-------------------|----------------|------------------|--------|
|            | <u>Normal</u>   | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1          | 0.00            | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2          | 0.00            | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3          | 0.12            | 0.00                 | 0.00              | 0.08           | 0.00             | 0.20   |
| 4          | 8.25            | 1.42                 | 0.00              | 0.68           | 0.00             | 10.35  |
| 5          | 2.79            | 3.91                 | 0.10              | 2.12           | 0.00             | 8.92   |
| 6          | 1.07            | 3.15                 | 0.60              | 2.16           | 0.77             | 7.75   |
| 7          | 1.19            | 3.34                 | 0.59              | 0.72           | 12.13            | 17.98  |
| 8          | 0.67            | 16.82                | 0.31              | 0.11           | 14.33            | 32.24  |
| 9          | 0.24            | 1.76                 | 0.00              | 0.00           | 11.64            | 13.64  |
| 10         | 0.10            | 0.61                 | 0.00              | 0.00           | 6.60             | 7.30   |
| 11         | 0.01            | 0.65                 | 0.00              | 0.00           | 0.80             | 1.47   |
| 12         | 0.00            | 0.17                 | 0.00              | 0.00           | 0.00             | 0.17   |
| Total      | 14.43           | 31.83                | 1.60              | 5.88           | 46.26            | 100.00 |

Average Molecular Weight = 97.01

Average Density = .766

Average Carbon Number = 6.64

H/C Ratio = 1.71

TABLE 22. - Fuel composition summary - Duluth - summer

| Volume-percent Summation by Carbon Number and Compound Class |                |                      |                   |                |                  |        |
|--------------------------------------------------------------|----------------|----------------------|-------------------|----------------|------------------|--------|
| Carbon No.                                                   | <u>Initial</u> |                      |                   |                |                  | Total  |
|                                                              | <u>Normal</u>  | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 2                                                            | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| 3                                                            | 0.63           | 0.00                 | 0.00              | 0.04           | 0.00             | 0.67   |
| 4                                                            | 9.86           | 3.71                 | 0.00              | 2.19           | 0.00             | 15.76  |
| 5                                                            | 2.60           | 5.94                 | 0.05              | 1.34           | 0.00             | 9.94   |
| 6                                                            | 2.27           | 5.81                 | 0.88              | 2.09           | 2.20             | 13.24  |
| 7                                                            | 1.29           | 6.79                 | 1.44              | 1.66           | 8.09             | 19.28  |
| 8                                                            | 0.41           | 18.28                | 0.25              | 0.06           | 9.04             | 28.06  |
| 9                                                            | 0.09           | 1.68                 | 0.00              | 0.00           | 6.17             | 7.95   |
| 10                                                           | 0.04           | 1.00                 | 0.00              | 0.00           | 3.61             | 4.65   |
| 11                                                           | 0.02           | 0.19                 | 0.00              | 0.00           | 0.25             | 0.47   |
| 12                                                           | 0.00           | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00   |
| Total                                                        | 17.21          | 43.40                | 2.63              | 7.39           | 29.36            | 100.00 |

Average Molecular Weight = 90.48

Average Density = .725

Average Carbon Number = 6.24

H/C Ratio = 1.89

| <u>48 Hours</u> |               |                      |                   |                |                  |              |
|-----------------|---------------|----------------------|-------------------|----------------|------------------|--------------|
| Carbon No.      | <u>Normal</u> | <u>Paraffins Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> | <u>Total</u> |
| 1               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 2               | 0.00          | 0.00                 | 0.00              | 0.00           | 0.00             | 0.00         |
| 3               | 0.08          | 0.00                 | 0.00              | 0.04           | 0.00             | 0.12         |
| 4               | 7.07          | 1.32                 | 0.00              | 1.24           | 0.00             | 9.63         |
| 5               | 1.28          | 2.95                 | 0.04              | 0.69           | 0.00             | 4.95         |
| 6               | 2.03          | 4.51                 | 0.81              | 1.52           | 1.68             | 10.56        |
| 7               | 1.44          | 7.14                 | 1.43              | 1.68           | 8.98             | 20.68        |
| 8               | 0.56          | 21.29                | 0.36              | 0.07           | 12.14            | 34.41        |
| 9               | 0.14          | 2.34                 | 0.00              | 0.00           | 9.14             | 11.61        |
| 10              | 0.06          | 1.56                 | 0.00              | 0.00           | 5.44             | 7.06         |
| 11              | 0.04          | 0.09                 | 0.00              | 0.00           | 0.77             | 0.90         |
| 12              | 0.00          | 0.08                 | 0.00              | 0.00           | 0.00             | 0.08         |
| Total           | 12.69         | 41.28                | 2.64              | 5.25           | 38.15            | 100.00       |

Average Molecular Weight = 98.22

Average Density = .754

Average Carbon Number = 6.73

H/C Ratio = 1.79

TABLE 23. - Fuel composition summary - New Orleans - summer

## Volume-percent Summation by Carbon Number and Compound Class

| Carbon<br>No. | <u>Initial</u> |                          |                   |                |                  | Total  |
|---------------|----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>  | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00           | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.59           | 0.00                     | 0.00              | 0.10           | 0.00             | 0.69   |
| 4             | 8.74           | 3.65                     | 0.00              | 2.10           | 0.00             | 14.49  |
| 5             | 5.23           | 6.29                     | 0.14              | 2.70           | 0.00             | 14.36  |
| 6             | 4.24           | 6.43                     | 2.24              | 3.63           | 1.71             | 18.25  |
| 7             | 1.61           | 5.27                     | 1.25              | 2.14           | 7.21             | 17.48  |
| 8             | 0.54           | 5.19                     | 0.81              | 0.15           | 10.29            | 16.98  |
| 9             | 0.16           | 2.51                     | 0.08              | 0.00           | 8.30             | 11.05  |
| 10            | 0.08           | 0.63                     | 0.00              | 0.00           | 4.82             | 5.53   |
| 11            | 0.05           | 0.19                     | 0.00              | 0.00           | 0.68             | 0.92   |
| 12            | 0.00           | 0.20                     | 0.00              | 0.00           | 0.04             | 0.24   |
| Total         | 21.24          | 30.37                    | 4.51              | 10.83          | 33.06            | 100.00 |

Average Molecular Weight = 89.21

Average Density = .731

Average Carbon Number = 6.16

H/C Ratio = 1.84

48 Hours

| Carbon<br>No. | <u>48 Hours</u> |                          |                   |                |                  | Total  |
|---------------|-----------------|--------------------------|-------------------|----------------|------------------|--------|
|               | <u>Normal</u>   | <u>Paraffins<br/>Iso</u> | <u>Naphthenes</u> | <u>Olefins</u> | <u>Aromatics</u> |        |
| 1             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 2             | 0.00            | 0.00                     | 0.00              | 0.00           | 0.00             | 0.00   |
| 3             | 0.54            | 0.00                     | 0.00              | 0.08           | 0.00             | 0.63   |
| 4             | 6.91            | 3.15                     | 0.00              | 2.15           | 0.00             | 12.21  |
| 5             | 5.37            | 5.93                     | 0.14              | 2.72           | 0.00             | 14.16  |
| 6             | 4.29            | 6.48                     | 2.27              | 3.64           | 1.74             | 18.42  |
| 7             | 1.66            | 5.40                     | 1.40              | 2.15           | 7.50             | 18.11  |
| 8             | 0.57            | 5.26                     | 0.85              | 0.15           | 10.75            | 17.58  |
| 9             | 0.16            | 2.74                     | 0.08              | 0.00           | 8.64             | 11.62  |
| 10            | 0.28            | 0.55                     | 0.00              | 0.00           | 5.30             | 6.13   |
| 11            | 0.05            | 0.19                     | 0.00              | 0.00           | 0.67             | 0.91   |
| 12            | 0.00            | 0.19                     | 0.00              | 0.00           | 0.04             | 0.23   |
| Total         | 19.84           | 29.90                    | 4.74              | 10.89          | 34.63            | 100.00 |

Average Molecular Weight = 90.64

Average Density = .737

Average Carbon Number = 6.27

H/C Ratio = 1.82

TABLE 24. - Fuel composition summary - Chicago - summer

| Volume-percent Summation by Carbon Number and Compound Class |        |               |            |         |           |        |
|--------------------------------------------------------------|--------|---------------|------------|---------|-----------|--------|
| <u>Initial</u>                                               |        |               |            |         |           |        |
| Carbon No.                                                   | Normal | Paraffins Iso | Naphthenes | Olefins | Aromatics | Total  |
| 1                                                            | 0.00   | 0.00          | 0.00       | 0.00    | 0.00      | 0.00   |
| 2                                                            | 0.00   | 0.00          | 0.00       | 0.00    | 0.00      | 0.00   |
| 3                                                            | 0.67   | 0.00          | 0.00       | 0.04    | 0.00      | 0.71   |
| 4                                                            | 6.30   | 2.57          | 0.00       | 1.93    | 0.00      | 10.80  |
| 5                                                            | 5.94   | 10.82         | 0.21       | 6.56    | 0.00      | 23.53  |
| 6                                                            | 3.78   | 10.04         | 2.95       | 5.22    | 1.99      | 23.98  |
| 7                                                            | 1.64   | 4.40          | 1.55       | 2.53    | 8.10      | 18.22  |
| 8                                                            | 0.66   | 3.86          | 0.71       | 0.18    | 4.79      | 10.19  |
| 9                                                            | 0.09   | 1.75          | 0.06       | 0.00    | 5.02      | 6.93   |
| 10                                                           | 0.09   | 0.30          | 0.00       | 0.00    | 3.80      | 4.20   |
| 11                                                           | 0.16   | 0.16          | 0.00       | 0.00    | 0.67      | 0.99   |
| 12                                                           | 0.13   | 0.26          | 0.00       | 0.00    | 0.04      | 0.44   |
| Total                                                        | 19.47  | 34.16         | 5.49       | 16.46   | 24.42     | 100.00 |

Average Molecular Weight = 85.82

Average Density = .716

Average Carbon Number = 5.91

H/C Ratio = 1.91

| <u>48 Hours</u> |        |               |            |         |           |        |
|-----------------|--------|---------------|------------|---------|-----------|--------|
| Carbon No.      | Normal | Paraffins Iso | Naphthenes | Olefins | Aromatics | Total  |
| 1               | 0.00   | 0.00          | 0.00       | 0.00    | 0.00      | 0.00   |
| 2               | 0.00   | 0.00          | 0.00       | 0.00    | 0.00      | 0.00   |
| 3               | 0.09   | 0.00          | 0.00       | 0.05    | 0.00      | 0.15   |
| 4               | 6.98   | 1.17          | 0.00       | 1.63    | 0.00      | 9.79   |
| 5               | 2.34   | 4.55          | 0.12       | 3.17    | 0.00      | 10.18  |
| 6               | 2.98   | 7.39          | 2.44       | 3.73    | 1.48      | 18.03  |
| 7               | 1.95   | 4.94          | 1.86       | 3.27    | 10.42     | 22.44  |
| 8               | 1.00   | 6.02          | 1.32       | 0.25    | 8.31      | 16.90  |
| 9               | 0.16   | 2.99          | 0.11       | 0.00    | 9.00      | 12.26  |
| 10              | 0.17   | 0.81          | 0.00       | 0.00    | 6.51      | 7.49   |
| 11              | 0.29   | 0.31          | 0.00       | 0.00    | 1.04      | 1.63   |
| 12              | 0.24   | 0.79          | 0.00       | 0.00    | 0.11      | 1.14   |
| Total           | 16.20  | 28.98         | 5.85       | 12.10   | 36.87     | 100.00 |

Average Molecular Weight = 94.21

Average Density = .752

Average Carbon Number = 6.39

H/C Ratio = 1.78

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65  
66  
67  
68  
69  
70  
71  
72  
73  
74  
75  
76  
77  
78  
79  
80  
81  
82  
83  
84  
85  
86  
87  
88  
89  
90  
91  
92  
93  
94  
95  
96  
97  
98  
99  
100



APPENDIX A

DISTRIBUTION LIST

Jack Acampora, ANM-174W  
Western ACO  
P.O. Box 92007  
Worldway Postal Center  
Los Angeles, CA 90009-2007

William Ackerman  
6B1 Adams Building  
Bartlesville, OK 74005

Jerry Allsup  
National Institute for  
Petroleum & Energy Research  
P.O. Box 2128  
Bartlesville, OK 74005

Bob Alpiser  
Chicago ACO  
2300 East Devon  
Des Plaines, IL 60018

Neils Andersen  
Senior VP - Engineering  
AVTEK Corporation  
4680 Calle Carga  
Camarillo, CA 93010

Oscar Ball, ACE-112  
DOT/FAA Central Region  
601 East 12th Street  
Kansas City, MO 64106

Paul Benjunas  
Engineer I  
Textron Lycoming  
550 South Main Street  
Stratford, CT 06497

Dave Bently  
Aerospace Program Manager  
Society of Automotive Engineers  
400 Commonwealth Drive  
Warrendale, PA 15096

Bob Berman, AWS-110  
DOT/FAA National Headquarters  
800 Independence Ave., SW.  
Washington, DC 20591

Bernard Berns  
Accident Prevention Spl.  
Alaska FSDO-61  
3788 University Avenue  
Fairbanks, AK 99709

Robert Blair  
Aviation Safety Inspector  
WP - FSDO-13  
218 Lagoon Road, Room 215  
Honolulu, HI 96819

Raymond Boice, ACE-107  
DOT/FAA Central Region  
601 East 12th Street  
Kansas City, MO 64106

Carl Borchers  
FSDO #2  
1387 Airport Boulevard  
San Jose, CA 95110

Raymond Borowski, ANE-170  
New York ACO  
181 South Franklin Avenue  
Room 202  
Valley Stream, NY 11581

Michael Bragg  
Ohio State University  
2300 West Case Road  
Columbus, OH 43220

Richard Brandiger  
Principal Airworthiness Insp.  
GL-FSDO-66  
RR2, Box 4750  
Rapid City, SD 57701

Steve Brown  
AOPA  
421 Aviation Way  
Frederick, MD 21701

Dr. Burtner  
Sun Refining and Marketing  
ARD Department  
P.O. Box 1226  
Marcus Hook, PA 19061-0526

Hank Burwash, ANM-174W  
Western ACO  
P.O. Box 92007  
Worldway Postal Center  
Los Angeles, CA 90009-2007

Gene Chartier, ANM-174W  
FAA Western ACO  
P.O. Box 92007  
World Way Postal Center  
Los Angeles, CA 90009-2007

Burton Chesterfield  
Transportation Safety Institute, DMA-60  
6500 South MacArthur Boulevard  
Oklahoma City, OK 73125

Ernest Cross, Jr.  
College of Engineering  
Old Dominion University  
Norfolk, VA 23508

Terence Dixon  
Boeing Aerospace Corporation  
P.O. Box 3999  
M/S 8M-11  
Seattle, WA 98124

David Downing  
Department of Aerospace Engineering  
The University of Kansas  
2004 Learned Hall  
Lawrence, KS 66045-2221

Locke Easton, ANE-141  
DOT/FAA New England Region  
12 New England Executive Park  
Burlington, MA 01803

Eldon Elam  
Air Safety Investigator  
FAA Headquarters, ASF-100  
800 Independence Avenue, SW.  
Washington, DC 20591

Frank Feinberg  
Mobil Research and Development Corp.  
Research Department  
Billingsport Road  
Paulsboro, NJ 08066

Augusto Ferrara, ACT-320  
DOT/FAA Technical Center  
Atlantic City Internat'l A/P, NJ 08405

John Garner  
Air Safety Specialist  
U.S. Army Safety Center  
ATTN: CSSC-RI  
Fort Rucker, AL 36362

Wayne Gaulzetti, ANE-153  
FAA New England Region  
12 New England Executive Park  
Burlington, MA 01803

George Heath  
Investigator  
Canadian Aviation Safety Board  
12-14220 Yellowhead Trail  
Edmonton, AB., CANADA

Roy Hettenbach, ANE-174  
New York ACO  
181 South Franklin Avenue  
Room 202  
Valley Stream, NY 11581

Alfred Hughes  
Central Region-FSDO 65  
General Aviation Building  
Lincoln Municipal Airport  
Lincoln, NE 68524

Stephen Imbrogno  
106 East Miami Avenue  
Cherry Hill, NJ 08034

Don Jacobsen, ACE-101  
DOT/FAA Central Region  
601 East 12th Street  
Kansas City, MO 64106

Eric Jevons  
Colt Industries  
Control Systems Division  
Charter Oak Boulevard  
West Hartford, CT 06101

Frank Kertis  
Sun Refining and Marketing  
ARD Department  
P.O. Box 1226  
Marcus Hook, PA 19061-0526

William Kilmartin  
Manager, Technical Services  
ARCO Chemical Company  
3801 West Chester Pike  
Newtown Square, PA 19073

Gene Kingsbury  
Room 6733  
U.S. Department of Commerce  
Washington, DC 20230

Richard Kirsch, AWS-120  
DOT/FAA National Headquarters  
800 Independence Ave., SW.  
Washington, DC 20591

Robert Koenig  
NASA Langley Reserach Center  
Mail Stop 352  
Hampton, VA 23665-5225

Harold L. Mesaris  
Manager, Field Investigations  
Avco Lycoming Textron  
652 Oliver Street  
Williamsport, PA 17701

Ted Lacara  
Prin. Aviation Safety Insp.  
Western Pacific Long Beach-FSDO-5  
2815 East Spring Street  
Long Beach, CA 90806

Damien Lawson  
Canadian Aviation Safety Board  
P.O. Box 9120  
Alta Vista Terminal  
Ottawa, Ontario K1G 3T8 CANADA

Jacob Leggett  
Chief Chemist  
Derby Refining Company  
P.O. Box 1030  
Wichita, KS 67201

R. Lewis  
Market Manager, Methyl Fuels  
Celanese Chemical Corporation  
1250 West Mockingbird Lane  
Dallas, TX 75247-0320

Donald Magnuson  
Aviation Safety Insp.  
FAA-NM-FSDO-67  
116 North 2400 West  
Salt Lake City, UT 84116

Phil Meng  
MS-500 219  
NASA Lewis Research Center  
21000 Brookpark Road  
Cleveland, OH 44135

Jay Nelson  
SW-FSDO-67  
FAA Building, Room 111  
Wiley Post Airport  
Bethany, OK 73008

Willie Nelson  
Assistant Manager (Airworthiness)  
ASO-FSDO-64  
9355 Tradeport Drive  
Orlando, FL 32827

Richard Newcombe  
Canadian Aviation Safety Board  
P.O. Box 9120  
Alta Vista Terminal  
Ottawa, Ontario K1G 3T8 CANADA

Cathy Nickolaisin  
Director  
New Jersey Division of Aeronautics  
1035 Parkway Avenue  
Trenton, NJ 08625

A. Peacock  
Douglas Aircraft Company  
Internal Mail Code 36-41  
3855 Lakewood Boulevard  
Long Beach, CA 90846

Paul Pendleton, ACE-140W  
DOT/FAA Central Region  
1801 Airport Road, Room 100  
Wichita, KS 67209

Charles Petersen  
Petersen Aviation  
Route 1, Box 18  
Minden, NE 68959

Jim Peterson, ACE-140W  
DOT/FAA Central Region  
1801 Airport Road, Room 100  
Wichita, KS 67209

David Phillips  
Textron Lycoming  
Manager, Field Investigations  
652 Oliver Street  
Williamsport, PA 17701

Harold Pierce  
Honeywell, Inc.  
1625 Zarthan Avenue, South  
P.O. Box 312  
St. Louis Park, MN 55416

Jake Plante, AEE-200  
FAA National Headquarters  
Room 431  
800 Independence Avenue, SW.  
Washington, DC 20591

Alma Ramirez, ANM-100A  
ACO  
701 C. Street  
Box 14  
Anchorage, AK 99513

Harold Riesen  
Chief, Mech/Env. Systems, R&D  
Beech Aircraft Corporation  
9709 East Central  
Wichita, KS 67201

Robert Roehm  
WP-FSDO-1  
7120 Hayvenhurst Avenue  
Suite 316  
Van Nuys, CA 91406

Dick Roemer  
EAA Aviation Foundation  
Whitman Airfield  
Oshkosh, WI 54903-2591

Russell Rogers  
Aeroquip Corporation  
Corporate Engineering  
Jackson, MI 49203

Len Royer  
Accident Investigator  
USASC  
Fort Rucker, AL 36362

John Shimski  
Naval Air Propulsion Center  
P.O. Box 7176  
Trenton, NJ 08628

Frederick Smetana  
North Carolina State University  
P.O. Box 5246  
Raleigh, NC 27650

H. Smith  
Engineered Fabrics Division  
Goodyear Aerospace Corporation  
1210 Massillon Road  
Akron, OH 44315

Hubert Smith  
Assistant Professor  
Pennsylvania State University  
233 Hammond Building  
University Park, PA 16802

Robert Stewart  
Program Manager  
Gulfstream Aerospace Corp, B-08  
P.O. Box 2206  
Savannah, GA 31402

Fen Taylor  
Chief, Aerodynamics & Performance  
Mooney Aircraft Corporation  
P.O. Box 72  
Kerrville, TX 78029

Peter Thomas  
Sundstrand Aerospace Fluid Systems  
2421 11th Street  
P.O. Box 7002  
Rockford, IL 61125-7002

Charles Turrentine  
Engineering Specialist  
General Dynamics Corporation  
P.O. Box 748, M/S 1772  
Fort Worth, TX 76101

Neil Wagstaff  
Avn. Safety Representative  
McDonnell Douglas Helicopter Company  
500 East McDowell 560/G-22A  
Mesa, AZ 85205

Donald Ward  
Associate Professor  
Aerospace Engineering Department  
Texas A&M University  
College Station, TX 77843

Richard Wares  
National Institute for  
Petroleum & Energy Research  
P.O. Box 2128  
Bartlesville, OK 74005

John Wells  
Director of Development & Certification  
Gates Learjet Corporation  
P.O. Box 7707  
Wichita, KS 67277

Louis Williams  
NASA Langley Research Center  
Mail Stop 286  
Hampton, VA 23665-5225

Edward Willis, Jr.  
NASA Lewis Research Center  
Mail Stop 77-6  
21000 Brookpark Road  
Cleveland, OH 44135

David Yeoman  
Collins-Rockwell  
MS 124-111  
400 Collins Road, NE.  
Cedar Rapids, IA 52498

Richard Yotter, ACE-109  
DOT/FAA Central Region  
601 East 12th Street  
Kansas City, MO 64106

Acro Sport, Incorporated  
P.O. Box 462  
Hales Corners, WI 53130

Adams Balloon Loft, Inc.  
27 DeKalb Peachtree Airport  
Atlanta, GA 30341

Advanced Aviation, Incorporated  
323 North Ivey Lane  
P.O. Box 16716  
Orlando, FL 32861

Aero Composites, Incorporated  
1201 4th Street  
P.O. Box 246  
Fulton, IL 61252

Aerocar, Incorporated  
P.O. Box 1171  
Longview, WA 98632

Aerospatiale Aircraft Corporation  
20 Expert Drive  
Sterling, VA 22170

Aerospatiale Helicopter Corporation  
2701 Forum Drive  
Grand Prairie, TX 75053-4005

Aerostar International, Inc.  
P.O. Box 5057  
Sioux Falls, SD 57117

Avian Balloon Company  
South 3722 Ridgeview Drive  
Spokane, WA 99206

Agusta Aviation Corporation  
Norcom and Red Lion Roads  
Philadelphia, PA 19154

Avtek Corporation  
509 Calle Carga  
Camarillo, CA 93010

Air Command Manufacturing, Incorporated  
Route 3  
P.O. Box 197A  
Liberty, MO 64068

Avtek Corporation  
509 Calle Carga  
Camarillo, CA 93010

Air Tractor, Inc.  
P.O. Box 485  
Olney, TX 76374

Ayres Corporation  
P.O. Box 3090  
Municipal Airport  
Albany, GA 31708

Aircraft Designs, Incorporated  
11082 Bel Aire Court  
Cupertino, CA 95014

Barnett Rotorcraft  
4307 Olivehurst Avenue  
Olivehurst, CA 95961

Alpha Aviation Supply Company  
P.O. Box 641  
Greenville, TX 75401

Barney Oldfield Aircraft  
P.O. Box 228  
Needham, MA 02192

Amsin Aviation, Incorporated  
P.O. Box 10993  
Pittsburgh, PA 15236

Beech Aircraft Corporation  
Box 85  
Wichita, KS 67201-0085

Arctic Aircraft Company  
P.O. Box 6-141  
Anchorage, AK 99502

Bell Helicopter Textron  
P.O. Box 482  
Fort Worth, TX 76101

Atlantic Aviation Corporation  
Westwind Sales  
Greater Wilmington Airport  
P.O. Box 15000  
Wilmington, DE 19850

Bellanca, Inc.  
P.O. Box 964  
Alexandria, MN 56308

Bensen Aircraft Corporation  
P.O. Box 31047  
Raleigh, NC 27622

CDX Aviation Sales  
11343 104th Street  
Edmonton, Alberta  
T5G 2K7  
CANADA

Boeing Commercial Airplane  
Company  
P.O. Box 3707  
Seattle, WA 98124

Cessna Aircraft Company  
P.O. Box 1521  
Wichita, KS 67201

Box 51, Ltd.  
Municipal Airport  
Route 1, Box 102  
Denton, TX 76201

Christen Industries  
P.O. Box 547  
Afton, WY 83110

British Aerospace, Inc.  
P.O. Box 17414  
Dulles Int'l Airport  
Washington, DC 20041-0414

Christen Industries, Inc.  
Aircraft Manufacturing Division  
P.O. Box 547  
Afton, WY 83110

Burkhart-Grob of America  
1070 Navajo Drive  
Bluffton Airport Complex  
Bluffton, OH 45817

De Havilland Aircraft of Canada  
Garratt Boulevard  
Downsview, Ontario M3K 1Y5  
CANADA

Bushby Aircraft, Incorporated  
647 Route 52  
Minooka, IL 60447

Denney Aerocraft Company  
6140 Morris Hill Lane  
Boise, ID 83704

Cameron Balloons, U.S.  
41 Enterprise Drive  
Ann Arbor, MI 48103

DeVore Aviation Corporation  
6104B Kircher Boulevard, NE.  
Albuquerque, NM 87109

Canadair  
274 Riverside Avenue  
Westport, CT 06880  
CANADA

Diehl Aero-Nautical  
1855 North Elm  
Jenks, OK 74037

CASA Aircraft USA, Inc.  
1215 Jefferson Davis Highway  
Suite 404  
Arlington, VA 22202

Dornier Aviation-North America, Inc.  
1213 Jefferson Davis Highway  
#1001  
Arlington, VA 22202

E. H. Industries, Limited  
Granville House  
132-135 Sloane Street  
London SW1X9BB  
ENGLAND

Eagle Balloons, Ltd.  
Hanover Municipal Airport  
Ashland, VA 23005

Earthstar Aircraft, Incorporated  
Star Route  
P.O. Box 313  
Santa Margarita, CA 93453

Eipper Aircraft  
26531 Ynez Road  
Temecula, CA 92390

Embraer Aircraft Corporation  
276 SW. 34 Street  
Fort Lauderdale, FL 33315

Enstrom Helicopter Corporation  
Twin County Airport  
P.O. Box 277  
Menominee, MI 49858

Fairchild Aircraft Corporation  
P.O. Box 32486  
San Antonio, TX 78284

Falcon Jet Corporation  
Teterboro Airport  
Teterboro, NJ 07608

Fisher Flying Products, Incorporated  
Route 2  
P.O. Box 282  
South Webster, OH 45682

Fokker Aircraft USA, Inc.  
1199 North Fairfax Street  
Suite 500  
Alexandria, VA 22314

Freedom Master Corporation  
450 Hamlin Avenue  
Satellite Beach, FL 32937

Galaxy Balloons, Inc.  
820 Salisbury Road  
Statesville, NC 28677

Gates Learjet Corporation  
P.O. Box 11186  
Tuscon, AZ 85734

General Aviation  
Manufacturers Association  
1400 K Street, NW.  
Suite 801  
Washington, DC 20005

Glaser Dirks Sailplanes, Inc.  
5847 Sharpe Road  
Calistoga, CA 94515

Graham Thomson, Ltd.  
P.O. Box 1175  
Pacific Palisades, CA 90272

Gulfstream Aerospace Corporation  
Wiley Post Airport  
P.O. Box 22500  
Oklahoma City, OK 73123

Head Balloons, Inc.  
550 Echelon Road  
Greenville, SC 29605



Hynes Aviation Industries  
P.O. Box 697  
Frederick, OK 73542

Litecraft, Inc.  
Route 4, Box 48  
Vacherie, LA 70090

INAV Limited  
895 West 20th Avenue  
P.O. Box 2984  
Oshkosh, WI 54903

Lockheed Georgia Company  
Technical Reports Department  
Department 72-34, Zone 235  
86 South Cobb Drive  
Marietta, GA 30063

Jonas Aircraft and Arms  
Company, Inc.  
225 Broadway  
New York, NY 10007

Loehle Aviation, Incorporated  
Shipmans Creek Road  
Wartrace, TN 37183

Ken Brock Manufacturing  
11852 Western Avenue  
Stanton, CA 90680

Mael Aircraft Corporation  
Box 138  
Portage, WI 53901

Ken Knowles Sport Aircraft, Incorporated  
104 East Avenue  
K-4, Unit G  
Lancaster, CA 93535

Maule Aircraft Corporation  
Lake Maule  
Route 5, Box 319  
Moultrie, GA 31768

Kolb Company  
Rural Delivery 3  
P.O. Box 38  
Phoenixville, PA 19460

MBB Helicopter Corporation  
900 Airport Road  
P.O. Box 2349  
West Chester, PA 19380

Lake Aircraft  
Laconia Airport Hangar 1  
Laconia, NH 03246

McDonnell Douglas Corporation  
3855 Lakewood Boulevard  
Long Beach, CA 90846

Light Aero, Incorporated  
4823 Aviation Way  
P.O. Box 728  
Caldwell, ID 83606

McDonnell Douglas Helicopter  
Company  
Centinela and Teale Streets  
Culver City, CA 90230

Light Miniature Aircraft  
Building 414  
Opa-Locka Airport  
Opa Locka, FL 33054

Melex USA, Inc.  
1200 Front Street  
Suite 101  
Raleigh, NC 27609

Mike Smith Aero  
Box 430  
Stanton County Airport  
Johnson City, KS 67855

Osprey Aircraft  
3741 El Ricon Way  
Sacramento, CA 95825

Mooney Aircraft Corporation  
P.O. Box 72  
Kerville, TX 78028-0072

Partenavia of America  
1235 Jefferson Davis Highway  
#500  
Arlington, VA 22202

Morris Aviation, Ltd.  
P.O. Box 718  
Statesboro Airport  
Statesboro, GA 30458

Pazmany Aircraft Corporation  
P.O. Box 80051  
San Diego, CA 92138

Mudry Aviation, Ltd.  
Dutchess City Airport  
Route 376  
Wappingers Falls, NY 12590

PIK Pacific  
1231 Second Street  
Manhattan Beach, CA 90266

National Aeronautics and Manufacturing  
Company, Incorporated  
P.O. Box 1718  
Independence, MO 64055

Piper Aircraft Corporation  
Box 1328  
Vero Beach, FL 32961

Neico Aviation  
403 South Ojai Street  
Santa Paula, CA 93060

Prescott Aeronautical Corporation  
1006 West 53rd Street, N.  
P.O. Box 4590  
Wichita, KS 67204

Nostalgaair, Incorporated  
4823 Aviation Way  
P.O. Box 2049  
Hendersonville, NC 28739

Quad City Aircraft Corporation  
3610 Coaltown Road  
Moline, IL 61265

Nuwaco Aircraft  
2978 East Euclid Place  
Littleton, CO 80121

Rand Robinson Engineering, Incorporated  
5395 Industrial Drive  
Suite A  
Huntington Beach, CA 92649

OMAC, Inc.  
P.O. Box 3530  
Albany, GA 31708

Rans Company  
1104 East Highway 40 Bypass  
Hays, KS 67601

Raven Industries, Inc.  
421 West Eighteenth Street  
Box 1007  
Sioux Falls, SD 57101

Shorts Brothers, USA, Inc.  
2011 Crystal Drive  
Suite 713  
Arlington, VA 22202-3702

Robinson Helicopter Company  
24747 Crenshaw Boulevard  
Torrance, CA 90505

Sikorsky Aircraft  
North Main Street  
Stratford, CT 06601

Rogerson Aircraft Corporation  
2201 Alton Avenue  
Irvine, CA 92714

Silhouette Aircraft Sales, Incorporated  
848 East Santa Maria Street  
Santa Paula, CA 93060

Rotec Engineering, Incorporated  
P.O. Box 220  
Duncanville, TX 75138

Skypower  
Box 236  
Tea, SD 57064

Rotorway Aircraft  
7411 West Galveston  
Chandler, AZ 85224

Sorrell Aviation, Limited  
16525 Tilley Road, S.  
Tenino, WA 98589

SAAB Aircraft of America, Inc.  
200 Fairbrook Drive  
Herndon, VA 22070

Spencer Amphibian Air Car, Incorporated  
11019 Glenoaks Boulevard  
Pacoima, CA 91331

Schleicher Sailplanes, Inc.  
P.O. Box 118  
Port Matilda, PA 16870

Squadron Aviation, Incorporated  
P.O. Box 2376  
Columbus, OH 43223

Schweizer Aircraft Corporation  
P.O. Box 147  
Elmira, NY 14902

Star-Lite Aircraft, Incorporated  
2219 Orange Blossom  
San Antonio, TX 78247

Sequoia Aircraft Corporation  
2000 Tomlynn Street  
P.O. Box 6821  
Richmond, VA 23230

Stoddard-Hamilton Aircraft,  
Incorporated  
18701 58th Avenue, NE.  
Arlington, WA 98223

Stolp Starduster Corporation  
4301 Twining  
Flabob Airport  
Riverside, CA 92509

War Aircraft Replica, Incorporated  
348 South Eighth Street  
Santa Paula, CA 93060

Swearingen Aircraft Corporation  
1234 99th Street  
San Antonio, TX 78214

Weatherly Aviation Company  
2304 San Felipe Road  
Hollister, CA 95023

Taylorcraft Aviation Corporation  
P.O. Box 947  
820 East Bald Eagle Street  
Lock Haven, PA 17745

Westland, Inc.  
7135 Jefferson Davis Highway  
Suite 805  
Arlington, VA 22202

Teenie Company  
P.O. Box 625  
Coolidge, AZ 85228

White Lightning Aircraft Corporation  
P.O. Drawer 40  
Sheldon, SC 29941

The Balloon Works  
810 Salisbury Road  
Statesville, NC 28677

Zenair, Limited  
25 King Road  
Nobleton, Ontario  
LOG 1N0  
CANADA

Thunder and Colt, U.S.  
Box 320  
Chatham, NY 12037-0320

Ultimate Aerobatics, Limited  
Guelph Airpark  
Guelph, Ontario  
N1H 6H8  
CANADA

Van's Aircraft, Incorporated  
P.O. Box 160  
North Plains, OR 97133

Wag-Aero, Incorporated  
P.O. Box 181  
Lyons, WI 53148

Civil Aviation Authority (5)  
 Aviation House  
 129 Kingsway  
 London WC2B 6NN England

DOT-FAA AEU-500 (4)  
 American Embassy  
 APO New York, NY 09667

Embassy of Australia (1)  
 Civil Air Attache  
 1601 Mass. Ave. NW  
 Washington, DC 20036

University of California (1)  
 Service Dept Institute of  
 Transportation Standard Lib  
 412 McLaughlin Hall  
 Berkely, CA 94720

Scientific & Tech. Info FAC (1)  
 ATTN: NASA Rep.  
 P.O. Box 8757 BWI Airport  
 Baltimore, MD 21240

British Embassy (1)  
 Civil Air Attache ATS  
 3100 Mass Ave. NW  
 Washington, DC 20008

Northwestern University (1)  
 Trisnet Repository  
 Transportation Center Library  
 Evanston, ILL 60201

Director DuCentre Exp DE LA (1)  
 Navigation Aerineene  
 941 Orly, France

|              |     |           |     |         |     |
|--------------|-----|-----------|-----|---------|-----|
| ANE-40       | (2) | ACT-61A   | (2) | ASW-53B | (2) |
| ASO-52C4     | (2) | AAL-400   | (2) | AAC-64D | (2) |
| APM-13 Nigro | (2) | M-493.2   | (5) | ACE-66  | (2) |
| AEA-61       | (3) | Bldg. 10A |     | ADL-1   | (1) |
| ADL-32 North | (1) | APM-1     | (1) | ALG-300 | (1) |
| AES-3        | (1) | APA-300   | (1) | ACT-5   | (1) |
| ANM-60       | (2) | AGL-60    | (2) |         |     |

ASF-1 - Office of Aviation Safety

AST-1 - Office of Science & Advanced  
 Technology

APM-1 - Program Engineer & Maintenance  
 Service

AVS-1 - Associate Administrator for  
 Aviation Standards

AWS-1 - Office of Airworthiness

AWS-1 - Aircraft Engineering Division

Faa, Chief, Civil Aviation (1)  
Assistance Group  
Madrid, Spain  
c/o American Embassy  
APO New York, NY 09285-0001

Dick Tobiason (1)  
ATA of America  
1709 New York Avenue, NW  
Washington, DC 20006

FAA Anchorage ACO (1)  
701 C Street, Box 14  
Anchorage, Alaska 99513

FAA Atlanta ACO (1)  
1075 Inner Loop Road  
College Park, Georgia 30337

FAA Boston ACO (1)  
12 New England Executive Park  
Burlington, Mass. 01803

FAA Brussels ACO (1)  
c/o American Embassy, APO  
New York, NY 09667

FAA Chicago ACO (1)  
2300 E. Devon, Room 232  
Des Plaines, Illinois 60008

FAA Denver (1)  
10455 E. 25th Ave., Suite 307  
Aurora, CO 98168

Frank Taylor (1)  
3542 Church Road  
Ellicott City, MD 21043

Mr. Gale Branden (FAA) (1)  
5928 Queenston Street  
Springfield, VA 22152

Richard E. Livingston, Jr. (1)  
Director, Aerotech Operations for  
the IAPA Group  
1805 Crystal Drive  
Suite 1112 South  
Arlington, VA 22202

Al Astorga (1)  
Federal Aviation Administration  
(CAAG)  
American Embassy, Box 38  
APO New York, NY 09285-0001

Burton Chesterfield, DMA-603 (1)  
DOT Transportation Safety Inst.  
6500 South McArthur Blvd.  
Oklahoma City, OK 73125

FAA Fort Worth ACO (1)  
P. O. Box 1689  
Fort Worth, TX 76101

Faa Long Beach ACO (1)  
4344 Donald Douglas Drive  
Long Beach, CA 90808

FAA Los Angeles ACO (1)  
P. O. Box 92007  
Worldway Postal Center  
Hawthorne, CA 90009

FAA New York ACO (1)  
181 S. Frankline Ave., Room 202  
Valley Stream, NY 11581

FAA Seattle ACO (1)  
17900 Pacific Highway South  
C-68966  
Seattle, Washington 98168

FAA Wichita ACO (1)  
Mid Continent Airport  
Room 100 FAA Bldg.  
1891 Airport Road  
Wichita, KA 67209

Dr. Hans A. Krakauer (1)  
Deputy Chairman, International  
Airline Pilots Assoc. Group  
Apartado 97  
8200 Albufeira, Portugal

Geoffrey Lipman (1)  
Executive Director, President du  
Conseil  
International Foundation of  
Airline Passenger Assocs.  
Case Postale 463, 1215 Geneve  
15 Aeroport, Suisse, Geneva

2

Y

2

2

